


Ho₁₁Ge₁₀ Structure:

A10B11_tI84_139_dehim_eh2n-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://afLOW.org/p/HN10>

https://afLOW.org/p/A10B11_tI84_139_dehim_eh2n-001

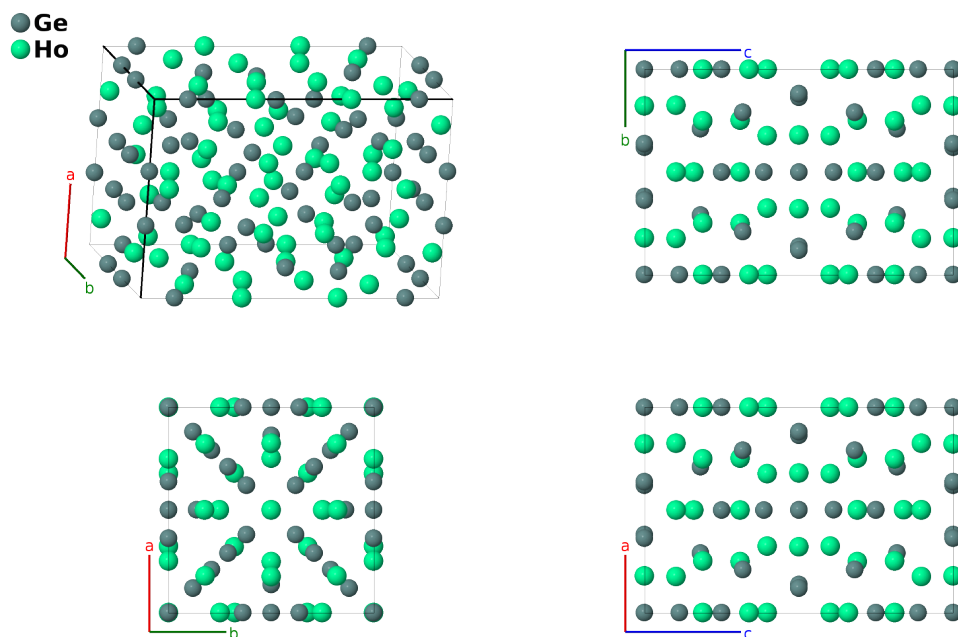


Prototype	Ge ₁₀ Ho ₁₁
AFLOW prototype label	A10B11_tI84_139_dehim_eh2n-001
ICSD	43052
Pearson symbol	tI84
Space group number	139
Space group symbol	<i>I4/mmm</i>
AFLOW prototype command	<code>afLOW --proto=A10B11_tI84_139_dehim_eh2n-001 --params=a, c/a, z₂, z₃, x₄, x₅, x₆, x₇, z₇, y₈, z₈, y₉, z₉</code>

Other compounds with this structure

Ba₁₁Bi₁₀, Ca₁₁Bi₁₀, Ca₁₁Sb₁₀, Eu₁₁Sb₁₀, Sr₁₁Bi₁₀, Sr₁₁Sb₁₀, Yb₁₁Sb₁₀, Yb₁₁Sb₁₀

Body-centered Tetragonal primitive vectors

$$\begin{aligned}
\mathbf{a}_1 &= -\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\
\mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\
\mathbf{a}_3 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} - \frac{1}{2}c \hat{\mathbf{z}}
\end{aligned}$$

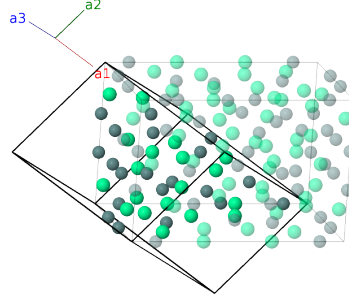

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= \frac{3}{4} \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4d)	Ge I
\mathbf{B}_2	$= \frac{1}{4} \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4d)	Ge I
\mathbf{B}_3	$= z_2 \mathbf{a}_1 + z_2 \mathbf{a}_2$	$=$	$cz_2 \hat{\mathbf{z}}$	(4e)	Ge II
\mathbf{B}_4	$= -z_2 \mathbf{a}_1 - z_2 \mathbf{a}_2$	$=$	$-cz_2 \hat{\mathbf{z}}$	(4e)	Ge II
\mathbf{B}_5	$= z_3 \mathbf{a}_1 + z_3 \mathbf{a}_2$	$=$	$cz_3 \hat{\mathbf{z}}$	(4e)	Ho I
\mathbf{B}_6	$= -z_3 \mathbf{a}_1 - z_3 \mathbf{a}_2$	$=$	$-cz_3 \hat{\mathbf{z}}$	(4e)	Ho I
\mathbf{B}_7	$= x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + 2x_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}}$	(8h)	Ge III
\mathbf{B}_8	$= -x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - 2x_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}}$	(8h)	Ge III
\mathbf{B}_9	$= x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2$	$=$	$-ax_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}}$	(8h)	Ge III
\mathbf{B}_{10}	$= -x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2$	$=$	$ax_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}}$	(8h)	Ge III
\mathbf{B}_{11}	$= x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + 2x_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + ax_5 \hat{\mathbf{y}}$	(8h)	Ho II
\mathbf{B}_{12}	$= -x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - 2x_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}}$	(8h)	Ho II
\mathbf{B}_{13}	$= x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2$	$=$	$-ax_5 \hat{\mathbf{x}} + ax_5 \hat{\mathbf{y}}$	(8h)	Ho II
\mathbf{B}_{14}	$= -x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2$	$=$	$ax_5 \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}}$	(8h)	Ho II
\mathbf{B}_{15}	$= x_6 \mathbf{a}_2 + x_6 \mathbf{a}_3$	$=$	$ax_6 \hat{\mathbf{x}}$	(8i)	Ge IV
\mathbf{B}_{16}	$= -x_6 \mathbf{a}_2 - x_6 \mathbf{a}_3$	$=$	$-ax_6 \hat{\mathbf{x}}$	(8i)	Ge IV
\mathbf{B}_{17}	$= x_6 \mathbf{a}_1 + x_6 \mathbf{a}_3$	$=$	$ax_6 \hat{\mathbf{y}}$	(8i)	Ge IV
\mathbf{B}_{18}	$= -x_6 \mathbf{a}_1 - x_6 \mathbf{a}_3$	$=$	$-ax_6 \hat{\mathbf{y}}$	(8i)	Ge IV
\mathbf{B}_{19}	$= (x_7 + z_7) \mathbf{a}_1 + (x_7 + z_7) \mathbf{a}_2 + 2x_7 \mathbf{a}_3$	$=$	$ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
\mathbf{B}_{20}	$= -(x_7 - z_7) \mathbf{a}_1 - (x_7 - z_7) \mathbf{a}_2 - 2x_7 \mathbf{a}_3$	$=$	$-ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
\mathbf{B}_{21}	$= (x_7 + z_7) \mathbf{a}_1 - (x_7 - z_7) \mathbf{a}_2$	$=$	$-ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
\mathbf{B}_{22}	$= -(x_7 - z_7) \mathbf{a}_1 + (x_7 + z_7) \mathbf{a}_2$	$=$	$ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
\mathbf{B}_{23}	$= (x_7 - z_7) \mathbf{a}_1 - (x_7 + z_7) \mathbf{a}_2$	$=$	$-ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
\mathbf{B}_{24}	$= -(x_7 + z_7) \mathbf{a}_1 + (x_7 - z_7) \mathbf{a}_2$	$=$	$ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
\mathbf{B}_{25}	$= (x_7 - z_7) \mathbf{a}_1 + (x_7 - z_7) \mathbf{a}_2 + 2x_7 \mathbf{a}_3$	$=$	$ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
\mathbf{B}_{26}	$= -(x_7 + z_7) \mathbf{a}_1 - (x_7 + z_7) \mathbf{a}_2 - 2x_7 \mathbf{a}_3$	$=$	$-ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
\mathbf{B}_{27}	$= (y_8 + z_8) \mathbf{a}_1 + z_8 \mathbf{a}_2 + y_8 \mathbf{a}_3$	$=$	$ay_8 \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}}$	(16n)	Ho III
\mathbf{B}_{28}	$= -(y_8 - z_8) \mathbf{a}_1 + z_8 \mathbf{a}_2 - y_8 \mathbf{a}_3$	$=$	$-ay_8 \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}}$	(16n)	Ho III

$$\begin{aligned}
\mathbf{B}_{29} &= z_8 \mathbf{a}_1 - (y_8 - z_8) \mathbf{a}_2 - y_8 \mathbf{a}_3 &= & -ay_8 \hat{\mathbf{x}} + cz_8 \hat{\mathbf{z}} & (16n) & \text{Ho III} \\
\mathbf{B}_{30} &= z_8 \mathbf{a}_1 + (y_8 + z_8) \mathbf{a}_2 + y_8 \mathbf{a}_3 &= & ay_8 \hat{\mathbf{x}} + cz_8 \hat{\mathbf{z}} & (16n) & \text{Ho III} \\
\mathbf{B}_{31} &= (y_8 - z_8) \mathbf{a}_1 - z_8 \mathbf{a}_2 + y_8 \mathbf{a}_3 &= & ay_8 \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}} & (16n) & \text{Ho III} \\
\mathbf{B}_{32} &= -(y_8 + z_8) \mathbf{a}_1 - z_8 \mathbf{a}_2 - y_8 \mathbf{a}_3 &= & -ay_8 \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}} & (16n) & \text{Ho III} \\
\mathbf{B}_{33} &= -z_8 \mathbf{a}_1 + (y_8 - z_8) \mathbf{a}_2 + y_8 \mathbf{a}_3 &= & ay_8 \hat{\mathbf{x}} - cz_8 \hat{\mathbf{z}} & (16n) & \text{Ho III} \\
\mathbf{B}_{34} &= -z_8 \mathbf{a}_1 - (y_8 + z_8) \mathbf{a}_2 - y_8 \mathbf{a}_3 &= & -ay_8 \hat{\mathbf{x}} - cz_8 \hat{\mathbf{z}} & (16n) & \text{Ho III} \\
\mathbf{B}_{35} &= (y_9 + z_9) \mathbf{a}_1 + z_9 \mathbf{a}_2 + y_9 \mathbf{a}_3 &= & ay_9 \hat{\mathbf{y}} + cz_9 \hat{\mathbf{z}} & (16n) & \text{Ho IV} \\
\mathbf{B}_{36} &= -(y_9 - z_9) \mathbf{a}_1 + z_9 \mathbf{a}_2 - y_9 \mathbf{a}_3 &= & -ay_9 \hat{\mathbf{y}} + cz_9 \hat{\mathbf{z}} & (16n) & \text{Ho IV} \\
\mathbf{B}_{37} &= z_9 \mathbf{a}_1 - (y_9 - z_9) \mathbf{a}_2 - y_9 \mathbf{a}_3 &= & -ay_9 \hat{\mathbf{x}} + cz_9 \hat{\mathbf{z}} & (16n) & \text{Ho IV} \\
\mathbf{B}_{38} &= z_9 \mathbf{a}_1 + (y_9 + z_9) \mathbf{a}_2 + y_9 \mathbf{a}_3 &= & ay_9 \hat{\mathbf{x}} + cz_9 \hat{\mathbf{z}} & (16n) & \text{Ho IV} \\
\mathbf{B}_{39} &= (y_9 - z_9) \mathbf{a}_1 - z_9 \mathbf{a}_2 + y_9 \mathbf{a}_3 &= & ay_9 \hat{\mathbf{y}} - cz_9 \hat{\mathbf{z}} & (16n) & \text{Ho IV} \\
\mathbf{B}_{40} &= -(y_9 + z_9) \mathbf{a}_1 - z_9 \mathbf{a}_2 - y_9 \mathbf{a}_3 &= & -ay_9 \hat{\mathbf{y}} - cz_9 \hat{\mathbf{z}} & (16n) & \text{Ho IV} \\
\mathbf{B}_{41} &= -z_9 \mathbf{a}_1 + (y_9 - z_9) \mathbf{a}_2 + y_9 \mathbf{a}_3 &= & ay_9 \hat{\mathbf{x}} - cz_9 \hat{\mathbf{z}} & (16n) & \text{Ho IV} \\
\mathbf{B}_{42} &= -z_9 \mathbf{a}_1 - (y_9 + z_9) \mathbf{a}_2 - y_9 \mathbf{a}_3 &= & -ay_9 \hat{\mathbf{x}} - cz_9 \hat{\mathbf{z}} & (16n) & \text{Ho IV}
\end{aligned}$$

References

- [1] G. S. Smith, Q. Johnson, and A. G. Tharp, *The Crystal Structure of Ho₁₁Ga₁₀*, *Acta Cryst.* **23**, 640–644 (1967), doi:10.1107/S0365110X67003329.

Found in

- [1] A. Rehr and S. M. Kauzlarich, *Sr₁₁Sb₁₀*, *Acta Crystallogr. Sect. C* **50**, 1859–1861 (1994), doi:10.1107/S0108270194003951.