


Palladseite (Pd₁₇Se₁₅) Structure: A17B15_cP64_207_acfk_eij-001

This structure originally had the label A17B15_cP64_207_acfk_eij. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043

<https://aflow.org/p/8LH0>

https://aflow.org/p/A17B15_cP64_207_acfk_eij-001

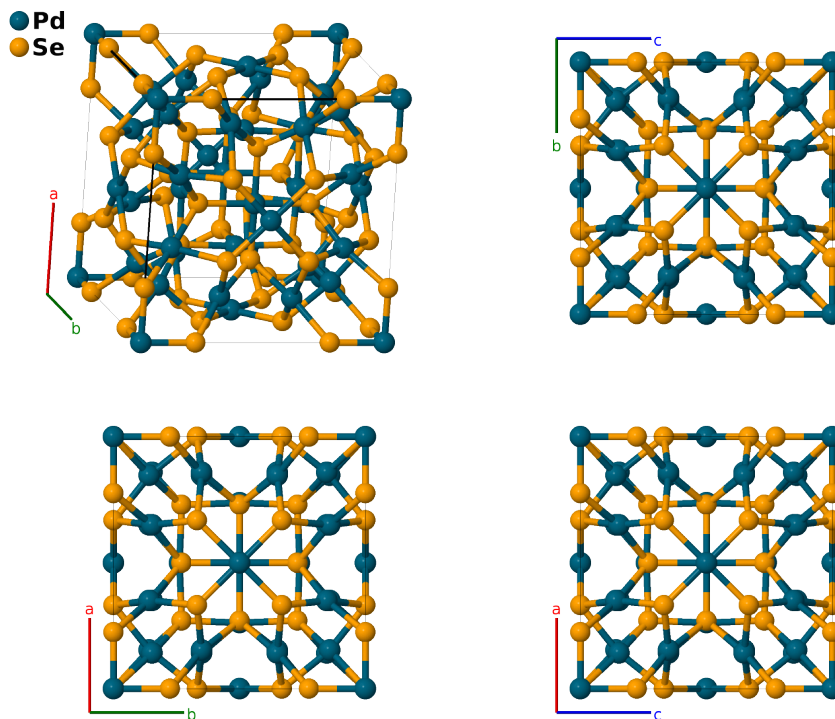

Prototype	Pd ₁₇ Se ₁₅
AFLOW prototype label	A17B15_cP64_207_acfk_eij-001
Mineral name	palladseite
ICSD	none
Pearson symbol	cP64
Space group number	207
Space group symbol	<i>P</i> 432
AFLOW prototype command	<code>aflow --proto=A17B15_cP64_207_acfk_eij-001 --params=a, x₃, x₄, y₅, y₆, x₇, y₇, z₇</code>


Other compounds with this structure

Rh₁₇S₁₅

- (Geller, 1962) determined that $\text{Pd}_{17}\text{Se}_{15}$ could be in space group $Pm\bar{3}m$ #221, $P\bar{4}3m$ #215, or $P432$ #207 (this structure), and finds that $Pm\bar{3}m$ gives the best fit to single-crystal X-ray diffraction pattern, although the parameter fit for the all of the Wyckoff sites did not converge. We therefore present all three structure possibilities.
- We shifted the coordinates of (Geller, 1962) to move the Pd-I atom from the center of the cubic cell, Wyckoff position (1b), to the origin, Wyckoff position (1a).

Simple Cubic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= a \hat{\mathbf{z}} \end{aligned}$$

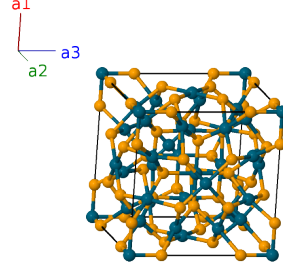

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= 0$	$=$	0	(1a)	Pd I
\mathbf{B}_2	$= \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(3c)	Pd II
\mathbf{B}_3	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{z}}$	(3c)	Pd II
\mathbf{B}_4	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}}$	(3c)	Pd II
\mathbf{B}_5	$= x_3 \mathbf{a}_1$	$=$	$ax_3 \hat{\mathbf{x}}$	(6e)	Se I
\mathbf{B}_6	$= -x_3 \mathbf{a}_1$	$=$	$-ax_3 \hat{\mathbf{x}}$	(6e)	Se I
\mathbf{B}_7	$= x_3 \mathbf{a}_2$	$=$	$ax_3 \hat{\mathbf{y}}$	(6e)	Se I
\mathbf{B}_8	$= -x_3 \mathbf{a}_2$	$=$	$-ax_3 \hat{\mathbf{y}}$	(6e)	Se I
\mathbf{B}_9	$= x_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{z}}$	(6e)	Se I
\mathbf{B}_{10}	$= -x_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{z}}$	(6e)	Se I
\mathbf{B}_{11}	$= x_4 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f)	Pd III
\mathbf{B}_{12}	$= -x_4 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f)	Pd III
\mathbf{B}_{13}	$= \frac{1}{2} \mathbf{a}_1 + x_4 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f)	Pd III
\mathbf{B}_{14}	$= \frac{1}{2} \mathbf{a}_1 - x_4 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f)	Pd III
\mathbf{B}_{15}	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + x_4 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + ax_4 \hat{\mathbf{z}}$	(6f)	Pd III
\mathbf{B}_{16}	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 - x_4 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} - ax_4 \hat{\mathbf{z}}$	(6f)	Pd III
\mathbf{B}_{17}	$= y_5 \mathbf{a}_2 + y_5 \mathbf{a}_3$	$=$	$ay_5 \hat{\mathbf{y}} + ay_5 \hat{\mathbf{z}}$	(12i)	Se II
\mathbf{B}_{18}	$= -y_5 \mathbf{a}_2 + y_5 \mathbf{a}_3$	$=$	$-ay_5 \hat{\mathbf{y}} + ay_5 \hat{\mathbf{z}}$	(12i)	Se II
\mathbf{B}_{19}	$= y_5 \mathbf{a}_2 - y_5 \mathbf{a}_3$	$=$	$ay_5 \hat{\mathbf{y}} - ay_5 \hat{\mathbf{z}}$	(12i)	Se II
\mathbf{B}_{20}	$= -y_5 \mathbf{a}_2 - y_5 \mathbf{a}_3$	$=$	$-ay_5 \hat{\mathbf{y}} - ay_5 \hat{\mathbf{z}}$	(12i)	Se II
\mathbf{B}_{21}	$= y_5 \mathbf{a}_1 + y_5 \mathbf{a}_3$	$=$	$ay_5 \hat{\mathbf{x}} + ay_5 \hat{\mathbf{z}}$	(12i)	Se II
\mathbf{B}_{22}	$= y_5 \mathbf{a}_1 - y_5 \mathbf{a}_3$	$=$	$ay_5 \hat{\mathbf{x}} - ay_5 \hat{\mathbf{z}}$	(12i)	Se II
\mathbf{B}_{23}	$= -y_5 \mathbf{a}_1 + y_5 \mathbf{a}_3$	$=$	$-ay_5 \hat{\mathbf{x}} + ay_5 \hat{\mathbf{z}}$	(12i)	Se II
\mathbf{B}_{24}	$= -y_5 \mathbf{a}_1 - y_5 \mathbf{a}_3$	$=$	$-ay_5 \hat{\mathbf{x}} - ay_5 \hat{\mathbf{z}}$	(12i)	Se II

References

- [1] S. Geller, *The Crystal Structure of Pd₁₇Se₁₅*, *Acta Cryst.* **15**, 713–721 (1962), doi:10.1107/S0365110X62001929.

Found in

- [1] D. Barthelmy, *Mineralogy Database* (2012). Palladseite Mineral Data.