


Y₃Rh₂Si₂ Structure: A2B2C3_oP28_57_e_cd_de-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/0RQ9>

https://aflow.org/prototype-encyclopedia/A2B2C3_oP28_57_e_cd_de-001

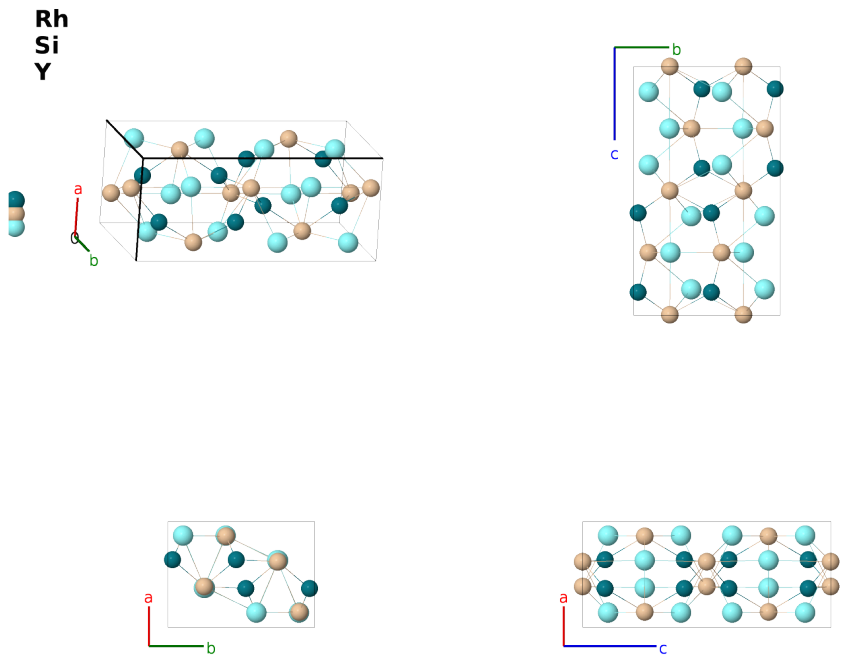

Prototype	Rh ₂ Si ₂ Y ₃
AFLOW prototype label	A2B2C3_oP28_57_e_cd_de-001
ICSD	30725
CCDC	1604966
Pearson symbol	oP28
Space group number	57
Space group symbol	<i>Pbcm</i>
AFLOW prototype command	<pre>aflow --proto=A2B2C3_oP28_57_e_cd_de-001 --params=a, b/a, c/a, x₁, x₂, y₂, x₃, y₃, x₄, y₄, z₄, x₅, y₅, z₅</pre>

Other compounds with this structure


Ce₃Ga₂Ni₂, Ce₃Ga₂Pd₂, Ce₃Ga₂Pt₂, Ce₃Ge₂Rh₂, Ce₃Ge₂Ru₂, Ce₃Si₂Rh₂, La₃Ga₂Ni₂, La₃Ge₂Ru₂, Nd₃Ge₂Ru₂, Pr₃Ga₂Ni₂, Pr₃Ge₂Ru₂, Sm₃Ge₂Ru₂

Simple Orthorhombic primitive vectors

$$\mathbf{a}_1 = a \hat{\mathbf{x}}$$

$$\mathbf{a}_2 = b \hat{\mathbf{y}}$$

$$\mathbf{a}_3 = c \hat{\mathbf{z}}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2$	$=$	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}}$	(4c)	Si I
$\mathbf{B}_2$	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4c)	Si I
$\mathbf{B}_3$	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2$	$=$	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}}$	(4c)	Si I
$\mathbf{B}_4$	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4c)	Si I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4d)	Si II
$\mathbf{B}_6$	$= -x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(4d)	Si II
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4d)	Si II
$\mathbf{B}_8$	$= x_2 \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(4d)	Si II
$\mathbf{B}_9$	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4d)	Y I
$\mathbf{B}_{10}$	$= -x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(4d)	Y I
$\mathbf{B}_{11}$	$= -x_3 \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4d)	Y I
$\mathbf{B}_{12}$	$= x_3 \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(4d)	Y I
$\mathbf{B}_{13}$	$= x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8e)	Rh I
$\mathbf{B}_{14}$	$= -x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(8e)	Rh I
$\mathbf{B}_{15}$	$= -x_4 \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + b(y_4 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \hat{\mathbf{z}}$	(8e)	Rh I
$\mathbf{B}_{16}$	$= x_4 \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} - b(y_4 - \frac{1}{2}) \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(8e)	Rh I
$\mathbf{B}_{17}$	$= -x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(8e)	Rh I
$\mathbf{B}_{18}$	$= x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \hat{\mathbf{z}}$	(8e)	Rh I
$\mathbf{B}_{19}$	$= x_4 \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} - b(y_4 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(8e)	Rh I
$\mathbf{B}_{20}$	$= -x_4 \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + b(y_4 + \frac{1}{2}) \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8e)	Rh I
$\mathbf{B}_{21}$	$= x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(8e)	Y II
$\mathbf{B}_{22}$	$= -x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(8e)	Y II
$\mathbf{B}_{23}$	$= -x_5 \mathbf{a}_1 + (y_5 + \frac{1}{2}) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} + b(y_5 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \hat{\mathbf{z}}$	(8e)	Y II
$\mathbf{B}_{24}$	$= x_5 \mathbf{a}_1 - (y_5 - \frac{1}{2}) \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} - b(y_5 - \frac{1}{2}) \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$	(8e)	Y II

$$\begin{aligned}
\mathbf{B}_{25} &= -x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3 &= -ax_5 \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}} & (8e) & \text{Y II} \\
\mathbf{B}_{26} &= x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 - \left(z_5 - \frac{1}{2}\right) \mathbf{a}_3 &= ax_5 \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} - c \left(z_5 - \frac{1}{2}\right) \hat{\mathbf{z}} & (8e) & \text{Y II} \\
\mathbf{B}_{27} &= x_5 \mathbf{a}_1 - \left(y_5 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_5 + \frac{1}{2}\right) \mathbf{a}_3 &= ax_5 \hat{\mathbf{x}} - b \left(y_5 - \frac{1}{2}\right) \hat{\mathbf{y}} + c \left(z_5 + \frac{1}{2}\right) \hat{\mathbf{z}} & (8e) & \text{Y II} \\
\mathbf{B}_{28} &= -x_5 \mathbf{a}_1 + \left(y_5 + \frac{1}{2}\right) \mathbf{a}_2 + z_5 \mathbf{a}_3 &= -ax_5 \hat{\mathbf{x}} + b \left(y_5 + \frac{1}{2}\right) \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}} & (8e) & \text{Y II}
\end{aligned}$$

References

- [1] J. M. Moreau, D. Paccard, and L. Paccard, *Dirhodium triyttrium disilicide*, $Y_3Rh_2Si_2$, Acta Crystallogr. Sect. C **40**, 1311–1312 (1984), doi:10.1107/S0108270184007770.

First cited in

N. Anderson, M. J. Mehl, H. Eckert, S. Divilov, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 5*. Submitted to Computational Materials Science (2026).