


# Li<sub>2</sub>PrO<sub>3</sub> Structure: A2B3C\_oC12\_65\_h\_ah\_b-001

This structure originally had the label A2B3C\_oC12\_65\_h\_bh\_a. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://afLOW.org/p/2B54>

[https://afLOW.org/p/A2B3C\\_oC12\\_65\\_h\\_ah\\_b-001](https://afLOW.org/p/A2B3C_oC12_65_h_ah_b-001)

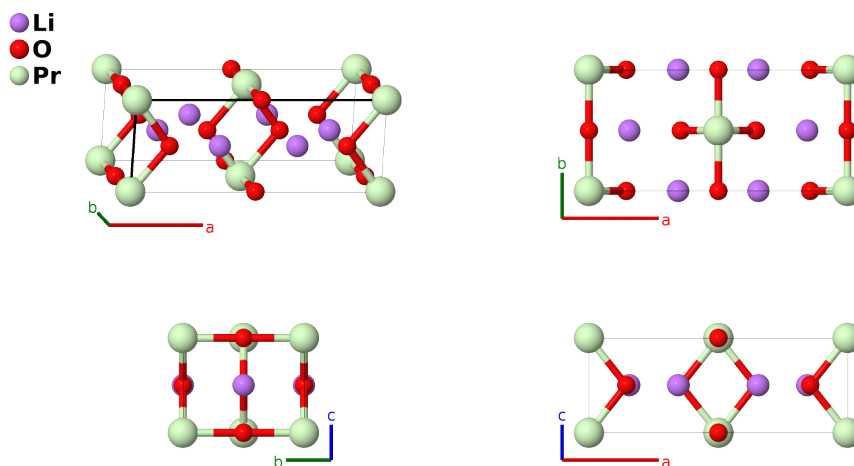

Prototype	Li <sub>2</sub> O <sub>3</sub> Pr
AFLOW prototype label	A2B3C_oC12_65_h_ah_b-001
ICSD	154704
Pearson symbol	oC12
Space group number	65
Space group symbol	<i>Cmmm</i>
AFLOW prototype command	afLOW --proto=A2B3C_oC12_65_h_ah_b-001 --params=a, b/a, c/a, x <sub>3</sub> , x <sub>4</sub>


## Other compounds with this structure

Na<sub>2</sub>PrO<sub>3</sub>

- Data was taken at 20K.

## Base-centered Orthorhombic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a \hat{x} - \frac{1}{2}b \hat{y} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{x} + \frac{1}{2}b \hat{y} \\ \mathbf{a}_3 &= c \hat{z} \end{aligned}$$

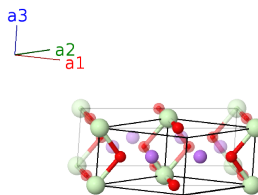

---

## Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	=	0	=	0	(2a) O I
$\mathbf{B}_2$	=	$\frac{1}{2}\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2$	=	$\frac{1}{2}a\hat{\mathbf{x}}$	(2b) Pr I
$\mathbf{B}_3$	=	$x_3\mathbf{a}_1 + x_3\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	=	$ax_3\hat{\mathbf{x}} + \frac{1}{2}c\hat{\mathbf{z}}$	(4h) Li I
$\mathbf{B}_4$	=	$-x_3\mathbf{a}_1 - x_3\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	=	$-ax_3\hat{\mathbf{x}} + \frac{1}{2}c\hat{\mathbf{z}}$	(4h) Li I
$\mathbf{B}_5$	=	$x_4\mathbf{a}_1 + x_4\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	=	$ax_4\hat{\mathbf{x}} + \frac{1}{2}c\hat{\mathbf{z}}$	(4h) O II
$\mathbf{B}_6$	=	$-x_4\mathbf{a}_1 - x_4\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	=	$-ax_4\hat{\mathbf{x}} + \frac{1}{2}c\hat{\mathbf{z}}$	(4h) O II

## References

- [1] Y. Hinatsu and Y. Doi, *Crystal structures and magnetic properties of alkali-metal lanthanide oxides  $A_2LnO_3$  ( $A = Li, Na; Ln = Ce, Pr, Tb$ )*, J. Alloys Compd. **418**, 155–160 (2006), doi:10.1016/j.jallcom.2005.08.100.