


SrAu₃Al₂ Structure:

A2B3C_oP24_62_d_3c_c-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/DAG0>

https://aflow.org/p/A2B3C_oP24_62_d_3c_c-001

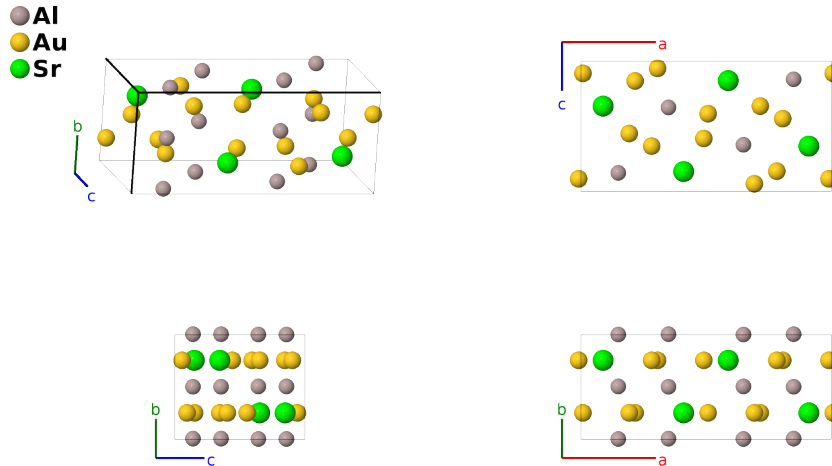

Prototype	Al ₂ Au ₃ Sr
AFLOW prototype label	A2B3C_oP24_62_d_3c_c-001
ICSD	429904
Pearson symbol	oP24
Space group number	62
Space group symbol	<i>Pnma</i>
AFLOW prototype command	aflow --proto=A2B3C_oP24_62_d_3c_c-001 --params=a, b/a, c/a, x ₁ , z ₁ , x ₂ , z ₂ , x ₃ , z ₃ , x ₄ , z ₄ , x ₅ , y ₅ , z ₅

Other compounds with this structure

EuAu₃Al₂, RuAu₃Ga₂


- This is the ternary form of the SrZn₅ structure.

Simple Orthorhombic primitive vectors

$$\mathbf{a}_1 = a \hat{\mathbf{x}}$$

$$\mathbf{a}_2 = b \hat{\mathbf{y}}$$

$$\mathbf{a}_3 = c \hat{\mathbf{z}}$$

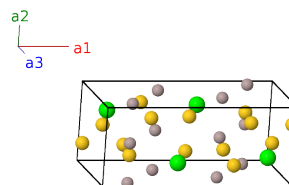

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4c)	Au I
\mathbf{B}_2	$= -(x_1 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_1 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Au I
\mathbf{B}_3	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	(4c)	Au I
\mathbf{B}_4	$= (x_1 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_1 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Au I
\mathbf{B}_5	$= x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4c)	Au II
\mathbf{B}_6	$= -(x_2 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Au II
\mathbf{B}_7	$= -x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4c)	Au II
\mathbf{B}_8	$= (x_2 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Au II
\mathbf{B}_9	$= x_3 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(4c)	Au III
\mathbf{B}_{10}	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Au III
\mathbf{B}_{11}	$= -x_3 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(4c)	Au III
\mathbf{B}_{12}	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Au III
\mathbf{B}_{13}	$= x_4 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(4c)	Sr I
\mathbf{B}_{14}	$= -(x_4 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_4 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Sr I
\mathbf{B}_{15}	$= -x_4 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(4c)	Sr I
\mathbf{B}_{16}	$= (x_4 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_4 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Sr I
\mathbf{B}_{17}	$= x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(8d)	Al I
\mathbf{B}_{18}	$= -(x_5 - \frac{1}{2}) \mathbf{a}_1 - y_5 \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_5 - \frac{1}{2}) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Al I
\mathbf{B}_{19}	$= -x_5 \mathbf{a}_1 + (y_5 + \frac{1}{2}) \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} + b(y_5 + \frac{1}{2}) \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$	(8d)	Al I
\mathbf{B}_{20}	$= (x_5 + \frac{1}{2}) \mathbf{a}_1 - (y_5 - \frac{1}{2}) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_5 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_5 - \frac{1}{2}) \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Al I
\mathbf{B}_{21}	$= -x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$	(8d)	Al I
\mathbf{B}_{22}	$= (x_5 + \frac{1}{2}) \mathbf{a}_1 + y_5 \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_5 + \frac{1}{2}) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Al I
\mathbf{B}_{23}	$= x_5 \mathbf{a}_1 - (y_5 - \frac{1}{2}) \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} - b(y_5 - \frac{1}{2}) \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(8d)	Al I
\mathbf{B}_{24}	$= -(x_5 - \frac{1}{2}) \mathbf{a}_1 + (y_5 + \frac{1}{2}) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_5 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_5 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Al I

References

- [1] B. Gerke and R. Pöttgen, *Alkaline earth-gold-aluminides: synthesis and structure of SrAu₃Al₂, SrAu_{2.83}Al_{2.17}, BaAu_{2.89}Al_{2.11} and BaAu_{7.09}Al_{5.91}*, Z. Naturforsch. B **70**, 903–909 (2015), doi:10.1515/znb-2015-0119.

Found in

- [1] J.-P. Schmiegel, T. Block, B. Gerke, T. Fickenscher, R. S. Touzani, B. P. T. Fokwa, and O. Janka, *EuAu₃Al₂: Crystal and Electronic Structures and Spectroscopic, Magnetic, and Magnetocaloric Properties*, Inorg. Chem. **55**, 9057–0964 (2016), doi:10.1021/acs.inorgchem.6b01530.