


Co₈Zn₉Mn₃ Structure: A2B3_cP20_213_c_d-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/KXT1>

https://aflow.org/p/A2B3_cP20_213_c_d-001

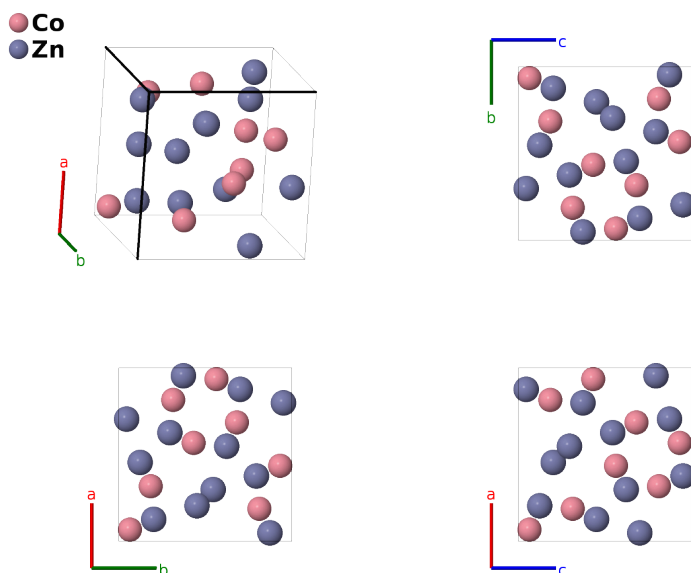


Prototype	Co ₈ Mn ₃ Zn ₉
AFLOW prototype label	A2B3_cP20_213_c_d-001
ICSD	19272
Pearson symbol	cP20
Space group number	213
Space group symbol	$P4_132$
AFLOW prototype command	<code>aflow --proto=A2B3_cP20_213_c_d-001 --params=a, x₁, y₂</code>

- The composition of the site we label “Co (8c)” is actually Co_{7.616}Mn_{0.834}, and the site labeled “Zn (12d)” is Zn_{8.7756}Co_{0.684}Mn_{2.448}. (Bocarsly, 2019)
- Many other compositions are observed.
- We use the synchrotron data taken by (Bocarsly, 2019) at 100K.
- This structure can also be found in the enantiomorphic space group $P4_332$ #212.

Simple Cubic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= a \hat{\mathbf{z}}\end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2 + x_1 \mathbf{a}_3$	=	$ax_1 \hat{\mathbf{x}} + ax_1 \hat{\mathbf{y}} + ax_1 \hat{\mathbf{z}}$	(8c)	Co I
\mathbf{B}_2	$-(x_1 - \frac{1}{2}) \mathbf{a}_1 - x_1 \mathbf{a}_2 + (x_1 + \frac{1}{2}) \mathbf{a}_3$	=	$-a(x_1 - \frac{1}{2}) \hat{\mathbf{x}} - ax_1 \hat{\mathbf{y}} + a(x_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(8c)	Co I
\mathbf{B}_3	$-x_1 \mathbf{a}_1 + (x_1 + \frac{1}{2}) \mathbf{a}_2 - (x_1 - \frac{1}{2}) \mathbf{a}_3$	=	$-ax_1 \hat{\mathbf{x}} + a(x_1 + \frac{1}{2}) \hat{\mathbf{y}} - a(x_1 - \frac{1}{2}) \hat{\mathbf{z}}$	(8c)	Co I
\mathbf{B}_4	$(x_1 + \frac{1}{2}) \mathbf{a}_1 - (x_1 - \frac{1}{2}) \mathbf{a}_2 - x_1 \mathbf{a}_3$	=	$a(x_1 + \frac{1}{2}) \hat{\mathbf{x}} - a(x_1 - \frac{1}{2}) \hat{\mathbf{y}} - ax_1 \hat{\mathbf{z}}$	(8c)	Co I
\mathbf{B}_5	$(x_1 + \frac{3}{4}) \mathbf{a}_1 + (x_1 + \frac{1}{4}) \mathbf{a}_2 - (x_1 - \frac{1}{4}) \mathbf{a}_3$	=	$a(x_1 + \frac{3}{4}) \hat{\mathbf{x}} + a(x_1 + \frac{1}{4}) \hat{\mathbf{y}} - a(x_1 - \frac{1}{4}) \hat{\mathbf{z}}$	(8c)	Co I
\mathbf{B}_6	$-(x_1 - \frac{3}{4}) \mathbf{a}_1 - (x_1 - \frac{3}{4}) \mathbf{a}_2 - (x_1 - \frac{3}{4}) \mathbf{a}_3$	=	$-a(x_1 - \frac{3}{4}) \hat{\mathbf{x}} - a(x_1 - \frac{3}{4}) \hat{\mathbf{y}} - a(x_1 - \frac{3}{4}) \hat{\mathbf{z}}$	(8c)	Co I
\mathbf{B}_7	$(x_1 + \frac{1}{4}) \mathbf{a}_1 - (x_1 - \frac{1}{4}) \mathbf{a}_2 + (x_1 + \frac{3}{4}) \mathbf{a}_3$	=	$a(x_1 + \frac{1}{4}) \hat{\mathbf{x}} - a(x_1 - \frac{1}{4}) \hat{\mathbf{y}} + a(x_1 + \frac{3}{4}) \hat{\mathbf{z}}$	(8c)	Co I
\mathbf{B}_8	$-(x_1 - \frac{1}{4}) \mathbf{a}_1 + (x_1 + \frac{3}{4}) \mathbf{a}_2 + (x_1 + \frac{1}{4}) \mathbf{a}_3$	=	$-a(x_1 - \frac{1}{4}) \hat{\mathbf{x}} + a(x_1 + \frac{3}{4}) \hat{\mathbf{y}} + a(x_1 + \frac{1}{4}) \hat{\mathbf{z}}$	(8c)	Co I
\mathbf{B}_9	$\frac{1}{8} \mathbf{a}_1 + y_2 \mathbf{a}_2 + (y_2 + \frac{1}{4}) \mathbf{a}_3$	=	$\frac{1}{8} a \hat{\mathbf{x}} + ay_2 \hat{\mathbf{y}} + a(y_2 + \frac{1}{4}) \hat{\mathbf{z}}$	(12d)	Zn I
\mathbf{B}_{10}	$\frac{3}{8} \mathbf{a}_1 - y_2 \mathbf{a}_2 + (y_2 + \frac{3}{4}) \mathbf{a}_3$	=	$\frac{3}{8} a \hat{\mathbf{x}} - ay_2 \hat{\mathbf{y}} + a(y_2 + \frac{3}{4}) \hat{\mathbf{z}}$	(12d)	Zn I
\mathbf{B}_{11}	$\frac{7}{8} \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 - (y_2 - \frac{1}{4}) \mathbf{a}_3$	=	$\frac{7}{8} a \hat{\mathbf{x}} + a(y_2 + \frac{1}{2}) \hat{\mathbf{y}} - a(y_2 - \frac{1}{4}) \hat{\mathbf{z}}$	(12d)	Zn I
\mathbf{B}_{12}	$\frac{5}{8} \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 - (y_2 - \frac{3}{4}) \mathbf{a}_3$	=	$\frac{5}{8} a \hat{\mathbf{x}} - a(y_2 - \frac{1}{2}) \hat{\mathbf{y}} - a(y_2 - \frac{3}{4}) \hat{\mathbf{z}}$	(12d)	Zn I
\mathbf{B}_{13}	$(y_2 + \frac{1}{4}) \mathbf{a}_1 + \frac{1}{8} \mathbf{a}_2 + y_2 \mathbf{a}_3$	=	$a(y_2 + \frac{1}{4}) \hat{\mathbf{x}} + \frac{1}{8} a \hat{\mathbf{y}} + ay_2 \hat{\mathbf{z}}$	(12d)	Zn I
\mathbf{B}_{14}	$(y_2 + \frac{3}{4}) \mathbf{a}_1 + \frac{3}{8} \mathbf{a}_2 - y_2 \mathbf{a}_3$	=	$a(y_2 + \frac{3}{4}) \hat{\mathbf{x}} + \frac{3}{8} a \hat{\mathbf{y}} - ay_2 \hat{\mathbf{z}}$	(12d)	Zn I
\mathbf{B}_{15}	$-(y_2 - \frac{1}{4}) \mathbf{a}_1 + \frac{7}{8} \mathbf{a}_2 + (y_2 + \frac{1}{2}) \mathbf{a}_3$	=	$-a(y_2 - \frac{1}{4}) \hat{\mathbf{x}} + \frac{7}{8} a \hat{\mathbf{y}} + a(y_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(12d)	Zn I
\mathbf{B}_{16}	$-(y_2 - \frac{3}{4}) \mathbf{a}_1 + \frac{5}{8} \mathbf{a}_2 - (y_2 - \frac{1}{2}) \mathbf{a}_3$	=	$-a(y_2 - \frac{3}{4}) \hat{\mathbf{x}} + \frac{5}{8} a \hat{\mathbf{y}} - a(y_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(12d)	Zn I
\mathbf{B}_{17}	$y_2 \mathbf{a}_1 + (y_2 + \frac{1}{4}) \mathbf{a}_2 + \frac{1}{8} \mathbf{a}_3$	=	$ay_2 \hat{\mathbf{x}} + a(y_2 + \frac{1}{4}) \hat{\mathbf{y}} + \frac{1}{8} a \hat{\mathbf{z}}$	(12d)	Zn I
\mathbf{B}_{18}	$-y_2 \mathbf{a}_1 + (y_2 + \frac{3}{4}) \mathbf{a}_2 + \frac{3}{8} \mathbf{a}_3$	=	$-ay_2 \hat{\mathbf{x}} + a(y_2 + \frac{3}{4}) \hat{\mathbf{y}} + \frac{3}{8} a \hat{\mathbf{z}}$	(12d)	Zn I
\mathbf{B}_{19}	$(y_2 + \frac{1}{2}) \mathbf{a}_1 - (y_2 - \frac{1}{4}) \mathbf{a}_2 + \frac{7}{8} \mathbf{a}_3$	=	$a(y_2 + \frac{1}{2}) \hat{\mathbf{x}} - a(y_2 - \frac{1}{4}) \hat{\mathbf{y}} + \frac{7}{8} a \hat{\mathbf{z}}$	(12d)	Zn I
\mathbf{B}_{20}	$-(y_2 - \frac{1}{2}) \mathbf{a}_1 - (y_2 - \frac{3}{4}) \mathbf{a}_2 + \frac{5}{8} \mathbf{a}_3$	=	$-a(y_2 - \frac{1}{2}) \hat{\mathbf{x}} - a(y_2 - \frac{3}{4}) \hat{\mathbf{y}} + \frac{5}{8} a \hat{\mathbf{z}}$	(12d)	Zn I

References

- [1] J. D. Bocarsly, C. Heikes, C. M. Brown, S. D. Wilson, and R. Seshadri, *Deciphering structural and magnetic disorder in the chiral skyrmion host materials $Co_xZn_yMn_z$ ($x + y + z = 20$)*, Phys. Rev. Materials **3**, 014402 (2019), doi:10.1103/PhysRevMaterials.3.014402.