


Ti₃Al₂N₂ Structure: A2B4C5_hP22_186_ab_4b_a4b-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/7JMK>

https://aflow.org/p/A2B4C5_hP22_186_ab_4b_a4b-001

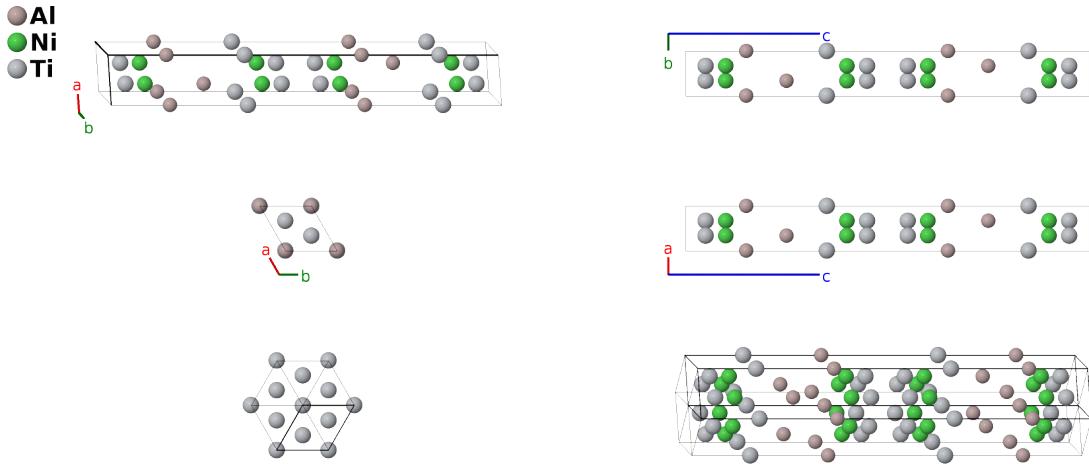


Prototype	Al ₂ N ₂ Ti ₂
AFLOW prototype label	A2B4C5_hP22_186_ab_4b_a4b-001
ICSD	52643
Pearson symbol	hP22
Space group number	186
Space group symbol	$P6_3mc$
AFLOW prototype command	<code>aflow --proto=A2B4C5_hP22_186_ab_4b_a4b-001 --params=a,c/a,z₁,z₂,z₃,z₄,z₅,z₆,z₇,z₈,z₉,z₁₀,z₁₁</code>

- This compound only exists at temperatures near 1573K, where this data was taken.
- (Schuster, 1984) placed this system in the trigonal space group $P31c$ #159. The (2a) and (2b) Wyckoff positions for space group #159 are identical to those in the hexagonal space group $P6_3mc$ #186, so we follow (Cenzual, 1991) and place this in the higher symmetry space group.
- The origin of the z -axis in space group $P6_3mc$ is arbitrary. We use the origin specified by (Schuster, 1984).
- Most of the Wyckoff positions in this structure are only partially occupied:
 - Sites Al-I and Ti-I are fully occupied.
 - Sites Ni-I, Ni-II, Ti-II, and Ti-III are 80% occupied.
 - Sites Ni-III, Ni-IV, Ti-IV, and Ti-V are 20% occupied.
- This explains the short Ti-N bond lengths shown in the figure – for any given Ti-N pair, only one of the two atoms is actually present.

Hexagonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_3 &= c\hat{\mathbf{z}}\end{aligned}$$



Basis vectors

	Lattice coordinates	=	Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$z_1 \mathbf{a}_3$	=	$cz_1 \hat{\mathbf{z}}$	(2a)	Al I
\mathbf{B}_2	$(z_1 + \frac{1}{2}) \mathbf{a}_3$	=	$c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(2a)	Al I
\mathbf{B}_3	$z_2 \mathbf{a}_3$	=	$cz_2 \hat{\mathbf{z}}$	(2a)	Ti I
\mathbf{B}_4	$(z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(2a)	Ti I
\mathbf{B}_5	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(2b)	Al II
\mathbf{B}_6	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	Al II
\mathbf{B}_7	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(2b)	Ni I
\mathbf{B}_8	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	Ni I
\mathbf{B}_9	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_5 \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(2b)	Ni II
\mathbf{B}_{10}	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	Ni II
\mathbf{B}_{11}	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_6 \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}}$	(2b)	Ni III
\mathbf{B}_{12}	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	Ni III
\mathbf{B}_{13}	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_7 \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(2b)	Ni IV
\mathbf{B}_{14}	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 + (z_7 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	Ni IV
\mathbf{B}_{15}	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_8 \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}}$	(2b)	Ti II
\mathbf{B}_{16}	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 + (z_8 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + c(z_8 + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	Ti II
\mathbf{B}_{17}	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_9 \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_9 \hat{\mathbf{z}}$	(2b)	Ti III
\mathbf{B}_{18}	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 + (z_9 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + c(z_9 + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	Ti III
\mathbf{B}_{19}	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_{10} \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_{10} \hat{\mathbf{z}}$	(2b)	Ti IV
\mathbf{B}_{20}	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 + (z_{10} + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + c(z_{10} + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	Ti IV
\mathbf{B}_{21}	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_{11} \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_{11} \hat{\mathbf{z}}$	(2b)	Ti V
\mathbf{B}_{22}	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 + (z_{11} + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + c(z_{11} + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	Ti V

References

- [1] J. C. Schuster and J. Bauer, *The Ternary System Titanium-Aluminum-Nitrogen*, J. Solid State Chem. **53**, 260–265 (1984), doi:10.1016/0022-4596(84)90100-2.

Found in

- [1] K. Cenzual, L. M. Gelato, M. Penzo, and E. Parthé, *Inorganic structure types with revised space groups. I*, Acta Crystallogr. Sect. B **47**, 433–439 (1991), doi:10.1107/S0108768191000903.