


B₂Pd₅ Structure: A2B5_mC28_15_f_e2f-001

This structure originally had the label A2B5_mC28_15_f_e2f. Calls to that address will be redirected here.

Cite this page as: M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017

<https://aflow.org/p/CZ5K>

https://aflow.org/p/A2B5_mC28_15_f_e2f-001

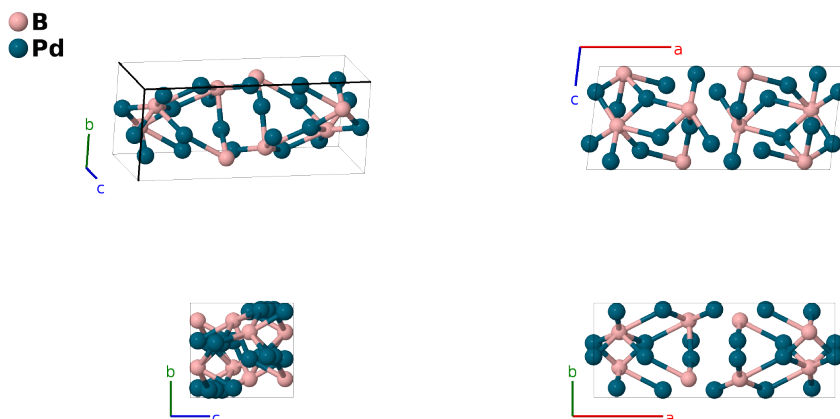

Prototype	B ₂ Pd ₅
AFLOW prototype label	A2B5_mC28_15_f_e2f-001
ICSD	43513
Pearson symbol	mC28
Space group number	15
Space group symbol	C2/c
AFLOW prototype command	aflow --proto=A2B5_mC28_15_f_e2f-001 --params=a, b/a, c/a, β, y ₁ , x ₂ , y ₂ , z ₂ , x ₃ , y ₃ , z ₃ , x ₄ , y ₄ , z ₄


Other compounds with this structure

C₂Mn₅

- B₂Pd₅ and Nb₂O₅ share the same AFLOW prototype label, A2B5_mC28_15_f_e2f, but have substantially different environments around each atom. The structures are generated by the same symmetry operations with different sets of parameters (--params) specified in their corresponding CIF files.

Base-centered Monoclinic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}} \end{aligned}$$

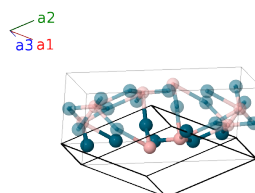

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= -y_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Pd I
\mathbf{B}_2	$= y_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Pd I
\mathbf{B}_3	$= (x_2 - y_2) \mathbf{a}_1 + (x_2 + y_2) \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(8f)	B I
\mathbf{B}_4	$= -(x_2 + y_2) \mathbf{a}_1 - (x_2 - y_2) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_2 + c(z_2 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	B I
\mathbf{B}_5	$= -(x_2 - y_2) \mathbf{a}_1 - (x_2 + y_2) \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(8f)	B I
\mathbf{B}_6	$= (x_2 + y_2) \mathbf{a}_1 + (x_2 - y_2) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	B I
\mathbf{B}_7	$= (x_3 - y_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Pd II
\mathbf{B}_8	$= -(x_3 + y_3) \mathbf{a}_1 - (x_3 - y_3) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Pd II
\mathbf{B}_9	$= -(x_3 - y_3) \mathbf{a}_1 - (x_3 + y_3) \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Pd II
\mathbf{B}_{10}	$= (x_3 + y_3) \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Pd II
\mathbf{B}_{11}	$= (x_4 - y_4) \mathbf{a}_1 + (x_4 + y_4) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	Pd III
\mathbf{B}_{12}	$= -(x_4 + y_4) \mathbf{a}_1 - (x_4 - y_4) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Pd III
\mathbf{B}_{13}	$= -(x_4 - y_4) \mathbf{a}_1 - (x_4 + y_4) \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	Pd III
\mathbf{B}_{14}	$= (x_4 + y_4) \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Pd III

References

- [1] E. Stenberg, *The Crystal Structures of Pd₅B₂, (Mn₅C₂), and Pd₃B*, Acta Chem. Scand. **15**, 861–870 (1961), doi:10.3891/acta.chem.scand.15-0861.