





In₂Te₅ (I) Structure: A2B5_mC28_9_2a_5a-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/FD0C>

https://aflow.org/p/A2B5_mC28_9_2a_5a-001

● In
● Te

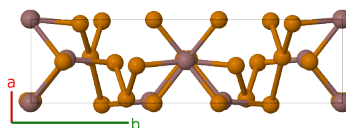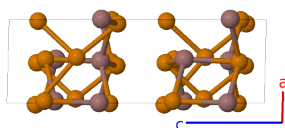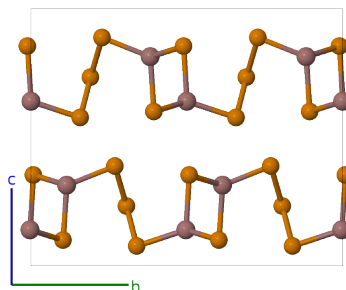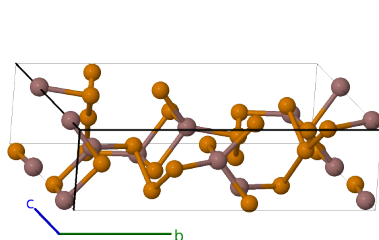


Prototype	In ₂ Te ₅
AFLOW prototype label	A2B5_mC28_9_2a_5a-001
ICSD	501
Pearson symbol	mC28
Space group number	9
Space group symbol	<i>Cc</i>
AFLOW prototype command	<code>aflow --proto=A2B5_mC28_9_2a_5a-001</code> <code>--params=a, b/a, c/a, β, $x_1, y_1, z_1, x_2, y_2, z_2, x_3, y_3, z_3, x_4, y_4, z_4, x_5, y_5, z_5, x_6, y_6, z_6, x_7, y_7, z_7$</code>

- (Sutherland, 1976) found this structure, which we call In₂Te₅ (I), but later also found evidence of another tetragonal structure in the same sample. (Walton, 1978) investigated this new structure, which they called In₂Te₅ (II). (Villars, 2018) and others list In₂Te₅ (I) as the room temperature structure.

Base-centered Monoclinic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}\end{aligned}$$

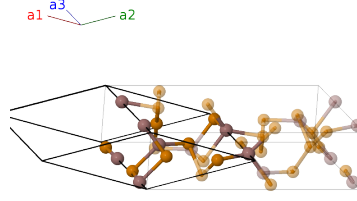

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$(x_1 - y_1) \mathbf{a}_1 + (x_1 + y_1) \mathbf{a}_2 + z_1 \mathbf{a}_3$	=	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(4a)	In I
\mathbf{B}_2	$(x_1 + y_1) \mathbf{a}_1 + (x_1 - y_1) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	In I
\mathbf{B}_3	$(x_2 - y_2) \mathbf{a}_1 + (x_2 + y_2) \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4a)	In II
\mathbf{B}_4	$(x_2 + y_2) \mathbf{a}_1 + (x_2 - y_2) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	In II
\mathbf{B}_5	$(x_3 - y_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4a)	Te I
\mathbf{B}_6	$(x_3 + y_3) \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	Te I
\mathbf{B}_7	$(x_4 - y_4) \mathbf{a}_1 + (x_4 + y_4) \mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4a)	Te II
\mathbf{B}_8	$(x_4 + y_4) \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	Te II
\mathbf{B}_9	$(x_5 - y_5) \mathbf{a}_1 + (x_5 + y_5) \mathbf{a}_2 + z_5 \mathbf{a}_3$	=	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4a)	Te III
\mathbf{B}_{10}	$(x_5 + y_5) \mathbf{a}_1 + (x_5 - y_5) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	Te III
\mathbf{B}_{11}	$(x_6 - y_6) \mathbf{a}_1 + (x_6 + y_6) \mathbf{a}_2 + z_6 \mathbf{a}_3$	=	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(4a)	Te IV
\mathbf{B}_{12}	$(x_6 + y_6) \mathbf{a}_1 + (x_6 - y_6) \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_6 + c(z_6 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	Te IV
\mathbf{B}_{13}	$(x_7 - y_7) \mathbf{a}_1 + (x_7 + y_7) \mathbf{a}_2 + z_7 \mathbf{a}_3$	=	$(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \sin \beta \hat{\mathbf{z}}$	(4a)	Te V
\mathbf{B}_{14}	$(x_7 + y_7) \mathbf{a}_1 + (x_7 - y_7) \mathbf{a}_2 + (z_7 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_7 + c(z_7 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	Te V

References

- [1] H. H. Sutherland, J. H. C. Hogg, and P. D. Walton, *Indium Polytelluride In_2Te_5* **32**, 2539–2541 (1976), doi:10.1107/S0567740876008182.

- [2] P. Villars, H. Okamoto, and K. Cenzual, eds., *ASM Alloy Phase Diagram Database* (ASM International, 2018), chap. Indium-Tellurium Binary Phase Diagram (1998 Budanova N.Y.). Copyright ©2006-2018 ASM International.
- [3] P. D. Walton, H. H. Sutherland, and J. H. C. Hogg, *Indium polytelluride In_2Te_5 (II)*, Acta Crystallogr. Sect. B **34**, 41–45 (1978), doi:10.1107/S0567740878002277.

Found in

- [1] H. J. Deiseroth, P. Amann, and H. Thurn, *Die Pentatelluride M_2Te_5 ($M = Al, Ga, In$): Polymorphie, Strukturbeziehungen und Homogenitätsbereiche*, Z. Anorganische und Allgemeine Chemie **622**, 985–993 (1996), doi:10.1002/zaac.19966220611.