


Li₂ZrTeO₆ Structure: A2B6CD_hR10_146_2a_2b_a_a-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://afLOW.org/p/T7PA>

https://afLOW.org/p/A2B6CD_hR10_146_2a_2b_a_a-001

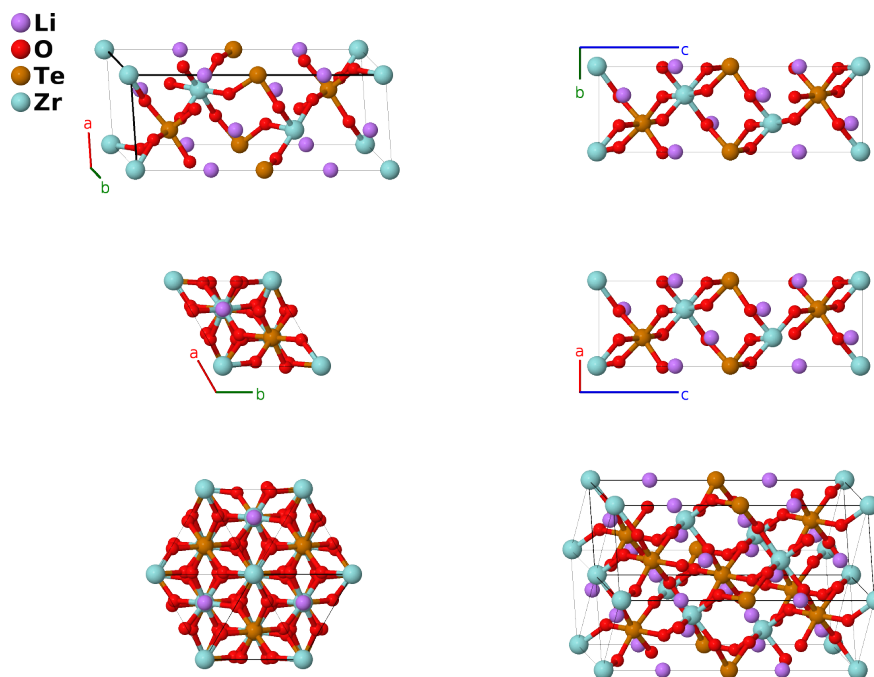

Prototype	Li ₂ O ₆ TeZr
AFLOW prototype label	A2B6CD_hR10_146_2a_2b_a_a-001
ICSD	202648
Pearson symbol	hR10
Space group number	146
Space group symbol	<i>R</i> 3
AFLOW prototype command	<code>afLOW --proto=A2B6CD_hR10_146_2a_2b_a_a-001 --params=a, c/a, x₁, x₂, x₃, x₄, x₅, y₅, z₅, x₆, y₆, z₆</code>


Other compounds with this structure

Li₂HfTeO₆

- This is the quaternary form of the FePSe₃ structure and a distortion of the ferroelectric LiNbO₃ structure (Choisnet, 1988; De Bruin, 1993).
- Hexagonal settings of this structure can be obtained with the option `--hex`.

Rhombohedral primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{\sqrt{3}}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}} \\ \mathbf{a}_3 &= -\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}}\end{aligned}$$

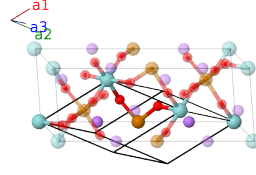

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2 + x_1 \mathbf{a}_3$	$=$	$cx_1 \hat{\mathbf{z}}$	(1a)	Li I
\mathbf{B}_2	$= x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	$=$	$cx_2 \hat{\mathbf{z}}$	(1a)	Li II
\mathbf{B}_3	$= x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$cx_3 \hat{\mathbf{z}}$	(1a)	Te I
\mathbf{B}_4	$= x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$	$=$	$cx_4 \hat{\mathbf{z}}$	(1a)	Zr I
\mathbf{B}_5	$= x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_5 - z_5) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_5 - 2y_5 + z_5) \hat{\mathbf{y}} + \frac{1}{3}c(x_5 + y_5 + z_5) \hat{\mathbf{z}}$	(3b)	O I
\mathbf{B}_6	$= z_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + y_5 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(y_5 - z_5) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(2x_5 - y_5 - z_5) \hat{\mathbf{y}} + \frac{1}{3}c(x_5 + y_5 + z_5) \hat{\mathbf{z}}$	(3b)	O I
\mathbf{B}_7	$= y_5 \mathbf{a}_1 + z_5 \mathbf{a}_2 + x_5 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_5 - y_5) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_5 + y_5 - 2z_5) \hat{\mathbf{y}} + \frac{1}{3}c(x_5 + y_5 + z_5) \hat{\mathbf{z}}$	(3b)	O I
\mathbf{B}_8	$= x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_6 - z_6) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_6 - 2y_6 + z_6) \hat{\mathbf{y}} + \frac{1}{3}c(x_6 + y_6 + z_6) \hat{\mathbf{z}}$	(3b)	O II
\mathbf{B}_9	$= z_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 + y_6 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(y_6 - z_6) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(2x_6 - y_6 - z_6) \hat{\mathbf{y}} + \frac{1}{3}c(x_6 + y_6 + z_6) \hat{\mathbf{z}}$	(3b)	O II
\mathbf{B}_{10}	$= y_6 \mathbf{a}_1 + z_6 \mathbf{a}_2 + x_6 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_6 - y_6) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_6 + y_6 - 2z_6) \hat{\mathbf{y}} + \frac{1}{3}c(x_6 + y_6 + z_6) \hat{\mathbf{z}}$	(3b)	O II

References

- [1] J. Choisnet, A. Rulmont, and P. Tarte, *Les tellurates mixtes $\text{Li}_2\text{ZrTeO}_6$ et $\text{Li}_2\text{HfTeO}_6$: un nouveau phénomène d'ordre dans la famille corindon*, J. Solid State Chem. **75**, 124–135 (1988), doi:10.1016/0022-4596(88)90309-X.

Found in

- [1] T. J. M. D. Bruin, M. Wiegel, G. J. Dirksen, and G. Blasse, *Luminescence of $\text{Li}_2\text{ZrTeO}_6$* , J. Solid State Chem. **107**, 397–400 (1993), doi:10.1006/jssc.1993.1364.