


# $\alpha$ -RbPr[MoO<sub>4</sub>]<sub>2</sub> Structure: A2B8CD\_oP24\_48\_h\_2m\_a\_b-001

This structure originally had the label A2B8CD\_oP24\_48\_k\_2m\_d\_b. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043

<https://aflow.org/p/7YK7>

[https://aflow.org/p/A2B8CD\\_oP24\\_48\\_h\\_2m\\_a\\_b-001](https://aflow.org/p/A2B8CD_oP24_48_h_2m_a_b-001)

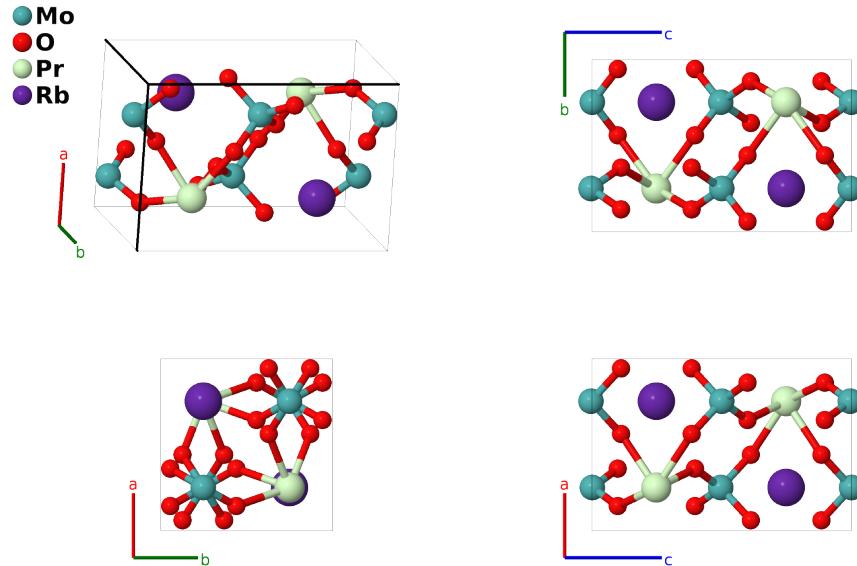


Prototype	Mo <sub>2</sub> O <sub>8</sub> PrRb
AFLOW prototype label	A2B8CD_oP24_48_h_2m_a_b-001
ICSD	6290
Pearson symbol	oP24
Space group number	48
Space group symbol	<i>Pnnn</i>
AFLOW prototype command	<pre>aflow --proto=A2B8CD_oP24_48_h_2m_a_b-001 --params=a,b/a,c/a,x3,x4,y4,z4,x5,y5,z5</pre>

---

## Simple Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{x} \\ \mathbf{a}_2 &= b \hat{y} \\ \mathbf{a}_3 &= c \hat{z}\end{aligned}$$

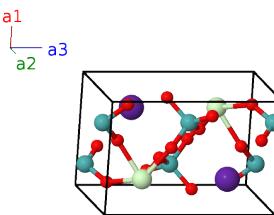

## Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$\frac{1}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + \frac{1}{4}\mathbf{a}_3$	=	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}b\hat{\mathbf{y}} + \frac{1}{4}c\hat{\mathbf{z}}$	(2a)	Pr I
$\mathbf{B}_2$	$\frac{3}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 + \frac{3}{4}\mathbf{a}_3$	=	$\frac{3}{4}a\hat{\mathbf{x}} + \frac{3}{4}b\hat{\mathbf{y}} + \frac{3}{4}c\hat{\mathbf{z}}$	(2a)	Pr I
$\mathbf{B}_3$	$\frac{3}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + \frac{1}{4}\mathbf{a}_3$	=	$\frac{3}{4}a\hat{\mathbf{x}} + \frac{1}{4}b\hat{\mathbf{y}} + \frac{1}{4}c\hat{\mathbf{z}}$	(2b)	Rb I
$\mathbf{B}_4$	$\frac{1}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 + \frac{3}{4}\mathbf{a}_3$	=	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{3}{4}b\hat{\mathbf{y}} + \frac{3}{4}c\hat{\mathbf{z}}$	(2b)	Rb I
$\mathbf{B}_5$	$x_3\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + \frac{3}{4}\mathbf{a}_3$	=	$ax_3\hat{\mathbf{x}} + \frac{1}{4}b\hat{\mathbf{y}} + \frac{3}{4}c\hat{\mathbf{z}}$	(4h)	Mo I
$\mathbf{B}_6$	$-(x_3 - \frac{1}{2})\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + \frac{3}{4}\mathbf{a}_3$	=	$-a(x_3 - \frac{1}{2})\hat{\mathbf{x}} + \frac{1}{4}b\hat{\mathbf{y}} + \frac{3}{4}c\hat{\mathbf{z}}$	(4h)	Mo I
$\mathbf{B}_7$	$-x_3\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 + \frac{1}{4}\mathbf{a}_3$	=	$-ax_3\hat{\mathbf{x}} + \frac{3}{4}b\hat{\mathbf{y}} + \frac{1}{4}c\hat{\mathbf{z}}$	(4h)	Mo I
$\mathbf{B}_8$	$(x_3 + \frac{1}{2})\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 + \frac{1}{4}\mathbf{a}_3$	=	$a(x_3 + \frac{1}{2})\hat{\mathbf{x}} + \frac{3}{4}b\hat{\mathbf{y}} + \frac{1}{4}c\hat{\mathbf{z}}$	(4h)	Mo I
$\mathbf{B}_9$	$x_4\mathbf{a}_1 + y_4\mathbf{a}_2 + z_4\mathbf{a}_3$	=	$ax_4\hat{\mathbf{x}} + by_4\hat{\mathbf{y}} + cz_4\hat{\mathbf{z}}$	(8m)	O I
$\mathbf{B}_{10}$	$-(x_4 - \frac{1}{2})\mathbf{a}_1 - (y_4 - \frac{1}{2})\mathbf{a}_2 + z_4\mathbf{a}_3$	=	$-a(x_4 - \frac{1}{2})\hat{\mathbf{x}} - b(y_4 - \frac{1}{2})\hat{\mathbf{y}} + cz_4\hat{\mathbf{z}}$	(8m)	O I
$\mathbf{B}_{11}$	$-(x_4 - \frac{1}{2})\mathbf{a}_1 + y_4\mathbf{a}_2 - (z_4 - \frac{1}{2})\mathbf{a}_3$	=	$-a(x_4 - \frac{1}{2})\hat{\mathbf{x}} + by_4\hat{\mathbf{y}} - c(z_4 - \frac{1}{2})\hat{\mathbf{z}}$	(8m)	O I
$\mathbf{B}_{12}$	$x_4\mathbf{a}_1 - (y_4 - \frac{1}{2})\mathbf{a}_2 - (z_4 - \frac{1}{2})\mathbf{a}_3$	=	$ax_4\hat{\mathbf{x}} - b(y_4 - \frac{1}{2})\hat{\mathbf{y}} - c(z_4 - \frac{1}{2})\hat{\mathbf{z}}$	(8m)	O I
$\mathbf{B}_{13}$	$-x_4\mathbf{a}_1 - y_4\mathbf{a}_2 - z_4\mathbf{a}_3$	=	$-ax_4\hat{\mathbf{x}} - by_4\hat{\mathbf{y}} - cz_4\hat{\mathbf{z}}$	(8m)	O I
$\mathbf{B}_{14}$	$(x_4 + \frac{1}{2})\mathbf{a}_1 + (y_4 + \frac{1}{2})\mathbf{a}_2 - z_4\mathbf{a}_3$	=	$a(x_4 + \frac{1}{2})\hat{\mathbf{x}} + b(y_4 + \frac{1}{2})\hat{\mathbf{y}} - cz_4\hat{\mathbf{z}}$	(8m)	O I
$\mathbf{B}_{15}$	$(x_4 + \frac{1}{2})\mathbf{a}_1 - y_4\mathbf{a}_2 + (z_4 + \frac{1}{2})\mathbf{a}_3$	=	$a(x_4 + \frac{1}{2})\hat{\mathbf{x}} - by_4\hat{\mathbf{y}} + c(z_4 + \frac{1}{2})\hat{\mathbf{z}}$	(8m)	O I
$\mathbf{B}_{16}$	$-x_4\mathbf{a}_1 + (y_4 + \frac{1}{2})\mathbf{a}_2 + (z_4 + \frac{1}{2})\mathbf{a}_3$	=	$-ax_4\hat{\mathbf{x}} + b(y_4 + \frac{1}{2})\hat{\mathbf{y}} + c(z_4 + \frac{1}{2})\hat{\mathbf{z}}$	(8m)	O I
$\mathbf{B}_{17}$	$x_5\mathbf{a}_1 + y_5\mathbf{a}_2 + z_5\mathbf{a}_3$	=	$ax_5\hat{\mathbf{x}} + by_5\hat{\mathbf{y}} + cz_5\hat{\mathbf{z}}$	(8m)	O II
$\mathbf{B}_{18}$	$-(x_5 - \frac{1}{2})\mathbf{a}_1 - (y_5 - \frac{1}{2})\mathbf{a}_2 + z_5\mathbf{a}_3$	=	$-a(x_5 - \frac{1}{2})\hat{\mathbf{x}} - b(y_5 - \frac{1}{2})\hat{\mathbf{y}} + cz_5\hat{\mathbf{z}}$	(8m)	O II
$\mathbf{B}_{19}$	$-(x_5 - \frac{1}{2})\mathbf{a}_1 + y_5\mathbf{a}_2 - (z_5 - \frac{1}{2})\mathbf{a}_3$	=	$-a(x_5 - \frac{1}{2})\hat{\mathbf{x}} + by_5\hat{\mathbf{y}} - c(z_5 - \frac{1}{2})\hat{\mathbf{z}}$	(8m)	O II
$\mathbf{B}_{20}$	$x_5\mathbf{a}_1 - (y_5 - \frac{1}{2})\mathbf{a}_2 - (z_5 - \frac{1}{2})\mathbf{a}_3$	=	$ax_5\hat{\mathbf{x}} - b(y_5 - \frac{1}{2})\hat{\mathbf{y}} - c(z_5 - \frac{1}{2})\hat{\mathbf{z}}$	(8m)	O II
$\mathbf{B}_{21}$	$-x_5\mathbf{a}_1 - y_5\mathbf{a}_2 - z_5\mathbf{a}_3$	=	$-ax_5\hat{\mathbf{x}} - by_5\hat{\mathbf{y}} - cz_5\hat{\mathbf{z}}$	(8m)	O II
$\mathbf{B}_{22}$	$(x_5 + \frac{1}{2})\mathbf{a}_1 + (y_5 + \frac{1}{2})\mathbf{a}_2 - z_5\mathbf{a}_3$	=	$a(x_5 + \frac{1}{2})\hat{\mathbf{x}} + b(y_5 + \frac{1}{2})\hat{\mathbf{y}} - cz_5\hat{\mathbf{z}}$	(8m)	O II
$\mathbf{B}_{23}$	$(x_5 + \frac{1}{2})\mathbf{a}_1 - y_5\mathbf{a}_2 + (z_5 + \frac{1}{2})\mathbf{a}_3$	=	$a(x_5 + \frac{1}{2})\hat{\mathbf{x}} - by_5\hat{\mathbf{y}} + c(z_5 + \frac{1}{2})\hat{\mathbf{z}}$	(8m)	O II
$\mathbf{B}_{24}$	$-x_5\mathbf{a}_1 + (y_5 + \frac{1}{2})\mathbf{a}_2 + (z_5 + \frac{1}{2})\mathbf{a}_3$	=	$-ax_5\hat{\mathbf{x}} + b(y_5 + \frac{1}{2})\hat{\mathbf{y}} + c(z_5 + \frac{1}{2})\hat{\mathbf{z}}$	(8m)	O II

## References

- [1] R. F. Klevtsova and P. V. Klevtsov, *Polymorphism of rubidium-praseodymium molybdate, RbPr(MoO<sub>4</sub>)<sub>2</sub>*, Kristallografiya **15**, 466–470 (1970).

## Found in

- [1] P. Villars and K. Cenzual, *Pearson's Crystal Data – Crystal Structure Database for Inorganic Compounds* (2013). ASM International.