

Ag₂CrO₄ Structure:


A2BC4_oP28_62_ac_c_2cd-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/VQRL>

https://aflow.org/prototype-encyclopedia/A2BC4_oP28_62_ac_c_2cd-001

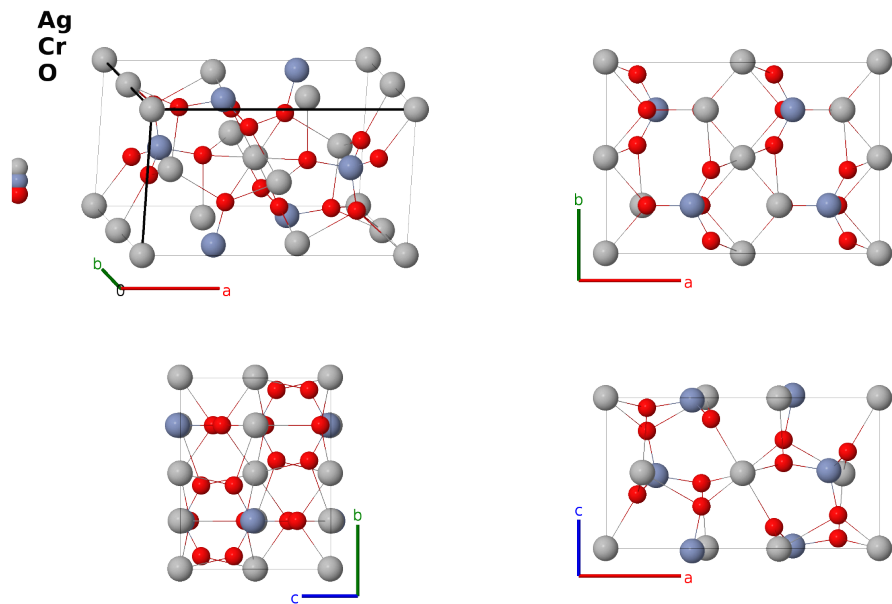

Prototype	Ag ₂ CrO ₄
AFLOW prototype label	A2BC4_oP28_62_ac_c_2cd-001
ICSD	16298
CCDC	1596897
Pearson symbol	oP28
Space group number	62
Space group symbol	<i>Pnma</i>
AFLOW prototype command	<pre>aflow --proto=A2BC4_oP28_62_ac_c_2cd-001 --params=a, b/a, c/a, x₂, z₂, x₃, z₃, x₄, z₄, x₅, z₅, x₆, y₆, z₆</pre>

Other compounds with this structure


Ag₂MnO₄

- (Santamaría-Pérez, 2013) find that above 4.5GPa there is a presumably second-order phase transition where the a axis contracts by about 4%.

- Above 13GPa they find a transition to an unknown structure.
- AgMnVO_4 , where manganese replaces silver on the (4a) site, is the quaternary form of this structure.

Simple Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

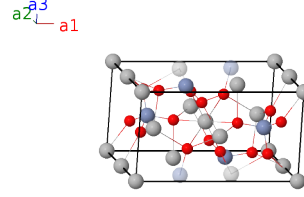

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	Ag I
$\mathbf{B}_2$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} c \hat{\mathbf{z}}$	Ag I
$\mathbf{B}_3$	$=$	$\frac{1}{2} \mathbf{a}_2$	$=$	$\frac{1}{2} b \hat{\mathbf{y}}$	Ag I
$\mathbf{B}_4$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} b \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	Ag I
$\mathbf{B}_5$	$=$	$x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{1}{4} b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	Ag II
$\mathbf{B}_6$	$=$	$-(x_2 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4} b \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	Ag II
$\mathbf{B}_7$	$=$	$-x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + \frac{3}{4} b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	Ag II
$\mathbf{B}_8$	$=$	$(x_2 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4} b \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	Ag II
$\mathbf{B}_9$	$=$	$x_3 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + \frac{1}{4} b \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	Cr I
$\mathbf{B}_{10}$	$=$	$-(x_3 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4} b \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	Cr I
$\mathbf{B}_{11}$	$=$	$-x_3 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{3}{4} b \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	Cr I
$\mathbf{B}_{12}$	$=$	$(x_3 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4} b \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	Cr I
$\mathbf{B}_{13}$	$=$	$x_4 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + \frac{1}{4} b \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	O I
$\mathbf{B}_{14}$	$=$	$-(x_4 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_4 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4} b \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	O I
$\mathbf{B}_{15}$	$=$	$-x_4 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + \frac{3}{4} b \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	O I
$\mathbf{B}_{16}$	$=$	$(x_4 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_4 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4} b \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \hat{\mathbf{z}}$	O I
$\mathbf{B}_{17}$	$=$	$x_5 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + \frac{1}{4} b \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	O II
$\mathbf{B}_{18}$	$=$	$-(x_5 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_5 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4} b \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	O II
$\mathbf{B}_{19}$	$=$	$-x_5 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} + \frac{3}{4} b \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$	O II
$\mathbf{B}_{20}$	$=$	$(x_5 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_5 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4} b \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \hat{\mathbf{z}}$	O II
$\mathbf{B}_{21}$	$=$	$x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$ax_6 \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}}$	O III
$\mathbf{B}_{22}$	$=$	$-(x_6 - \frac{1}{2}) \mathbf{a}_1 - y_6 \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_6 - \frac{1}{2}) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \hat{\mathbf{z}}$	O III
$\mathbf{B}_{23}$	$=$	$-x_6 \mathbf{a}_1 + (y_6 + \frac{1}{2}) \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-ax_6 \hat{\mathbf{x}} + b(y_6 + \frac{1}{2}) \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}}$	O III

$$\begin{aligned}
\mathbf{B}_{24} &= \begin{pmatrix} (x_6 + \frac{1}{2}) \mathbf{a}_1 - (y_6 - \frac{1}{2}) \mathbf{a}_2 - \\ (z_6 - \frac{1}{2}) \mathbf{a}_3 \end{pmatrix} = a \left(x_6 + \frac{1}{2}\right) \hat{\mathbf{x}} - b \left(y_6 - \frac{1}{2}\right) \hat{\mathbf{y}} - c \left(z_6 - \frac{1}{2}\right) \hat{\mathbf{z}} & (8d) & \text{O III} \\
\mathbf{B}_{25} &= -x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 - z_6 \mathbf{a}_3 = -ax_6 \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}} & (8d) & \text{O III} \\
\mathbf{B}_{26} &= \begin{pmatrix} (x_6 + \frac{1}{2}) \mathbf{a}_1 + y_6 \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3 \end{pmatrix} = a \left(x_6 + \frac{1}{2}\right) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} - c \left(z_6 - \frac{1}{2}\right) \hat{\mathbf{z}} & (8d) & \text{O III} \\
\mathbf{B}_{27} &= x_6 \mathbf{a}_1 - \left(y_6 - \frac{1}{2}\right) \mathbf{a}_2 + z_6 \mathbf{a}_3 = ax_6 \hat{\mathbf{x}} - b \left(y_6 - \frac{1}{2}\right) \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}} & (8d) & \text{O III} \\
\mathbf{B}_{28} &= \begin{pmatrix} -\left(x_6 - \frac{1}{2}\right) \mathbf{a}_1 + \left(y_6 + \frac{1}{2}\right) \mathbf{a}_2 + \\ \left(z_6 + \frac{1}{2}\right) \mathbf{a}_3 \end{pmatrix} = -a \left(x_6 - \frac{1}{2}\right) \hat{\mathbf{x}} + b \left(y_6 + \frac{1}{2}\right) \hat{\mathbf{y}} + c \left(z_6 + \frac{1}{2}\right) \hat{\mathbf{z}} & (8d) & \text{O III}
\end{aligned}$$

References

- [1] M. L. Hackert and R. A. Jacobson, *The crystal structure of silver chromate*, J. Solid State Chem. **3**, 364–368 (1971), doi:10.1016/0022-4596(71)90072-7.

Found in

- [1] D. Santamaría-Pérez, E. Bandiello, D. Errandonea, J. Ruiz-Fuertes, O. Gomis, J. A. Sans, F. J. Manjón, P. Rodríguez-Hernández, and A. M. noz, *Phase Behavior of Ag_2CrO_4 under Compression: Structural, Vibrational, and Optical Properties*, J. Phys. Chem. C **117**, 12239–12248 (2013), doi:10.1021/jp401524s.

First cited in

N. Anderson, M. J. Mehl, H. Eckert, S. Divilov, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 5*. Submitted to Computational Materials Science (2026).