


$C53$ (SrBr_2) Structure (*Obsolete*): A2B_oP12_62_2c_c-010

This structure originally had the label A2B_oP12_62_2c_c.SrBr2. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/p/NJ0X>

https://aflow.org/p/A2B_oP12_62_2c_c-010

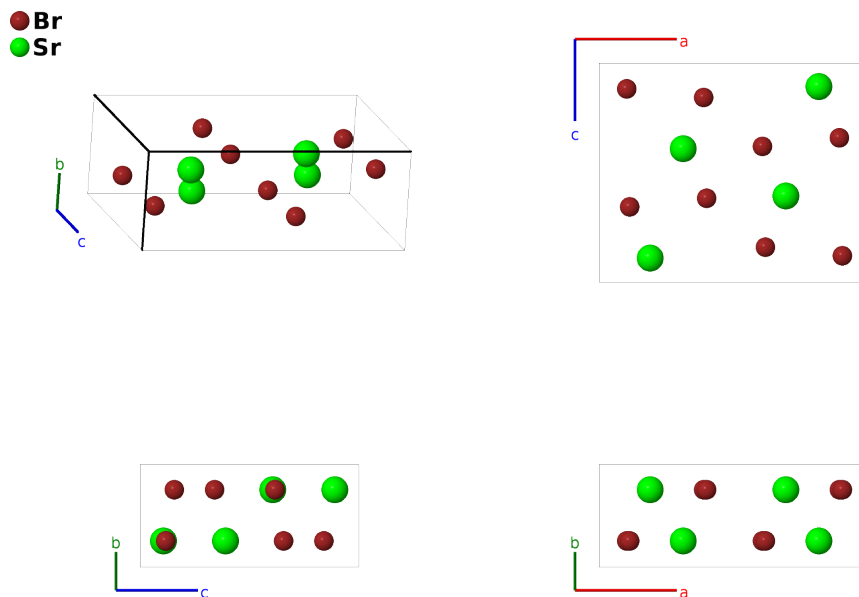


Prototype	Br_2Sr
AFLOW prototype label	A2B_oP12_62_2c_c-010
<i>Strukturbericht</i> designation	$C53$
ICSD	15972
Pearson symbol	oP12
Space group number	62
Space group symbol	$Pnma$
AFLOW prototype command	<code>aflow --proto=A2B_oP12_62_2c_c-010 --params=a, b/a, c/a, x1, z1, x2, z2, x3, z3</code>

- (Kamermans, 1939) determined that SrBr_2 had a distorted PbCl_2 structure and assigned it to space group $Pnma$ #62. (Hermann, 1939) gave this the *Strukturbericht* designation $C53$.
- Some years later (Sass, 1963) showed that this structure was incorrect, and that $\alpha\text{-SrBr}_2$ was actually in space group $P4/n$ #85, rendering the $C53$ symbol obsolete. We include it here for historical interest.

- (Kamermans, 1939) gave the atomic positions in terms of the $Pbnm$ setting of space group #62. We have used FINDSYM to translate this to the standard $Pnma$ setting.
- PbCl_2 ($C23$), HgCl_2 ($C25$), SrH_2 ($C29$), Co_2Si ($C37$), and SrBr_2 ($C53$) all share the same AFLOW label, A2B_oP12_62_2c.c. The structures are generated by the same symmetry operations with different sets of parameters (--params) specified in their corresponding CIF files.

Simple Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

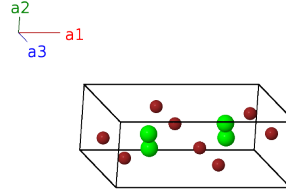

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4c)	Br I
\mathbf{B}_2	$= -(x_1 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_1 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Br I
\mathbf{B}_3	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	(4c)	Br I
\mathbf{B}_4	$= (x_1 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_1 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Br I
\mathbf{B}_5	$= x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4c)	Br II
\mathbf{B}_6	$= -(x_2 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Br II
\mathbf{B}_7	$= -x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4c)	Br II
\mathbf{B}_8	$= (x_2 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Br II
\mathbf{B}_9	$= x_3 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(4c)	Sr I
\mathbf{B}_{10}	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Sr I
\mathbf{B}_{11}	$= -x_3 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(4c)	Sr I
\mathbf{B}_{12}	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Sr I

References

- [1] M. A. Kamermans, *The Crystal Structure of SrBr₂*, *Z. Kristallogr.* **101**, 406–411 (1939), doi:10.1524/zkri.1939.101.1.406.
- [2] R. L. Sass, T. Brackett, and E. Brackett, *The Crystal Structure Of Strontium Bromide*, *J. Phys. Chem.* **67**, 2862–2863 (1963), doi:10.1021/j100806a516.

Found in

- [1] K. Herrmann, ed., *Strukturbericht Band VII 1939* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1943).