


Cu₂Sb (C38) Structure: A2B_tP6_129_ac_c-001

This structure originally had the label A2B_tP6_129_ac_c. Calls to that address will be redirected here.

Cite this page as: M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017

<https://aflow.org/p/YG4M>

https://aflow.org/p/A2B_tP6_129_ac_c-001

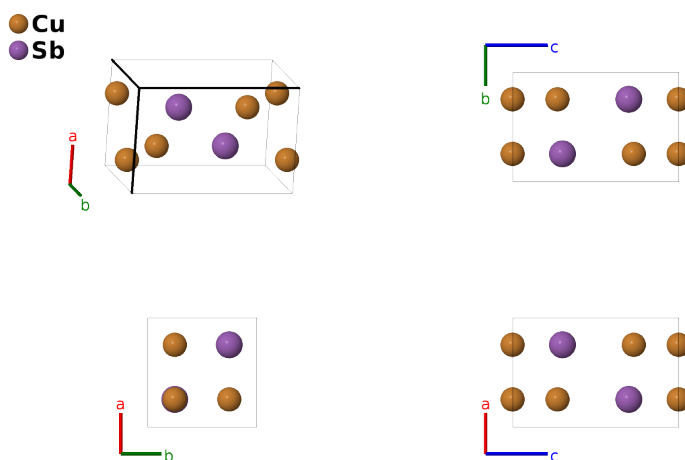


Prototype	Cu ₂ Sb
AFLOW prototype label	A2B_tP6_129_ac_c-001
<i>Strukturbericht</i> designation	C38
ICSD	42323
Pearson symbol	tP6
Space group number	129
Space group symbol	<i>P4/nmm</i>
AFLOW prototype command	aflow --proto=A2B_tP6_129_ac_c-001 --params=a, c/a, z ₂ , z ₃

Other compounds with this structure

As₂Th, As₂U, Bi₂Th, Bi₂U, Cr₂As, Cu₂As, Mn₂As, Mn₂Sb, O₂Gd, Pu₂U, Sb₂Hf, Sb₂Th, Sb₂U, Se₂Ce, Se₂Ho, Te₂Ce, Te₂La, Te₂U, S₂Yb, AlGeMn, AlFeAs, AsCuMg, AsKMn, GeNbSb, KMgP, SnTeU

Simple Tetragonal primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= a \hat{x} \\ \mathbf{a}_2 &= a \hat{y} \\ \mathbf{a}_3 &= c \hat{z} \end{aligned}$$

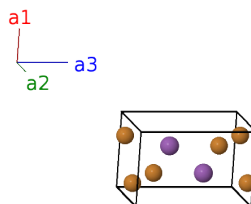

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$=$	$\frac{3}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2$	$=$	$\frac{3}{4}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}}$	(2a) Cu I
\mathbf{B}_2	$=$	$\frac{1}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{3}{4}a\hat{\mathbf{y}}$	(2a) Cu I
\mathbf{B}_3	$=$	$\frac{1}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + z_2\mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}} + cz_2\hat{\mathbf{z}}$	(2c) Cu II
\mathbf{B}_4	$=$	$\frac{3}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 - z_2\mathbf{a}_3$	$=$	$\frac{3}{4}a\hat{\mathbf{x}} + \frac{3}{4}a\hat{\mathbf{y}} - cz_2\hat{\mathbf{z}}$	(2c) Cu II
\mathbf{B}_5	$=$	$\frac{1}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + z_3\mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}} + cz_3\hat{\mathbf{z}}$	(2c) Sb I
\mathbf{B}_6	$=$	$\frac{3}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 - z_3\mathbf{a}_3$	$=$	$\frac{3}{4}a\hat{\mathbf{x}} + \frac{3}{4}a\hat{\mathbf{y}} - cz_3\hat{\mathbf{z}}$	(2c) Sb I

References

- [1] W. B. Pearson, *The Cu₂Sb and related structures*, Zeitschrift für Kristallographie **171**, 23–39 (1985), doi:10.1524/zkri.1985.171.14.23.