


# Mg<sub>23</sub>Al<sub>30</sub> Structure: A30B23\_hR53\_148\_5f\_a2c3f-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/DB0A>

[https://aflow.org/p/A30B23\\_hR53\\_148\\_5f\\_a2c3f-001](https://aflow.org/p/A30B23_hR53_148_5f_a2c3f-001)

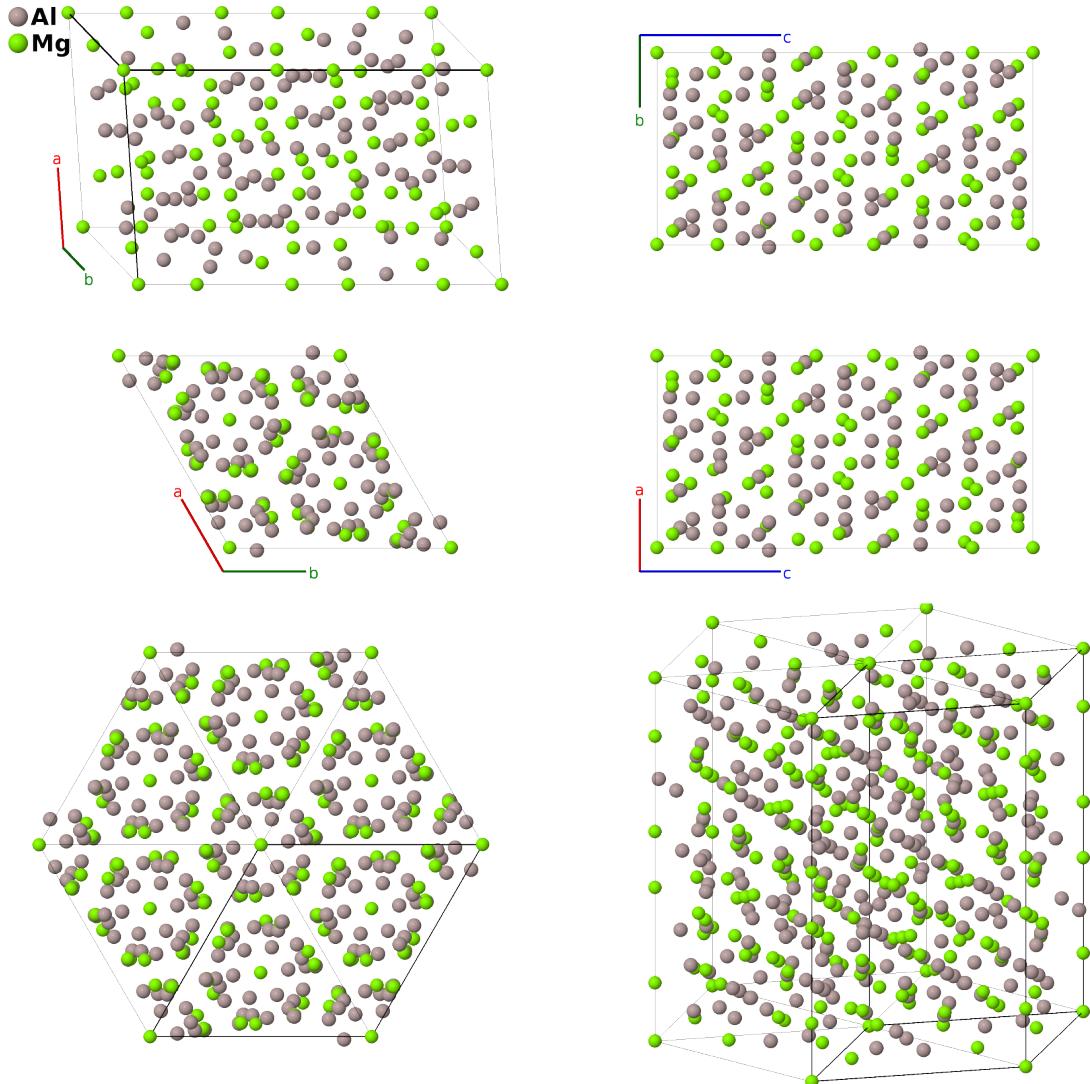

**Prototype** Al<sub>30</sub>Mg<sub>23</sub>

**AFLOW prototype label** A30B23\_hR53\_148\_5f\_a2c3f-001

**ICSD** 57965

**Pearson symbol** hR53

**Space group number** 148

**Space group symbol**  $R\bar{3}$

**AFLOW prototype command**


```
aflow --proto=A30B23_hR53_148_5f_a2c3f-001
--params=a, c/a, x2, x3, x4, y4, z4, x5, y5, z5, x6, y6, z6, x7, y7, z7, x8, y8, z8, x9, y9, z9, x10,
y10, z10, x11, y11, z11
```

---

- (Samson, 1968) finds that the stoichiometry of this system is closer to  $\text{Mg}_{22}\text{Al}_{31}$  than  $\text{Mg}_{23}\text{Al}_{30}$ , so there must be some substitutional disorder in this structure.
- We have shifted the origin so that the first magnesium atom is at (1a) (0 0 0) instead of (1b) (0 0 1/2).
- Hexagonal settings of this structure can be obtained with the option `--hex`.

### Rhombohedral primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + \frac{1}{3}c\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{\sqrt{3}}a\hat{\mathbf{y}} + \frac{1}{3}c\hat{\mathbf{z}} \\ \mathbf{a}_3 &= -\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + \frac{1}{3}c\hat{\mathbf{z}}\end{aligned}$$

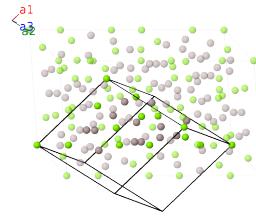

### Basis vectors

	Lattice coordinates	Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	= 0	= 0	(1a)	Mg I
$\mathbf{B}_2$	= $x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	= $cx_2 \hat{\mathbf{z}}$	(2c)	Mg II
$\mathbf{B}_3$	= $-x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 - x_2 \mathbf{a}_3$	= $-cx_2 \hat{\mathbf{z}}$	(2c)	Mg II
$\mathbf{B}_4$	= $x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	= $cx_3 \hat{\mathbf{z}}$	(2c)	Mg III
$\mathbf{B}_5$	= $-x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - x_3 \mathbf{a}_3$	= $-cx_3 \hat{\mathbf{z}}$	(2c)	Mg III
$\mathbf{B}_6$	= $x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	= $\frac{1}{2}a(x_4 - z_4)\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_4 - 2y_4 + z_4)\hat{\mathbf{y}} + \frac{1}{3}c(x_4 + y_4 + z_4)\hat{\mathbf{z}}$	(6f)	Al I
$\mathbf{B}_7$	= $z_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + y_4 \mathbf{a}_3$	= $-\frac{1}{2}a(y_4 - z_4)\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(2x_4 - y_4 - z_4)\hat{\mathbf{y}} + \frac{1}{3}c(x_4 + y_4 + z_4)\hat{\mathbf{z}}$	(6f)	Al I
$\mathbf{B}_8$	= $y_4 \mathbf{a}_1 + z_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$	= $-\frac{1}{2}a(x_4 - y_4)\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_4 + y_4 - 2z_4)\hat{\mathbf{y}} + \frac{1}{3}c(x_4 + y_4 + z_4)\hat{\mathbf{z}}$	(6f)	Al I
$\mathbf{B}_9$	= $-x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	= $-\frac{1}{2}a(x_4 - z_4)\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_4 - 2y_4 + z_4)\hat{\mathbf{y}} - \frac{1}{3}c(x_4 + y_4 + z_4)\hat{\mathbf{z}}$	(6f)	Al I
$\mathbf{B}_{10}$	= $-z_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - y_4 \mathbf{a}_3$	= $\frac{1}{2}a(y_4 - z_4)\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(2x_4 - y_4 - z_4)\hat{\mathbf{y}} - \frac{1}{3}c(x_4 + y_4 + z_4)\hat{\mathbf{z}}$	(6f)	Al I
$\mathbf{B}_{11}$	= $-y_4 \mathbf{a}_1 - z_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$	= $\frac{1}{2}a(x_4 - y_4)\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_4 + y_4 - 2z_4)\hat{\mathbf{y}} - \frac{1}{3}c(x_4 + y_4 + z_4)\hat{\mathbf{z}}$	(6f)	Al I
$\mathbf{B}_{12}$	= $x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	= $\frac{1}{2}a(x_5 - z_5)\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_5 - 2y_5 + z_5)\hat{\mathbf{y}} + \frac{1}{3}c(x_5 + y_5 + z_5)\hat{\mathbf{z}}$	(6f)	Al II
$\mathbf{B}_{13}$	= $z_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + y_5 \mathbf{a}_3$	= $-\frac{1}{2}a(y_5 - z_5)\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(2x_5 - y_5 - z_5)\hat{\mathbf{y}} + \frac{1}{3}c(x_5 + y_5 + z_5)\hat{\mathbf{z}}$	(6f)	Al II
$\mathbf{B}_{14}$	= $y_5 \mathbf{a}_1 + z_5 \mathbf{a}_2 + x_5 \mathbf{a}_3$	= $-\frac{1}{2}a(x_5 - y_5)\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_5 + y_5 - 2z_5)\hat{\mathbf{y}} + \frac{1}{3}c(x_5 + y_5 + z_5)\hat{\mathbf{z}}$	(6f)	Al II
$\mathbf{B}_{15}$	= $-x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	= $-\frac{1}{2}a(x_5 - z_5)\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_5 - 2y_5 + z_5)\hat{\mathbf{y}} - \frac{1}{3}c(x_5 + y_5 + z_5)\hat{\mathbf{z}}$	(6f)	Al II

$\mathbf{B}_{16}$	$=$	$-z_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - y_5 \mathbf{a}_3$	$=$	$\frac{1}{2}a(y_5 - z_5) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(2x_5 - y_5 - z_5) \hat{\mathbf{y}} - \frac{1}{3}c(x_5 + y_5 + z_5) \hat{\mathbf{z}}$	(6f)	Al II
$\mathbf{B}_{17}$	$=$	$-y_5 \mathbf{a}_1 - z_5 \mathbf{a}_2 - x_5 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_5 - y_5) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_5 + y_5 - 2z_5) \hat{\mathbf{y}} - \frac{1}{3}c(x_5 + y_5 + z_5) \hat{\mathbf{z}}$	(6f)	Al II
$\mathbf{B}_{18}$	$=$	$x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_6 - z_6) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_6 - 2y_6 + z_6) \hat{\mathbf{y}} + \frac{1}{3}c(x_6 + y_6 + z_6) \hat{\mathbf{z}}$	(6f)	Al III
$\mathbf{B}_{19}$	$=$	$z_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 + y_6 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(y_6 - z_6) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(2x_6 - y_6 - z_6) \hat{\mathbf{y}} + \frac{1}{3}c(x_6 + y_6 + z_6) \hat{\mathbf{z}}$	(6f)	Al III
$\mathbf{B}_{20}$	$=$	$y_6 \mathbf{a}_1 + z_6 \mathbf{a}_2 + x_6 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_6 - y_6) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_6 + y_6 - 2z_6) \hat{\mathbf{y}} + \frac{1}{3}c(x_6 + y_6 + z_6) \hat{\mathbf{z}}$	(6f)	Al III
$\mathbf{B}_{21}$	$=$	$-x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_6 - z_6) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_6 - 2y_6 + z_6) \hat{\mathbf{y}} - \frac{1}{3}c(x_6 + y_6 + z_6) \hat{\mathbf{z}}$	(6f)	Al III
$\mathbf{B}_{22}$	$=$	$-z_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 - y_6 \mathbf{a}_3$	$=$	$\frac{1}{2}a(y_6 - z_6) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(2x_6 - y_6 - z_6) \hat{\mathbf{y}} - \frac{1}{3}c(x_6 + y_6 + z_6) \hat{\mathbf{z}}$	(6f)	Al III
$\mathbf{B}_{23}$	$=$	$-y_6 \mathbf{a}_1 - z_6 \mathbf{a}_2 - x_6 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_6 - y_6) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_6 + y_6 - 2z_6) \hat{\mathbf{y}} - \frac{1}{3}c(x_6 + y_6 + z_6) \hat{\mathbf{z}}$	(6f)	Al III
$\mathbf{B}_{24}$	$=$	$x_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_7 - z_7) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_7 - 2y_7 + z_7) \hat{\mathbf{y}} + \frac{1}{3}c(x_7 + y_7 + z_7) \hat{\mathbf{z}}$	(6f)	Al IV
$\mathbf{B}_{25}$	$=$	$z_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 + y_7 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(y_7 - z_7) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(2x_7 - y_7 - z_7) \hat{\mathbf{y}} + \frac{1}{3}c(x_7 + y_7 + z_7) \hat{\mathbf{z}}$	(6f)	Al IV
$\mathbf{B}_{26}$	$=$	$y_7 \mathbf{a}_1 + z_7 \mathbf{a}_2 + x_7 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_7 - y_7) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_7 + y_7 - 2z_7) \hat{\mathbf{y}} + \frac{1}{3}c(x_7 + y_7 + z_7) \hat{\mathbf{z}}$	(6f)	Al IV
$\mathbf{B}_{27}$	$=$	$-x_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_7 - z_7) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_7 - 2y_7 + z_7) \hat{\mathbf{y}} - \frac{1}{3}c(x_7 + y_7 + z_7) \hat{\mathbf{z}}$	(6f)	Al IV
$\mathbf{B}_{28}$	$=$	$-z_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - y_7 \mathbf{a}_3$	$=$	$\frac{1}{2}a(y_7 - z_7) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(2x_7 - y_7 - z_7) \hat{\mathbf{y}} - \frac{1}{3}c(x_7 + y_7 + z_7) \hat{\mathbf{z}}$	(6f)	Al IV
$\mathbf{B}_{29}$	$=$	$-y_7 \mathbf{a}_1 - z_7 \mathbf{a}_2 - x_7 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_7 - y_7) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_7 + y_7 - 2z_7) \hat{\mathbf{y}} - \frac{1}{3}c(x_7 + y_7 + z_7) \hat{\mathbf{z}}$	(6f)	Al IV
$\mathbf{B}_{30}$	$=$	$x_8 \mathbf{a}_1 + y_8 \mathbf{a}_2 + z_8 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_8 - z_8) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_8 - 2y_8 + z_8) \hat{\mathbf{y}} + \frac{1}{3}c(x_8 + y_8 + z_8) \hat{\mathbf{z}}$	(6f)	Al V
$\mathbf{B}_{31}$	$=$	$z_8 \mathbf{a}_1 + x_8 \mathbf{a}_2 + y_8 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(y_8 - z_8) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(2x_8 - y_8 - z_8) \hat{\mathbf{y}} + \frac{1}{3}c(x_8 + y_8 + z_8) \hat{\mathbf{z}}$	(6f)	Al V
$\mathbf{B}_{32}$	$=$	$y_8 \mathbf{a}_1 + z_8 \mathbf{a}_2 + x_8 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_8 - y_8) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_8 + y_8 - 2z_8) \hat{\mathbf{y}} + \frac{1}{3}c(x_8 + y_8 + z_8) \hat{\mathbf{z}}$	(6f)	Al V
$\mathbf{B}_{33}$	$=$	$-x_8 \mathbf{a}_1 - y_8 \mathbf{a}_2 - z_8 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_8 - z_8) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_8 - 2y_8 + z_8) \hat{\mathbf{y}} - \frac{1}{3}c(x_8 + y_8 + z_8) \hat{\mathbf{z}}$	(6f)	Al V
$\mathbf{B}_{34}$	$=$	$-z_8 \mathbf{a}_1 - x_8 \mathbf{a}_2 - y_8 \mathbf{a}_3$	$=$	$\frac{1}{2}a(y_8 - z_8) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(2x_8 - y_8 - z_8) \hat{\mathbf{y}} - \frac{1}{3}c(x_8 + y_8 + z_8) \hat{\mathbf{z}}$	(6f)	Al V
$\mathbf{B}_{35}$	$=$	$-y_8 \mathbf{a}_1 - z_8 \mathbf{a}_2 - x_8 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_8 - y_8) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_8 + y_8 - 2z_8) \hat{\mathbf{y}} - \frac{1}{3}c(x_8 + y_8 + z_8) \hat{\mathbf{z}}$	(6f)	Al V
$\mathbf{B}_{36}$	$=$	$x_9 \mathbf{a}_1 + y_9 \mathbf{a}_2 + z_9 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_9 - z_9) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_9 - 2y_9 + z_9) \hat{\mathbf{y}} + \frac{1}{3}c(x_9 + y_9 + z_9) \hat{\mathbf{z}}$	(6f)	Mg IV
$\mathbf{B}_{37}$	$=$	$z_9 \mathbf{a}_1 + x_9 \mathbf{a}_2 + y_9 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(y_9 - z_9) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(2x_9 - y_9 - z_9) \hat{\mathbf{y}} + \frac{1}{3}c(x_9 + y_9 + z_9) \hat{\mathbf{z}}$	(6f)	Mg IV
$\mathbf{B}_{38}$	$=$	$y_9 \mathbf{a}_1 + z_9 \mathbf{a}_2 + x_9 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_9 - y_9) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_9 + y_9 - 2z_9) \hat{\mathbf{y}} + \frac{1}{3}c(x_9 + y_9 + z_9) \hat{\mathbf{z}}$	(6f)	Mg IV
$\mathbf{B}_{39}$	$=$	$-x_9 \mathbf{a}_1 - y_9 \mathbf{a}_2 - z_9 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_9 - z_9) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_9 - 2y_9 + z_9) \hat{\mathbf{y}} - \frac{1}{3}c(x_9 + y_9 + z_9) \hat{\mathbf{z}}$	(6f)	Mg IV

$\mathbf{B}_{40}$	$=$	$-z_9 \mathbf{a}_1 - x_9 \mathbf{a}_2 - y_9 \mathbf{a}_3$	$=$	$\frac{1}{2}a(y_9 - z_9) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(2x_9 - y_9 - z_9) \hat{\mathbf{y}} - \frac{1}{3}c(x_9 + y_9 + z_9) \hat{\mathbf{z}}$	(6f)	Mg IV
$\mathbf{B}_{41}$	$=$	$-y_9 \mathbf{a}_1 - z_9 \mathbf{a}_2 - x_9 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_9 - y_9) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_9 + y_9 - 2z_9) \hat{\mathbf{y}} - \frac{1}{3}c(x_9 + y_9 + z_9) \hat{\mathbf{z}}$	(6f)	Mg IV
$\mathbf{B}_{42}$	$=$	$x_{10} \mathbf{a}_1 + y_{10} \mathbf{a}_2 + z_{10} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_{10} - z_{10}) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_{10} - 2y_{10} + z_{10}) \hat{\mathbf{y}} + \frac{1}{3}c(x_{10} + y_{10} + z_{10}) \hat{\mathbf{z}}$	(6f)	Mg V
$\mathbf{B}_{43}$	$=$	$z_{10} \mathbf{a}_1 + x_{10} \mathbf{a}_2 + y_{10} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(y_{10} - z_{10}) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(2x_{10} - y_{10} - z_{10}) \hat{\mathbf{y}} + \frac{1}{3}c(x_{10} + y_{10} + z_{10}) \hat{\mathbf{z}}$	(6f)	Mg V
$\mathbf{B}_{44}$	$=$	$y_{10} \mathbf{a}_1 + z_{10} \mathbf{a}_2 + x_{10} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_{10} - y_{10}) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_{10} + y_{10} - 2z_{10}) \hat{\mathbf{y}} + \frac{1}{3}c(x_{10} + y_{10} + z_{10}) \hat{\mathbf{z}}$	(6f)	Mg V
$\mathbf{B}_{45}$	$=$	$-x_{10} \mathbf{a}_1 - y_{10} \mathbf{a}_2 - z_{10} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_{10} - z_{10}) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_{10} - 2y_{10} + z_{10}) \hat{\mathbf{y}} - \frac{1}{3}c(x_{10} + y_{10} + z_{10}) \hat{\mathbf{z}}$	(6f)	Mg V
$\mathbf{B}_{46}$	$=$	$-z_{10} \mathbf{a}_1 - x_{10} \mathbf{a}_2 - y_{10} \mathbf{a}_3$	$=$	$\frac{1}{2}a(y_{10} - z_{10}) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(2x_{10} - y_{10} - z_{10}) \hat{\mathbf{y}} - \frac{1}{3}c(x_{10} + y_{10} + z_{10}) \hat{\mathbf{z}}$	(6f)	Mg V
$\mathbf{B}_{47}$	$=$	$-y_{10} \mathbf{a}_1 - z_{10} \mathbf{a}_2 - x_{10} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_{10} - y_{10}) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_{10} + y_{10} - 2z_{10}) \hat{\mathbf{y}} - \frac{1}{3}c(x_{10} + y_{10} + z_{10}) \hat{\mathbf{z}}$	(6f)	Mg V
$\mathbf{B}_{48}$	$=$	$x_{11} \mathbf{a}_1 + y_{11} \mathbf{a}_2 + z_{11} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_{11} - z_{11}) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_{11} - 2y_{11} + z_{11}) \hat{\mathbf{y}} + \frac{1}{3}c(x_{11} + y_{11} + z_{11}) \hat{\mathbf{z}}$	(6f)	Mg VI
$\mathbf{B}_{49}$	$=$	$z_{11} \mathbf{a}_1 + x_{11} \mathbf{a}_2 + y_{11} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(y_{11} - z_{11}) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(2x_{11} - y_{11} - z_{11}) \hat{\mathbf{y}} + \frac{1}{3}c(x_{11} + y_{11} + z_{11}) \hat{\mathbf{z}}$	(6f)	Mg VI
$\mathbf{B}_{50}$	$=$	$y_{11} \mathbf{a}_1 + z_{11} \mathbf{a}_2 + x_{11} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_{11} - y_{11}) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_{11} + y_{11} - 2z_{11}) \hat{\mathbf{y}} + \frac{1}{3}c(x_{11} + y_{11} + z_{11}) \hat{\mathbf{z}}$	(6f)	Mg VI
$\mathbf{B}_{51}$	$=$	$-x_{11} \mathbf{a}_1 - y_{11} \mathbf{a}_2 - z_{11} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_{11} - z_{11}) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_{11} - 2y_{11} + z_{11}) \hat{\mathbf{y}} - \frac{1}{3}c(x_{11} + y_{11} + z_{11}) \hat{\mathbf{z}}$	(6f)	Mg VI
$\mathbf{B}_{52}$	$=$	$-z_{11} \mathbf{a}_1 - x_{11} \mathbf{a}_2 - y_{11} \mathbf{a}_3$	$=$	$\frac{1}{2}a(y_{11} - z_{11}) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(2x_{11} - y_{11} - z_{11}) \hat{\mathbf{y}} - \frac{1}{3}c(x_{11} + y_{11} + z_{11}) \hat{\mathbf{z}}$	(6f)	Mg VI
$\mathbf{B}_{53}$	$=$	$-y_{11} \mathbf{a}_1 - z_{11} \mathbf{a}_2 - x_{11} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_{11} - y_{11}) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_{11} + y_{11} - 2z_{11}) \hat{\mathbf{y}} - \frac{1}{3}c(x_{11} + y_{11} + z_{11}) \hat{\mathbf{z}}$	(6f)	Mg VI

## References

- [1] S. Samson and E. K. Gordon, *The crystal structure of  $\epsilon$ -Mg<sub>23</sub>Al<sub>30</sub>*, Acta Crystallogr. Sect. B **24**, 1004–1013 (1968), doi:10.1107/S0567740868003638.

## Found in

- [1] P. Villars, H. Okamoto, and K. Cenzual, eds., *ASM Alloy Phase Diagram Database* (ASM International, 2018), chap. Aluminum-Magnesium Binary Phase Diagram (1998 Okamoto H.). Copyright ©2006-2018 ASM International.