


Chiolite ($\text{Na}_5\text{Al}_3\text{F}_{14}$, $K7_5$) Structure: A3B14C5_tP44_128_ac_ehi_bg-001

This structure originally had the label A3B14C5_tP44_128_ac_ehi_bg. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/p/GFQ6>


https://aflow.org/p/A3B14C5_tP44_128_ac_ehi_bg-001

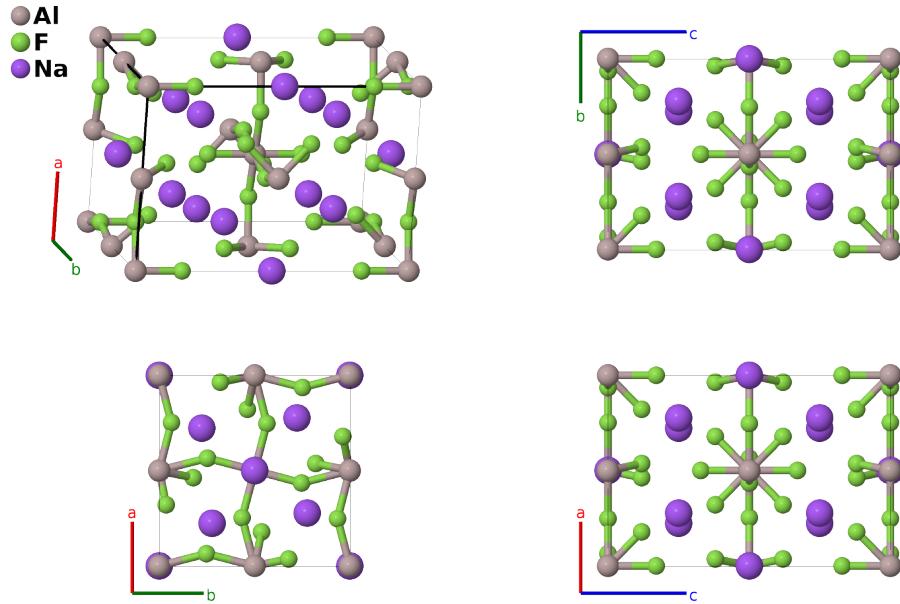

| | |
|------------------------------------|---|
| Prototype | $\text{Al}_3\text{F}_{14}\text{Na}_5$ |
| AFLOW prototype label | A3B14C5_tP44_128_ac_ehi_bg-001 |
| Strukturbericht designation | $K7_5$ |
| Mineral name | chiolite |
| ICSD | 26419 |
| Pearson symbol | tP44 |
| Space group number | 128 |
| Space group symbol | $P4/mnc$ |
| AFLOW prototype command | <code>aflow --proto=A3B14C5_tP44_128_ac_ehi_bg-001 --params=a, c/a, z4, x5, x6, y6, x7, y7, z7</code> |

Simple Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

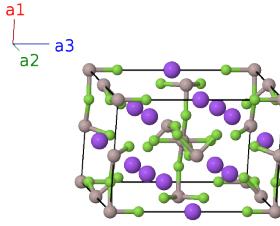

Basis vectors

| | Lattice coordinates | Cartesian coordinates | Wyckoff position | Atom type |
|-------------------|---|--|------------------|-----------|
| \mathbf{B}_1 | = 0 | = 0 | (2a) | Al I |
| \mathbf{B}_2 | = $\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$ | = $\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$ | (2a) | Al I |
| \mathbf{B}_3 | = $\frac{1}{2} \mathbf{a}_3$ | = $\frac{1}{2}c \hat{\mathbf{z}}$ | (2b) | Na I |
| \mathbf{B}_4 | = $\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$ | = $\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}}$ | (2b) | Na I |
| \mathbf{B}_5 | = $\frac{1}{2} \mathbf{a}_2$ | = $\frac{1}{2}a \hat{\mathbf{y}}$ | (4c) | Al II |
| \mathbf{B}_6 | = $\frac{1}{2} \mathbf{a}_1$ | = $\frac{1}{2}a \hat{\mathbf{x}}$ | (4c) | Al II |
| \mathbf{B}_7 | = $\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$ | = $\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$ | (4c) | Al II |
| \mathbf{B}_8 | = $\frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$ | = $\frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$ | (4c) | Al II |
| \mathbf{B}_9 | = $z_4 \mathbf{a}_3$ | = $c z_4 \hat{\mathbf{z}}$ | (4e) | F I |
| \mathbf{B}_{10} | = $\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$ | = $\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \hat{\mathbf{z}}$ | (4e) | F I |
| \mathbf{B}_{11} | = $-z_4 \mathbf{a}_3$ | = $-c z_4 \hat{\mathbf{z}}$ | (4e) | F I |
| \mathbf{B}_{12} | = $\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$ | = $\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$ | (4e) | F I |
| \mathbf{B}_{13} | = $x_5 \mathbf{a}_1 + (x_5 + \frac{1}{2}) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$ | = $a x_5 \hat{\mathbf{x}} + a(x_5 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$ | (8g) | Na II |
| \mathbf{B}_{14} | = $-x_5 \mathbf{a}_1 - (x_5 - \frac{1}{2}) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$ | = $-a x_5 \hat{\mathbf{x}} - a(x_5 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$ | (8g) | Na II |
| \mathbf{B}_{15} | = $-(x_5 - \frac{1}{2}) \mathbf{a}_1 + x_5 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$ | = $-a(x_5 - \frac{1}{2}) \hat{\mathbf{x}} + a x_5 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$ | (8g) | Na II |
| \mathbf{B}_{16} | = $(x_5 + \frac{1}{2}) \mathbf{a}_1 - x_5 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$ | = $a(x_5 + \frac{1}{2}) \hat{\mathbf{x}} - a x_5 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$ | (8g) | Na II |
| \mathbf{B}_{17} | = $-x_5 \mathbf{a}_1 - (x_5 - \frac{1}{2}) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$ | = $-a x_5 \hat{\mathbf{x}} - a(x_5 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$ | (8g) | Na II |
| \mathbf{B}_{18} | = $x_5 \mathbf{a}_1 + (x_5 + \frac{1}{2}) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$ | = $a x_5 \hat{\mathbf{x}} + a(x_5 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$ | (8g) | Na II |
| \mathbf{B}_{19} | = $(x_5 + \frac{1}{2}) \mathbf{a}_1 - x_5 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$ | = $a(x_5 + \frac{1}{2}) \hat{\mathbf{x}} - a x_5 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$ | (8g) | Na II |
| \mathbf{B}_{20} | = $-(x_5 - \frac{1}{2}) \mathbf{a}_1 + x_5 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$ | = $-a(x_5 - \frac{1}{2}) \hat{\mathbf{x}} + a x_5 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$ | (8g) | Na II |
| \mathbf{B}_{21} | = $x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2$ | = $a x_6 \hat{\mathbf{x}} + a y_6 \hat{\mathbf{y}}$ | (8h) | F II |
| \mathbf{B}_{22} | = $-x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2$ | = $-a x_6 \hat{\mathbf{x}} - a y_6 \hat{\mathbf{y}}$ | (8h) | F II |
| \mathbf{B}_{23} | = $-y_6 \mathbf{a}_1 + x_6 \mathbf{a}_2$ | = $-a y_6 \hat{\mathbf{x}} + a x_6 \hat{\mathbf{y}}$ | (8h) | F II |
| \mathbf{B}_{24} | = $y_6 \mathbf{a}_1 - x_6 \mathbf{a}_2$ | = $a y_6 \hat{\mathbf{x}} - a x_6 \hat{\mathbf{y}}$ | (8h) | F II |
| \mathbf{B}_{25} | = $-(x_6 - \frac{1}{2}) \mathbf{a}_1 + (y_6 + \frac{1}{2}) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$ | = $-a(x_6 - \frac{1}{2}) \hat{\mathbf{x}} + a(y_6 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$ | (8h) | F II |
| \mathbf{B}_{26} | = $(x_6 + \frac{1}{2}) \mathbf{a}_1 - (y_6 - \frac{1}{2}) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$ | = $a(x_6 + \frac{1}{2}) \hat{\mathbf{x}} - a(y_6 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$ | (8h) | F II |
| \mathbf{B}_{27} | = $(y_6 + \frac{1}{2}) \mathbf{a}_1 + (x_6 + \frac{1}{2}) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$ | = $a(y_6 + \frac{1}{2}) \hat{\mathbf{x}} + a(x_6 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$ | (8h) | F II |
| \mathbf{B}_{28} | = $-(y_6 - \frac{1}{2}) \mathbf{a}_1 - (x_6 - \frac{1}{2}) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$ | = $-a(y_6 - \frac{1}{2}) \hat{\mathbf{x}} - a(x_6 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$ | (8h) | F II |
| \mathbf{B}_{29} | = $x_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$ | = $a x_7 \hat{\mathbf{x}} + a y_7 \hat{\mathbf{y}} + c z_7 \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{30} | = $-x_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$ | = $-a x_7 \hat{\mathbf{x}} - a y_7 \hat{\mathbf{y}} + c z_7 \hat{\mathbf{z}}$ | (16i) | F III |

| | | | | | | |
|-------------------|-----|---|-----|--|-------|-------|
| \mathbf{B}_{31} | $=$ | $-y_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$ | $=$ | $-ay_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{32} | $=$ | $y_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$ | $=$ | $ay_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{33} | $=$ | $-(x_7 - \frac{1}{2}) \mathbf{a}_1 + (y_7 + \frac{1}{2}) \mathbf{a}_2 - (z_7 - \frac{1}{2}) \mathbf{a}_3$ | $=$ | $-a(x_7 - \frac{1}{2}) \hat{\mathbf{x}} + a(y_7 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{34} | $=$ | $(x_7 + \frac{1}{2}) \mathbf{a}_1 - (y_7 - \frac{1}{2}) \mathbf{a}_2 - (z_7 - \frac{1}{2}) \mathbf{a}_3$ | $=$ | $a(x_7 + \frac{1}{2}) \hat{\mathbf{x}} - a(y_7 - \frac{1}{2}) \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{35} | $=$ | $(y_7 + \frac{1}{2}) \mathbf{a}_1 + (x_7 + \frac{1}{2}) \mathbf{a}_2 - (z_7 - \frac{1}{2}) \mathbf{a}_3$ | $=$ | $a(y_7 + \frac{1}{2}) \hat{\mathbf{x}} + a(x_7 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{36} | $=$ | $-(y_7 - \frac{1}{2}) \mathbf{a}_1 - (x_7 - \frac{1}{2}) \mathbf{a}_2 - (z_7 - \frac{1}{2}) \mathbf{a}_3$ | $=$ | $-a(y_7 - \frac{1}{2}) \hat{\mathbf{x}} - a(x_7 - \frac{1}{2}) \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{37} | $=$ | $-x_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$ | $=$ | $-ax_7 \hat{\mathbf{x}} - ay_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{38} | $=$ | $x_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$ | $=$ | $ax_7 \hat{\mathbf{x}} + ay_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{39} | $=$ | $y_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$ | $=$ | $ay_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{40} | $=$ | $-y_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$ | $=$ | $-ay_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{41} | $=$ | $(x_7 + \frac{1}{2}) \mathbf{a}_1 - (y_7 - \frac{1}{2}) \mathbf{a}_2 + (z_7 + \frac{1}{2}) \mathbf{a}_3$ | $=$ | $a(x_7 + \frac{1}{2}) \hat{\mathbf{x}} - a(y_7 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{42} | $=$ | $-(x_7 - \frac{1}{2}) \mathbf{a}_1 + (y_7 + \frac{1}{2}) \mathbf{a}_2 + (z_7 + \frac{1}{2}) \mathbf{a}_3$ | $=$ | $-a(x_7 - \frac{1}{2}) \hat{\mathbf{x}} + a(y_7 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{43} | $=$ | $-(y_7 - \frac{1}{2}) \mathbf{a}_1 - (x_7 - \frac{1}{2}) \mathbf{a}_2 + (z_7 + \frac{1}{2}) \mathbf{a}_3$ | $=$ | $-a(y_7 - \frac{1}{2}) \hat{\mathbf{x}} - a(x_7 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \hat{\mathbf{z}}$ | (16i) | F III |
| \mathbf{B}_{44} | $=$ | $(y_7 + \frac{1}{2}) \mathbf{a}_1 + (x_7 + \frac{1}{2}) \mathbf{a}_2 + (z_7 + \frac{1}{2}) \mathbf{a}_3$ | $=$ | $a(y_7 + \frac{1}{2}) \hat{\mathbf{x}} + a(x_7 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \hat{\mathbf{z}}$ | (16i) | F III |

References

- [1] C. Jacoboni, A. Leble, and J. J. Rousseau, *Détermination précise de la structure de la chiolite $Na_5Al_3F_{14}$ et étude par R.P.E. de $Na_5Al_3F_{14}:Cr^{3+}$* , J. Solid State Chem. **36**, 297–304 (1981), doi:10.1016/0022-4596(81)90440-0.

Found in

- [1] R. T. Downs and M. Hall-Wallace, *The American Mineralogist Crystal Structure Database*, Am. Mineral. **88**, 247–250 (2003).