


# $S3_4$ (II) (Catapleiite, $\text{Na}_2\text{Zr}(\text{SiO}_3)_3 \cdot \text{H}_2\text{O}$ ) Structure (*Obsolete*): A3B2C9D3E\_hP36\_194\_g\_f\_hk\_h\_a-001

This structure originally had the label A3B2C9D3E\_hP36\_194\_g\_f\_hk\_h\_a. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://afLOW.org/p/6TN8>

[https://afLOW.org/p/A3B2C9D3E\\_hP36\\_194\\_g\\_f\\_hk\\_h\\_a-001](https://afLOW.org/p/A3B2C9D3E_hP36_194_g_f_hk_h_a-001)

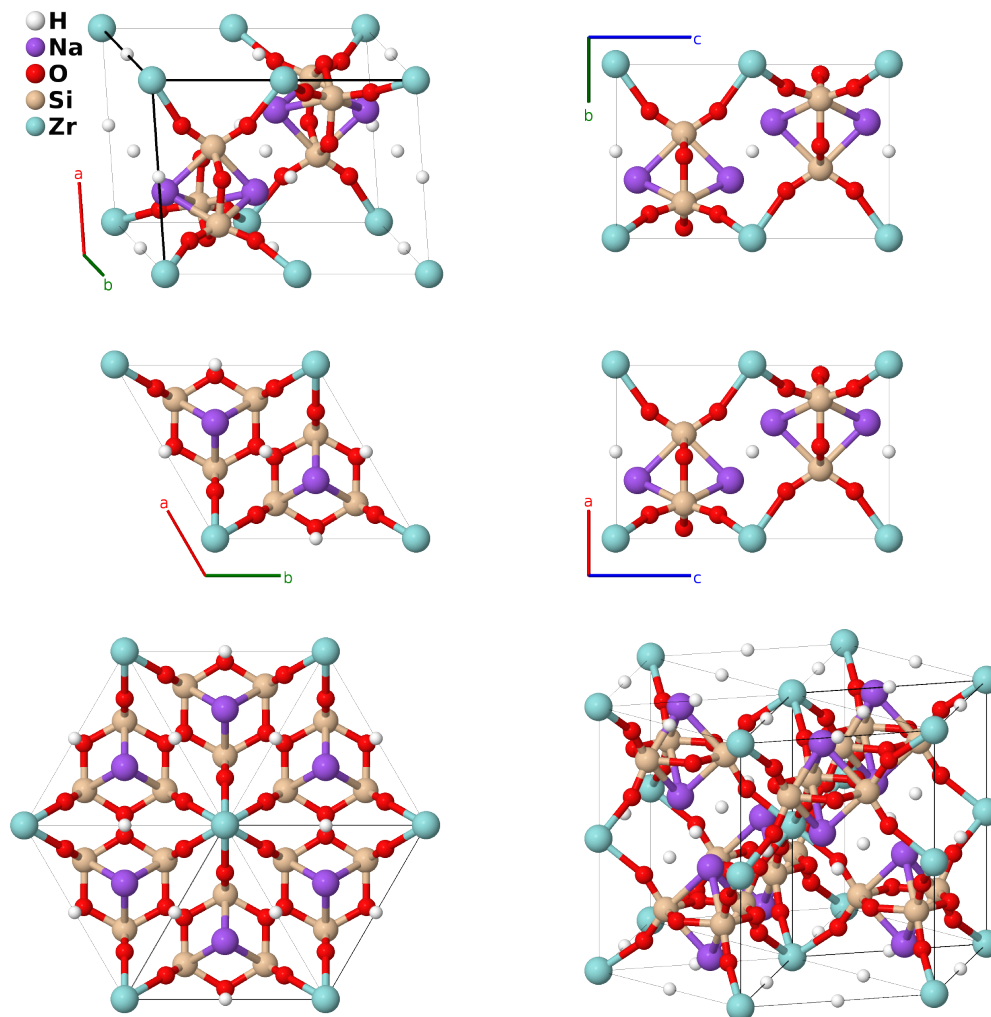


Prototype	$\text{H}_2\text{Na}_2\text{O}_9\text{Si}_2\text{Zr}$
AFLOW prototype label	A3B2C9D3E_hP36_194_g_f_hk_h_a-001
<i>Strukturbericht</i> designation	$S3_4$ (II)
Mineral name	catapleiite
ICSD	none
Pearson symbol	hP36

Space group number 194  
Space group symbol  $P6_3/mmc$   
AFLOW prototype command `aflow --proto=A3B2C9D3E_hP36_194_g_f_hk_h_a-001`  
`--params=a, c/a, z2, x4, x5, x6, z6`

- This hexagonal structure has been superseded by the monoclinic structure of (Ilyushin, 1981). We present it here for historical interest.
- We were unable to procure the original reference, so we use the data provided by (Gottfried, 1937).
- Four of the (6g) sites are randomly occupied by water molecules.
- (Gottfried, 1937) originally gave the *Strukturbericht* designation  $S3_4$  to chabazite, but (Gottfried, 1940) gave it to this structure of catapleite. We distinguish between the two cases by using  $S3_4(\text{I})$  to designate chabazite and  $S3_4(\text{II})$  to designate catapleite.

### Hexagonal primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}} \end{aligned}$$

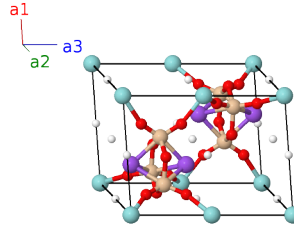

### Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1 =$	0	=	0	(2a)	Zr I
$\mathbf{B}_2 =$	$\frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}c \hat{\mathbf{z}}$	(2a)	Zr I
$\mathbf{B}_3 =$	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4f)	Na I
$\mathbf{B}_4 =$	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4f)	Na I
$\mathbf{B}_5 =$	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4f)	Na I
$\mathbf{B}_6 =$	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4f)	Na I
$\mathbf{B}_7 =$	$\frac{1}{2} \mathbf{a}_1$	=	$\frac{1}{4}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{4}a \hat{\mathbf{y}}$	(6g)	H I
$\mathbf{B}_8 =$	$\frac{1}{2} \mathbf{a}_2$	=	$\frac{1}{4}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{4}a \hat{\mathbf{y}}$	(6g)	H I
$\mathbf{B}_9 =$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	=	$\frac{1}{2}a \hat{\mathbf{x}}$	(6g)	H I
$\mathbf{B}_{10} =$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{4}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{4}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	H I
$\mathbf{B}_{11} =$	$\frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{4}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{4}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	H I
$\mathbf{B}_{12} =$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	H I
$\mathbf{B}_{13} =$	$x_4 \mathbf{a}_1 + 2x_4 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	=	$\frac{3}{2}ax_4 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	O I
$\mathbf{B}_{14} =$	$-2x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	=	$-\frac{3}{2}ax_4 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	O I
$\mathbf{B}_{15} =$	$x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	=	$-\sqrt{3}ax_4 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	O I
$\mathbf{B}_{16} =$	$-x_4 \mathbf{a}_1 - 2x_4 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	=	$-\frac{3}{2}ax_4 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6h)	O I
$\mathbf{B}_{17} =$	$2x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	=	$\frac{3}{2}ax_4 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6h)	O I

$$\begin{aligned}
\mathbf{B}_{18} &= -x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3 &= \sqrt{3}ax_4 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}} &(6h) & \text{O I} \\
\mathbf{B}_{19} &= x_5 \mathbf{a}_1 + 2x_5 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3 &= \frac{3}{2}ax_5 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_5 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}} &(6h) & \text{Si I} \\
\mathbf{B}_{20} &= -2x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3 &= -\frac{3}{2}ax_5 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_5 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}} &(6h) & \text{Si I} \\
\mathbf{B}_{21} &= x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3 &= -\sqrt{3}ax_5 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}} &(6h) & \text{Si I} \\
\mathbf{B}_{22} &= -x_5 \mathbf{a}_1 - 2x_5 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3 &= -\frac{3}{2}ax_5 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_5 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}} &(6h) & \text{Si I} \\
\mathbf{B}_{23} &= 2x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3 &= \frac{3}{2}ax_5 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_5 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}} &(6h) & \text{Si I} \\
\mathbf{B}_{24} &= -x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3 &= \sqrt{3}ax_5 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}} &(6h) & \text{Si I} \\
\mathbf{B}_{25} &= x_6 \mathbf{a}_1 + 2x_6 \mathbf{a}_2 + z_6 \mathbf{a}_3 &= \frac{3}{2}ax_6 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_6 \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}} &(12k) & \text{O II} \\
\mathbf{B}_{26} &= -2x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 + z_6 \mathbf{a}_3 &= -\frac{3}{2}ax_6 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_6 \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}} &(12k) & \text{O II} \\
\mathbf{B}_{27} &= x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 + z_6 \mathbf{a}_3 &= -\sqrt{3}ax_6 \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}} &(12k) & \text{O II} \\
\mathbf{B}_{28} &= -x_6 \mathbf{a}_1 - 2x_6 \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3 &= -\frac{3}{2}ax_6 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \hat{\mathbf{z}} &(12k) & \text{O II} \\
\mathbf{B}_{29} &= 2x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3 &= \frac{3}{2}ax_6 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \hat{\mathbf{z}} &(12k) & \text{O II} \\
\mathbf{B}_{30} &= -x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3 &= \sqrt{3}ax_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \hat{\mathbf{z}} &(12k) & \text{O II} \\
\mathbf{B}_{31} &= 2x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 - z_6 \mathbf{a}_3 &= \frac{3}{2}ax_6 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_6 \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}} &(12k) & \text{O II} \\
\mathbf{B}_{32} &= -x_6 \mathbf{a}_1 - 2x_6 \mathbf{a}_2 - z_6 \mathbf{a}_3 &= -\frac{3}{2}ax_6 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_6 \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}} &(12k) & \text{O II} \\
\mathbf{B}_{33} &= -x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 - z_6 \mathbf{a}_3 &= \sqrt{3}ax_6 \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}} &(12k) & \text{O II} \\
\mathbf{B}_{34} &= -2x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3 &= -\frac{3}{2}ax_6 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_6 \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \hat{\mathbf{z}} &(12k) & \text{O II} \\
\mathbf{B}_{35} &= x_6 \mathbf{a}_1 + 2x_6 \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3 &= \frac{3}{2}ax_6 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_6 \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \hat{\mathbf{z}} &(12k) & \text{O II} \\
\mathbf{B}_{36} &= x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3 &= -\sqrt{3}ax_6 \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \hat{\mathbf{z}} &(12k) & \text{O II}
\end{aligned}$$

## References

- [1] B. Brunowski, *Die Struktur des Katapleits*, Acta physicochim. USSR **5**, 863–892 (1936).  
[2] C. Gottfried and F. Schossberger, eds., *Strukturbericht Band III 1933-1935* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1937).

## Found in

- [1] C. Gottfried, ed., *Strukturbericht Band V 1937* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1940).