





# Pyrostilpnite ( $\text{Ag}_3\text{SbS}_3$ ) Structure: A3B3C\_mP28\_14\_3e\_3e\_e-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/8N0K>

[https://aflow.org/p/A3B3C\\_mP28\\_14\\_3e\\_3e\\_e-001](https://aflow.org/p/A3B3C_mP28_14_3e_3e_e-001)

● Ag  
● S  
● Sb

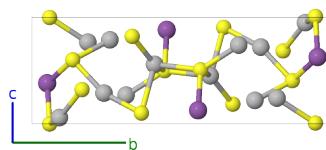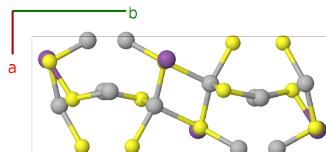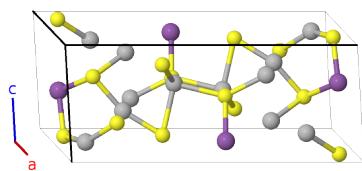

**Prototype**  $\text{Ag}_3\text{S}_3\text{Sb}$

**AFLOW prototype label** A3B3C\_mP28\_14\_3e\_3e\_e-001

**Mineral name** pyrostilpnite

**ICSD** 17780

**Pearson symbol** mP28

**Space group number** 14

**Space group symbol**  $P2_1/c$


**AFLOW prototype command**

```
aflow --proto=A3B3C_mP28_14_3e_3e_e-001
--params=a,b/a,c/a,\beta,x1,y1,z1,x2,y2,z2,x3,y3,z3,x4,y4,z4,x5,y5,z5,x6,y6,z6,x7,
y7,z7
```

- $\text{Ag}_3\text{SbS}_3$  can also be found as the mineral pyrargyrite, which has the proustite ( $\text{Ag}_3\text{AsS}_3$ ) structure.

**Simple Monoclinic primitive vectors**

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}\end{aligned}$$

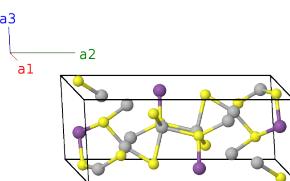

**Basis vectors**

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
<b>B<sub>1</sub></b>	= $x_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	=	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	Ag I
<b>B<sub>2</sub></b>	= $-x_1 \mathbf{a}_1 + (y_1 + \frac{1}{2}) \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_1 + c(z_1 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_1 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Ag I
<b>B<sub>3</sub></b>	= $-x_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	=	$-(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} - cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	Ag I
<b>B<sub>4</sub></b>	= $x_1 \mathbf{a}_1 - (y_1 - \frac{1}{2}) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_1 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Ag I
<b>B<sub>5</sub></b>	= $x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	Ag II
<b>B<sub>6</sub></b>	= $-x_2 \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_2 + c(z_2 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Ag II
<b>B<sub>7</sub></b>	= $-x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	Ag II
<b>B<sub>8</sub></b>	= $x_2 \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Ag II
<b>B<sub>9</sub></b>	= $x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	Ag III
<b>B<sub>10</sub></b>	= $-x_3 \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Ag III
<b>B<sub>11</sub></b>	= $-x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	Ag III
<b>B<sub>12</sub></b>	= $x_3 \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Ag III
<b>B<sub>13</sub></b>	= $x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	S I
<b>B<sub>14</sub></b>	= $-x_4 \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_4 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	S I
<b>B<sub>15</sub></b>	= $-x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	=	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	S I
<b>B<sub>16</sub></b>	= $x_4 \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_4 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	S I
<b>B<sub>17</sub></b>	= $x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	=	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4e)	S II
<b>B<sub>18</sub></b>	= $-x_5 \mathbf{a}_1 + (y_5 + \frac{1}{2}) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_5 + c(z_5 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_5 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	S II
<b>B<sub>19</sub></b>	= $-x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	=	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(4e)	S II
<b>B<sub>20</sub></b>	= $x_5 \mathbf{a}_1 - (y_5 - \frac{1}{2}) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_5 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	S II
<b>B<sub>21</sub></b>	= $x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	=	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(4e)	S III
<b>B<sub>22</sub></b>	= $-x_6 \mathbf{a}_1 + (y_6 + \frac{1}{2}) \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_6 + c(z_6 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_6 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	S III
<b>B<sub>23</sub></b>	= $-x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 - z_6 \mathbf{a}_3$	=	$-(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \sin \beta \hat{\mathbf{z}}$	(4e)	S III
<b>B<sub>24</sub></b>	= $x_6 \mathbf{a}_1 - (y_6 - \frac{1}{2}) \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_6 + c(z_6 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_6 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	S III
<b>B<sub>25</sub></b>	= $x_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$	=	$(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \sin \beta \hat{\mathbf{z}}$	(4e)	Sb I
<b>B<sub>26</sub></b>	= $-x_7 \mathbf{a}_1 + (y_7 + \frac{1}{2}) \mathbf{a}_2 - (z_7 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_7 + c(z_7 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_7 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Sb I
<b>B<sub>27</sub></b>	= $-x_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$	=	$-(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} - cz_7 \sin \beta \hat{\mathbf{z}}$	(4e)	Sb I
<b>B<sub>28</sub></b>	= $x_7 \mathbf{a}_1 - (y_7 - \frac{1}{2}) \mathbf{a}_2 + (z_7 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_7 + c(z_7 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_7 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Sb I

## References

- [1] C. Biagioni, F. Zaccarini, P. Roth, and L. Bindi, *Progress in the knowledge of ‘ruby silvers’: New structural and chemical data of pyrostilpnite,  $Ag_3SbS_3$* , Mineral. Mag. **84**, 463–467 (2020), doi:10.1180/mgm.2020.37.