


U₂Mn₃Si₅ Structure: A3B5C2_tP40_128_dh_egh_h-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://afLOW.org/p/P4UA>

https://afLOW.org/p/A3B5C2_tP40_128_dh_egh_h-001

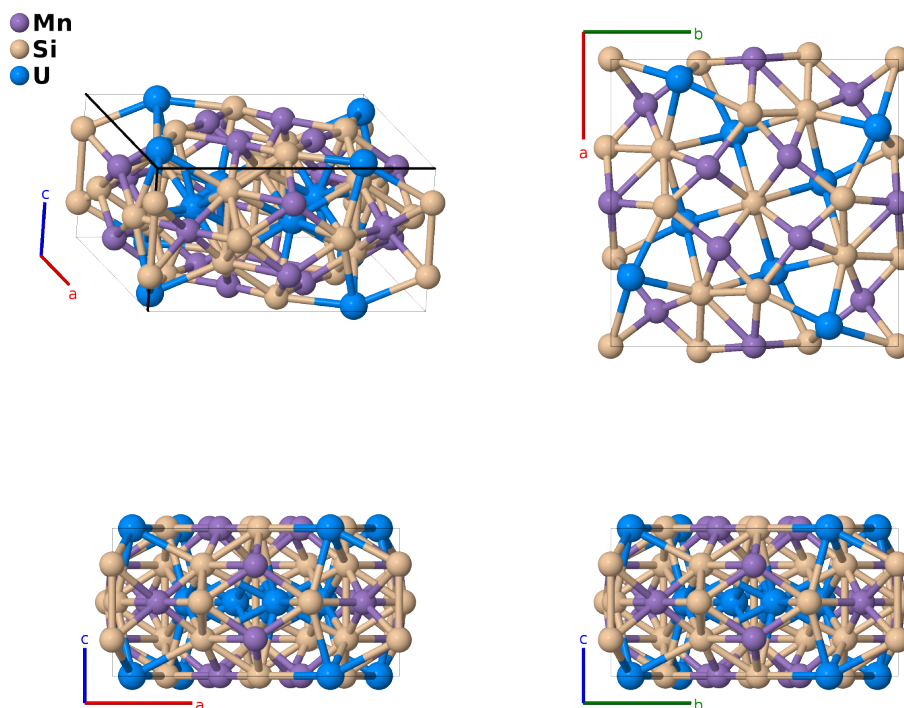

Prototype	Mn ₃ Si ₅ U ₂
AFLOW prototype label	A3B5C2_tP40_128_dh_egh_h-001
ICSD	20929
Pearson symbol	tP40
Space group number	128
Space group symbol	<i>P4/mnc</i>
AFLOW prototype command	<code>afLOW --proto=A3B5C2_tP40_128_dh_egh_h-001 --params=a, c/a, z₂, x₃, x₄, y₄, x₅, y₅, x₆, y₆</code>


Other compounds with this structure

Ce₂Co₃Si₅, Ce₂Ni₃Si₅, Ce₂Ru₃Ga₅, Dy₂Ni₃Si₅, Dy₂Ru₃Ge₅, Dy₂Ru₃Si₅, Er₂Mn₃Si₅, Gd₂Re₃Si₅, La₂Ru₃Ga₅, Lu₂Fe₃Si₅, Lu₂Ru₃Si₅, Nd₂Os₃Ga₅, Nd₂Ru₃Ga₅, Np₂Re₃Ga₅, Pr₂Ru₃Ga₅, Pr₂Ru₃Ge₅, Pu₂Fe₃Ga₅, Pu₂Re₃Ga₅, Pu₂Tc₃Ga₅, Rb₂Os₃Si₅, Sc₂Fe₃Si₅, Sm₂Ru₃Ga₅, Sm₂Ru₃Ge₅, Tb₂Mn₃Si₅, U₂Tc₃Ga₅, Y₂Ni₃Si₅

- Some authors refer to this as the Sc₂Fe₃Si₅ type.

Simple Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

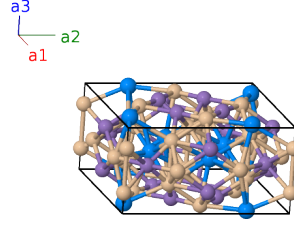

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= \frac{1}{2} \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{4} c \hat{\mathbf{z}}$	(4d)	Mn I
\mathbf{B}_2	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{4} c \hat{\mathbf{z}}$	(4d)	Mn I
\mathbf{B}_3	$= \frac{1}{2} \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{y}} + \frac{3}{4} c \hat{\mathbf{z}}$	(4d)	Mn I
\mathbf{B}_4	$= \frac{1}{2} \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{3}{4} c \hat{\mathbf{z}}$	(4d)	Mn I
\mathbf{B}_5	$= z_2 \mathbf{a}_3$	$=$	$c z_2 \hat{\mathbf{z}}$	(4e)	Si I
\mathbf{B}_6	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} - c (z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4e)	Si I
\mathbf{B}_7	$= -z_2 \mathbf{a}_3$	$=$	$-c z_2 \hat{\mathbf{z}}$	(4e)	Si I
\mathbf{B}_8	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + c (z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4e)	Si I
\mathbf{B}_9	$= x_3 \mathbf{a}_1 + (x_3 + \frac{1}{2}) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$a x_3 \hat{\mathbf{x}} + a (x_3 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{4} c \hat{\mathbf{z}}$	(8g)	Si II
\mathbf{B}_{10}	$= -x_3 \mathbf{a}_1 - (x_3 - \frac{1}{2}) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$-a x_3 \hat{\mathbf{x}} - a (x_3 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{4} c \hat{\mathbf{z}}$	(8g)	Si II
\mathbf{B}_{11}	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 + x_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$-a (x_3 - \frac{1}{2}) \hat{\mathbf{x}} + a x_3 \hat{\mathbf{y}} + \frac{1}{4} c \hat{\mathbf{z}}$	(8g)	Si II
\mathbf{B}_{12}	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$a (x_3 + \frac{1}{2}) \hat{\mathbf{x}} - a x_3 \hat{\mathbf{y}} + \frac{1}{4} c \hat{\mathbf{z}}$	(8g)	Si II
\mathbf{B}_{13}	$= -x_3 \mathbf{a}_1 - (x_3 - \frac{1}{2}) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-a x_3 \hat{\mathbf{x}} - a (x_3 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{3}{4} c \hat{\mathbf{z}}$	(8g)	Si II
\mathbf{B}_{14}	$= x_3 \mathbf{a}_1 + (x_3 + \frac{1}{2}) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$a x_3 \hat{\mathbf{x}} + a (x_3 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{3}{4} c \hat{\mathbf{z}}$	(8g)	Si II
\mathbf{B}_{15}	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$a (x_3 + \frac{1}{2}) \hat{\mathbf{x}} - a x_3 \hat{\mathbf{y}} + \frac{3}{4} c \hat{\mathbf{z}}$	(8g)	Si II
\mathbf{B}_{16}	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 + x_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-a (x_3 - \frac{1}{2}) \hat{\mathbf{x}} + a x_3 \hat{\mathbf{y}} + \frac{3}{4} c \hat{\mathbf{z}}$	(8g)	Si II
\mathbf{B}_{17}	$= x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2$	$=$	$a x_4 \hat{\mathbf{x}} + a y_4 \hat{\mathbf{y}}$	(8h)	Mn II
\mathbf{B}_{18}	$= -x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2$	$=$	$-a x_4 \hat{\mathbf{x}} - a y_4 \hat{\mathbf{y}}$	(8h)	Mn II
\mathbf{B}_{19}	$= -y_4 \mathbf{a}_1 + x_4 \mathbf{a}_2$	$=$	$-a y_4 \hat{\mathbf{x}} + a x_4 \hat{\mathbf{y}}$	(8h)	Mn II
\mathbf{B}_{20}	$= y_4 \mathbf{a}_1 - x_4 \mathbf{a}_2$	$=$	$a y_4 \hat{\mathbf{x}} - a x_4 \hat{\mathbf{y}}$	(8h)	Mn II
\mathbf{B}_{21}	$= -(x_4 - \frac{1}{2}) \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-a (x_4 - \frac{1}{2}) \hat{\mathbf{x}} + a (y_4 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(8h)	Mn II
\mathbf{B}_{22}	$= (x_4 + \frac{1}{2}) \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$a (x_4 + \frac{1}{2}) \hat{\mathbf{x}} - a (y_4 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(8h)	Mn II
\mathbf{B}_{23}	$= (y_4 + \frac{1}{2}) \mathbf{a}_1 + (x_4 + \frac{1}{2}) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$a (y_4 + \frac{1}{2}) \hat{\mathbf{x}} + a (x_4 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(8h)	Mn II
\mathbf{B}_{24}	$= -(y_4 - \frac{1}{2}) \mathbf{a}_1 - (x_4 - \frac{1}{2}) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-a (y_4 - \frac{1}{2}) \hat{\mathbf{x}} - a (x_4 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(8h)	Mn II
\mathbf{B}_{25}	$= x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2$	$=$	$a x_5 \hat{\mathbf{x}} + a y_5 \hat{\mathbf{y}}$	(8h)	Si III
\mathbf{B}_{26}	$= -x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2$	$=$	$-a x_5 \hat{\mathbf{x}} - a y_5 \hat{\mathbf{y}}$	(8h)	Si III
\mathbf{B}_{27}	$= -y_5 \mathbf{a}_1 + x_5 \mathbf{a}_2$	$=$	$-a y_5 \hat{\mathbf{x}} + a x_5 \hat{\mathbf{y}}$	(8h)	Si III

$$\begin{aligned}
\mathbf{B}_{28} &= y_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 &= ay_5 \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}} & (8h) & \text{Si III} \\
\mathbf{B}_{29} &= -\left(x_5 - \frac{1}{2}\right) \mathbf{a}_1 + \left(y_5 + \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= -a\left(x_5 - \frac{1}{2}\right) \hat{\mathbf{x}} + a\left(y_5 + \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} & (8h) & \text{Si III} \\
\mathbf{B}_{30} &= \left(x_5 + \frac{1}{2}\right) \mathbf{a}_1 - \left(y_5 - \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= a\left(x_5 + \frac{1}{2}\right) \hat{\mathbf{x}} - a\left(y_5 - \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} & (8h) & \text{Si III} \\
\mathbf{B}_{31} &= \left(y_5 + \frac{1}{2}\right) \mathbf{a}_1 + \left(x_5 + \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= a\left(y_5 + \frac{1}{2}\right) \hat{\mathbf{x}} + a\left(x_5 + \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} & (8h) & \text{Si III} \\
\mathbf{B}_{32} &= -\left(y_5 - \frac{1}{2}\right) \mathbf{a}_1 - \left(x_5 - \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= -a\left(y_5 - \frac{1}{2}\right) \hat{\mathbf{x}} - a\left(x_5 - \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} & (8h) & \text{Si III} \\
\mathbf{B}_{33} &= x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 &= ax_6 \hat{\mathbf{x}} + ay_6 \hat{\mathbf{y}} & (8h) & \text{U I} \\
\mathbf{B}_{34} &= -x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 &= -ax_6 \hat{\mathbf{x}} - ay_6 \hat{\mathbf{y}} & (8h) & \text{U I} \\
\mathbf{B}_{35} &= -y_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 &= -ay_6 \hat{\mathbf{x}} + ax_6 \hat{\mathbf{y}} & (8h) & \text{U I} \\
\mathbf{B}_{36} &= y_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 &= ay_6 \hat{\mathbf{x}} - ax_6 \hat{\mathbf{y}} & (8h) & \text{U I} \\
\mathbf{B}_{37} &= -\left(x_6 - \frac{1}{2}\right) \mathbf{a}_1 + \left(y_6 + \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= -a\left(x_6 - \frac{1}{2}\right) \hat{\mathbf{x}} + a\left(y_6 + \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} & (8h) & \text{U I} \\
\mathbf{B}_{38} &= \left(x_6 + \frac{1}{2}\right) \mathbf{a}_1 - \left(y_6 - \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= a\left(x_6 + \frac{1}{2}\right) \hat{\mathbf{x}} - a\left(y_6 - \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} & (8h) & \text{U I} \\
\mathbf{B}_{39} &= \left(y_6 + \frac{1}{2}\right) \mathbf{a}_1 + \left(x_6 + \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= a\left(y_6 + \frac{1}{2}\right) \hat{\mathbf{x}} + a\left(x_6 + \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} & (8h) & \text{U I} \\
\mathbf{B}_{40} &= -\left(y_6 - \frac{1}{2}\right) \mathbf{a}_1 - \left(x_6 - \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= -a\left(y_6 - \frac{1}{2}\right) \hat{\mathbf{x}} - a\left(x_6 - \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} & (8h) & \text{U I}
\end{aligned}$$

References

- [1] Y. P. Yarmolyuk, L. G. Aksel'rud, and E. I. Gladyshevskii, *Crystal structure of the compound $U_2Mn_3Si_5$* , Sov. Phys. Crystallogr. **22**, 358–359 (1977).

Found in

- [1] W. Jeitschko and M. Schlüter, *Rare Earth Ruthenium Gallides with the Ideal Composition $Ln_2Ru_3Ga_5$ ($Ln = La-Nd, Sm$) crystallizing with $U_2Mn_3Si_5$ ($Sc_2Fe_3Si_5$) Type Structure*, Z. Anorganische und Allgemeine Chemie **636**, 1100–1105 (2010), doi:10.1002/zaac.200900530.