

Fe₃Th₇ ($D10_2$) Structure: A3B7_hP20_186_c_b2c-001







This structure originally had the label A3B7_hP20_186_c_b2c. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043

<https://aflow.org/p/VG VG>

https://aflow.org/p/A3B7_hP20_186_c_b2c-001

● Fe
● Th

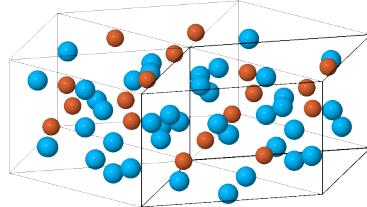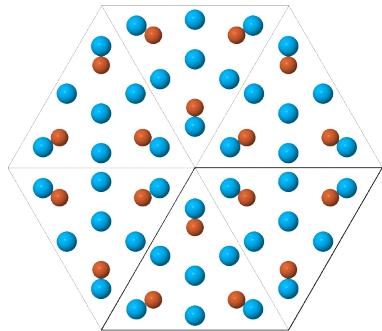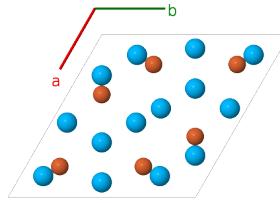

Prototype	Fe ₃ Th ₇
AFLOW prototype label	A3B7_hP20_186_c_b2c-001
Strukturbericht designation	$D10_2$
ICSD	108477
Pearson symbol	hP20
Space group number	186
Space group symbol	$P6_3mc$


AFLOW prototype command `aflow --proto=A3B7_hP20_186_c_b2c-001
--params=a, c/a, z1, x2, z2, x3, z3, x4, z4`

Other compounds with this structure

B₃CoRh₆, B₃FeRh₆, B₃Ni₇, B₃Re₇, B₃Rh₇, B₃Ru₇, B₃Tc₇, C₃Fe₇, Co₃Nd₇, Co₃Th₇, Ir₃Ce₇, Ir₃La₇, Ir₃Pr₇, Ir₃Th₇, Ni₃Ce₇, Ni₃La₇, Ni₃Nd₇, Ni₃Pr₇, Ni₃Th₇, Os₃Th₇, Pd₃Ce₇, Pd₃Gd₇, Pd₃La₇, Pd₃Nd₇, Pd₃Pr₇, Pd₃Sm₇, Pd₃Tb₇, Pd₃Th₇, Pt₃La₇, Pt₃Nd₇, Pt₃Th₇, Rh₃Ce₇, Rh₃Dy₇, Rh₃Gd₇, Rh₃Ho₇, Rh₃La₇, Rh₃Nd₇, Rh₃Pr₇, Rh₃Sm₇, Rh₃Tb₇, Rh₃Th₇, Ru₃Th₇

Hexagonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_3 &= c\hat{\mathbf{z}}\end{aligned}$$



Basis vectors

	Lattice coordinates	Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_1\mathbf{a}_3$	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_1\hat{\mathbf{z}}$	(2b)	Th I
\mathbf{B}_2	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 + (z_1 + \frac{1}{2})\mathbf{a}_3$	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + c(z_1 + \frac{1}{2})\hat{\mathbf{z}}$	(2b)	Th I
\mathbf{B}_3	$x_2\mathbf{a}_1 - x_2\mathbf{a}_2 + z_2\mathbf{a}_3$	$-\sqrt{3}ax_2\hat{\mathbf{y}} + cz_2\hat{\mathbf{z}}$	(6c)	Fe I
\mathbf{B}_4	$x_2\mathbf{a}_1 + 2x_2\mathbf{a}_2 + z_2\mathbf{a}_3$	$\frac{3}{2}ax_2\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_2\hat{\mathbf{y}} + cz_2\hat{\mathbf{z}}$	(6c)	Fe I
\mathbf{B}_5	$-2x_2\mathbf{a}_1 - x_2\mathbf{a}_2 + z_2\mathbf{a}_3$	$-\frac{3}{2}ax_2\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_2\hat{\mathbf{y}} + cz_2\hat{\mathbf{z}}$	(6c)	Fe I
\mathbf{B}_6	$-x_2\mathbf{a}_1 + x_2\mathbf{a}_2 + (z_2 + \frac{1}{2})\mathbf{a}_3$	$\sqrt{3}ax_2\hat{\mathbf{y}} + c(z_2 + \frac{1}{2})\hat{\mathbf{z}}$	(6c)	Fe I
\mathbf{B}_7	$-x_2\mathbf{a}_1 - 2x_2\mathbf{a}_2 + (z_2 + \frac{1}{2})\mathbf{a}_3$	$-\frac{3}{2}ax_2\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_2\hat{\mathbf{y}} + c(z_2 + \frac{1}{2})\hat{\mathbf{z}}$	(6c)	Fe I
\mathbf{B}_8	$2x_2\mathbf{a}_1 + x_2\mathbf{a}_2 + (z_2 + \frac{1}{2})\mathbf{a}_3$	$\frac{3}{2}ax_2\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_2\hat{\mathbf{y}} + c(z_2 + \frac{1}{2})\hat{\mathbf{z}}$	(6c)	Fe I
\mathbf{B}_9	$x_3\mathbf{a}_1 - x_3\mathbf{a}_2 + z_3\mathbf{a}_3$	$-\sqrt{3}ax_3\hat{\mathbf{y}} + cz_3\hat{\mathbf{z}}$	(6c)	Th II
\mathbf{B}_{10}	$x_3\mathbf{a}_1 + 2x_3\mathbf{a}_2 + z_3\mathbf{a}_3$	$\frac{3}{2}ax_3\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3\hat{\mathbf{y}} + cz_3\hat{\mathbf{z}}$	(6c)	Th II
\mathbf{B}_{11}	$-2x_3\mathbf{a}_1 - x_3\mathbf{a}_2 + z_3\mathbf{a}_3$	$-\frac{3}{2}ax_3\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3\hat{\mathbf{y}} + cz_3\hat{\mathbf{z}}$	(6c)	Th II
\mathbf{B}_{12}	$-x_3\mathbf{a}_1 + x_3\mathbf{a}_2 + (z_3 + \frac{1}{2})\mathbf{a}_3$	$\sqrt{3}ax_3\hat{\mathbf{y}} + c(z_3 + \frac{1}{2})\hat{\mathbf{z}}$	(6c)	Th II
\mathbf{B}_{13}	$-x_3\mathbf{a}_1 - 2x_3\mathbf{a}_2 + (z_3 + \frac{1}{2})\mathbf{a}_3$	$-\frac{3}{2}ax_3\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3\hat{\mathbf{y}} + c(z_3 + \frac{1}{2})\hat{\mathbf{z}}$	(6c)	Th II
\mathbf{B}_{14}	$2x_3\mathbf{a}_1 + x_3\mathbf{a}_2 + (z_3 + \frac{1}{2})\mathbf{a}_3$	$\frac{3}{2}ax_3\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3\hat{\mathbf{y}} + c(z_3 + \frac{1}{2})\hat{\mathbf{z}}$	(6c)	Th II
\mathbf{B}_{15}	$x_4\mathbf{a}_1 - x_4\mathbf{a}_2 + z_4\mathbf{a}_3$	$-\sqrt{3}ax_4\hat{\mathbf{y}} + cz_4\hat{\mathbf{z}}$	(6c)	Th III
\mathbf{B}_{16}	$x_4\mathbf{a}_1 + 2x_4\mathbf{a}_2 + z_4\mathbf{a}_3$	$\frac{3}{2}ax_4\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4\hat{\mathbf{y}} + cz_4\hat{\mathbf{z}}$	(6c)	Th III
\mathbf{B}_{17}	$-2x_4\mathbf{a}_1 - x_4\mathbf{a}_2 + z_4\mathbf{a}_3$	$-\frac{3}{2}ax_4\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4\hat{\mathbf{y}} + cz_4\hat{\mathbf{z}}$	(6c)	Th III
\mathbf{B}_{18}	$-x_4\mathbf{a}_1 + x_4\mathbf{a}_2 + (z_4 + \frac{1}{2})\mathbf{a}_3$	$\sqrt{3}ax_4\hat{\mathbf{y}} + c(z_4 + \frac{1}{2})\hat{\mathbf{z}}$	(6c)	Th III
\mathbf{B}_{19}	$-x_4\mathbf{a}_1 - 2x_4\mathbf{a}_2 + (z_4 + \frac{1}{2})\mathbf{a}_3$	$-\frac{3}{2}ax_4\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_4\hat{\mathbf{y}} + c(z_4 + \frac{1}{2})\hat{\mathbf{z}}$	(6c)	Th III
\mathbf{B}_{20}	$2x_4\mathbf{a}_1 + x_4\mathbf{a}_2 + (z_4 + \frac{1}{2})\mathbf{a}_3$	$\frac{3}{2}ax_4\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_4\hat{\mathbf{y}} + c(z_4 + \frac{1}{2})\hat{\mathbf{z}}$	(6c)	Th III

References

- [1] J. V. Florio, N. C. Baenziger, and R. E. Rundle, *Compounds of thorium with transition metals. II. Systems with iron, cobalt and nickel* **9**, 367–372 (1956), doi:10.1107/S0365110X5600108X.

Found in

[1] ICSD, *Inorganic Crystal Structure Database*. 108477.