


K₃SnTe₃ (K₆Sn₂Te₆) Structure: A3BC3_mP28_14_3e_e_3e-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/HJ0Y>

https://aflow.org/prototype-encyclopedia/A3BC3_mP28_14_3e_e_3e-001

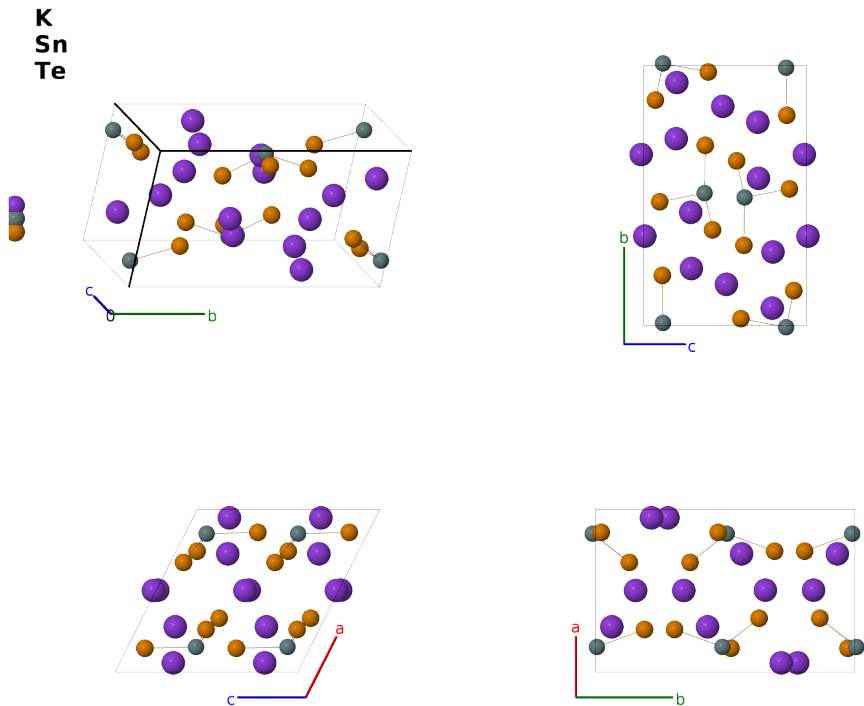

Prototype	K ₃ SnTe ₃
AFLOW prototype label	A3BC3_mP28_14_3e_e_3e-001
ICSD	10109
CCDC	1594983
Pearson symbol	mP28
Space group number	14
Space group symbol	$P2_1/c$
AFLOW prototype command	<pre>aflow --proto=A3BC3_mP28_14_3e_e_3e-001 --params=a,b/a,c/a,β,x₁,y₁,z₁,x₂,y₂,z₂,x₃,y₃,z₃,x₄,y₄,z₄,x₅,y₅,z₅,x₆,y₆,z₆,x₇,y₇,z₇</pre>


Other compounds with this structure

Ba₃SnP₃, K₃SnSe₃, Na₃GeSn₃, Na₃SiTe₃

- The ICSD lists α -AgCuPO₄ as a quaternary version of this structure.
- Although the print copy of (Dittmar, 1979) and the reference to it in (Eisenmann, 1985) give the publication date of 1978, the actual publication date is June, 1979.

Simple Monoclinic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}} \end{aligned}$$

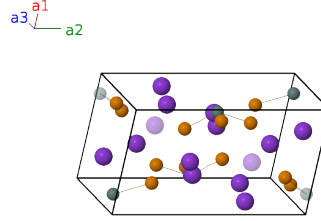

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	K I
$\mathbf{B}_2$	$= -x_1 \mathbf{a}_1 + (y_1 + \frac{1}{2}) \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_1 + c(z_1 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_1 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	K I
$\mathbf{B}_3$	$= -x_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} - cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	K I
$\mathbf{B}_4$	$= x_1 \mathbf{a}_1 - (y_1 - \frac{1}{2}) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_1 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	K I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	K II
$\mathbf{B}_6$	$= -x_2 \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_2 + c(z_2 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	K II
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	K II
$\mathbf{B}_8$	$= x_2 \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	K II
$\mathbf{B}_9$	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	K III
$\mathbf{B}_{10}$	$= -x_3 \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	K III
$\mathbf{B}_{11}$	$= -x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	K III
$\mathbf{B}_{12}$	$= x_3 \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	K III
$\mathbf{B}_{13}$	$= x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	Sn I
$\mathbf{B}_{14}$	$= -x_4 \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_4 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Sn I
$\mathbf{B}_{15}$	$= -x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	Sn I

$$\begin{aligned}
\mathbf{B}_{16} &= x_4 \mathbf{a}_1 - \left(y_4 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} (ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - \\ b(y_4 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Sn I} \\
\mathbf{B}_{17} &= x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3 = \begin{pmatrix} (ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te I} \\
\mathbf{B}_{18} &= -x_5 \mathbf{a}_1 + \left(y_5 + \frac{1}{2}\right) \mathbf{a}_2 - \left(z_5 - \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} -(ax_5 + c(z_5 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + \\ b(y_5 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te I} \\
\mathbf{B}_{19} &= -x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3 = \begin{pmatrix} -(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te I} \\
\mathbf{B}_{20} &= x_5 \mathbf{a}_1 - \left(y_5 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_5 + \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} (ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - \\ b(y_5 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te I} \\
\mathbf{B}_{21} &= x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3 = \begin{pmatrix} (ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te II} \\
\mathbf{B}_{22} &= -x_6 \mathbf{a}_1 + \left(y_6 + \frac{1}{2}\right) \mathbf{a}_2 - \left(z_6 - \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} -(ax_6 + c(z_6 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + \\ b(y_6 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te II} \\
\mathbf{B}_{23} &= -x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 - z_6 \mathbf{a}_3 = \begin{pmatrix} -(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te II} \\
\mathbf{B}_{24} &= x_6 \mathbf{a}_1 - \left(y_6 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_6 + \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} (ax_6 + c(z_6 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - \\ b(y_6 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te II} \\
\mathbf{B}_{25} &= x_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3 = \begin{pmatrix} (ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te III} \\
\mathbf{B}_{26} &= -x_7 \mathbf{a}_1 + \left(y_7 + \frac{1}{2}\right) \mathbf{a}_2 - \left(z_7 - \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} -(ax_7 + c(z_7 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + \\ b(y_7 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te III} \\
\mathbf{B}_{27} &= -x_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 - z_7 \mathbf{a}_3 = \begin{pmatrix} -(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} - cz_7 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te III} \\
\mathbf{B}_{28} &= x_7 \mathbf{a}_1 - \left(y_7 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_7 + \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} (ax_7 + c(z_7 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - \\ b(y_7 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{Te III}
\end{aligned}$$

References

- [1] G. Dittmar, *Die Kristallstrukturen von $K_6[\text{Ge}_2\text{Te}_6]$ und $K_6[\text{Sn}_2\text{Te}_6]$ und ihre kristall-chemische Beziehung zum $K_6[\text{Si}_2\text{Te}_6]$ -Typ*, Z. Anorganische und Allgemeine Chemie **453**, 68–78 (1979), doi:10.1002/zaac.19794530609.

Found in

- [1] B. Eisenmann, J. Hansa, and H. Schäfer, *Oligoselenidogermanate (III): Zur kenntnis von $\text{Na}_6\text{Ge}_2\text{Se}_6$ und $\text{Na}_8\text{Ge}_4\text{Se}_{10}$* , MRS Bull. **20**, 1339–1346 (1985), doi:10.1016/0025-5408(85)90127-8.

First cited in

N. Anderson, M. J. Mehl, H. Eckert, S. Divilov, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 5*. Submitted to Computational Materials Science (2026).