


# $\beta$ -RuCl<sub>3</sub> Structure: A3B\_hP8\_185\_c\_a-001

This structure originally had the label A3B\_hP8\_185\_c\_a. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043

<https://aflow.org/p/5RVU>

[https://aflow.org/p/A3B\\_hP8\\_185\\_c\\_a-001](https://aflow.org/p/A3B_hP8_185_c_a-001)

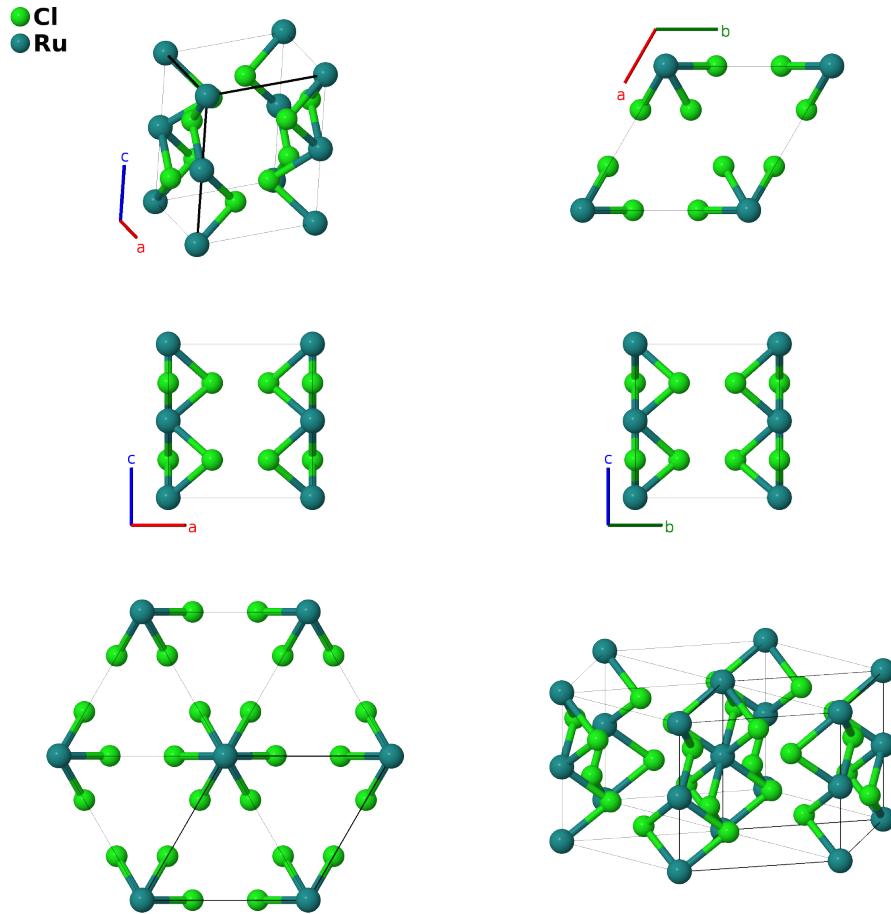


<b>Prototype</b>	Cl <sub>3</sub> Ru
<b>AFLOW prototype label</b>	A3B_hP8_185_c_a-001
<b>ICSD</b>	22092
<b>Pearson symbol</b>	hP8
<b>Space group number</b>	185
<b>Space group symbol</b>	$P6_3cm$
<b>AFLOW prototype command</b>	<code>aflow --proto=A3B_hP8_185_c_a-001 --params=a, c/a, z<sub>1</sub>, x<sub>2</sub>, z<sub>2</sub></code>

- The crystal structure of both  $\alpha$ - and  $\beta$ -RuCl<sub>3</sub> is somewhat uncertain:
- $\alpha$ -RuCl<sub>3</sub> has been reported in the trigonal CrCl<sub>3</sub> ( $D0_4$ ) structure (Fletcher, 1967) and in the monoclinic AlCl<sub>3</sub> structure (Johnson, 2015).
- (Fletcher, 1967) states that the structure of  $\beta$ -RuCl<sub>3</sub> is consistent with the hexagonal space groups  $P6_3cm$  #185 (this structure),  $P6c2$  #188, and  $P6_3/mcm$  #193, in addition to the trigonal space group  $P3c1$  #158, which we present here: trigonal  $\beta$ -RuCl<sub>3</sub> (A3B\_hP8\_158\_d\_a).
- Space group  $P6_3cm$  #185 allows an arbitrary choice of the origin of the  $z$ -axis. Here we set  $z_1 = 0$  for the ruthenium (2a) atoms.

### Hexagonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_3 &= c\hat{\mathbf{z}}\end{aligned}$$



### Basis vectors

	Lattice coordinates	=	Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$z_1 \mathbf{a}_3$	=	$cz_1 \hat{\mathbf{z}}$	(2a)	Ru I
$\mathbf{B}_2$	$(z_1 + \frac{1}{2}) \mathbf{a}_3$	=	$c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(2a)	Ru I
$\mathbf{B}_3$	$x_2 \mathbf{a}_1 + z_2 \mathbf{a}_3$	=	$\frac{1}{2}ax_2 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(6c)	Cl I
$\mathbf{B}_4$	$x_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$\frac{1}{2}ax_2 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(6c)	Cl I
$\mathbf{B}_5$	$-x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$-ax_2 \hat{\mathbf{x}} + cz_2 \hat{\mathbf{z}}$	(6c)	Cl I
$\mathbf{B}_6$	$-x_2 \mathbf{a}_1 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$-\frac{1}{2}ax_2 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(6c)	Cl I
$\mathbf{B}_7$	$-x_2 \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$-\frac{1}{2}ax_2 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(6c)	Cl I
$\mathbf{B}_8$	$x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$ax_2 \hat{\mathbf{x}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(6c)	Cl I

### References

- [1] J. M. Fletcher, W. E. Gardner, A. C. Fox, and G. Topping, *X-Ray, infrared, and magnetic studies of - and -ruthenium trichloride*, J. Chem. Soc. A pp. 1038–1045 (1967), doi:10.1039/J19670001038.