


ϵ -Al₃Ni (*D*0₂₀) Structure: A3B_oP16_62_cd_c-001

This structure originally had the label A3B_oP16_62_cd_c. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043

<https://afLOW.org/p/TJ6A>

https://afLOW.org/p/A3B_oP16_62_cd_c-001

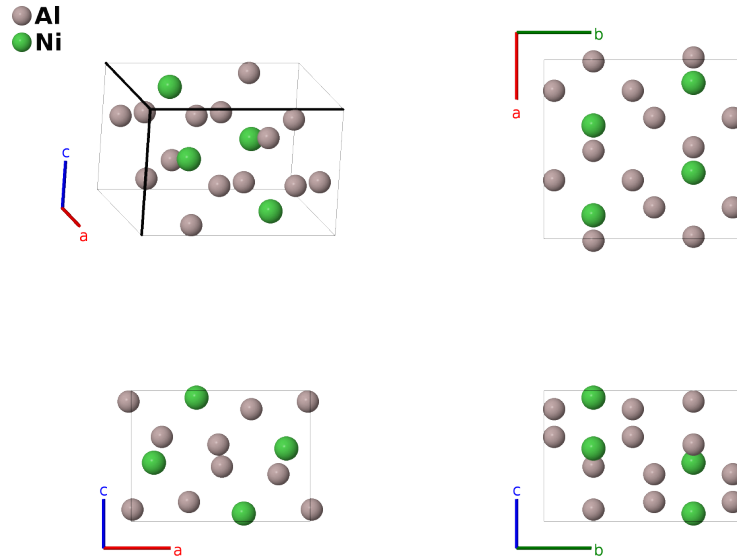


Prototype	Al ₃ Ni
AFLOW prototype label	A3B_oP16_62_cd_c-001
<i>Strukturbericht</i> designation	<i>D</i> 0 ₂₀
ICSD	58040
Pearson symbol	oP16
Space group number	62
Space group symbol	<i>Pnma</i>
AFLOW prototype command	<code>afLOW --proto=A3B_oP16_62_cd_c-001 --params=a, b/a, c/a, x₁, z₁, x₂, z₂, x₃, y₃, z₃</code>

Other compounds with this structure

In₃Ir

Simple Orthorhombic primitive vectors

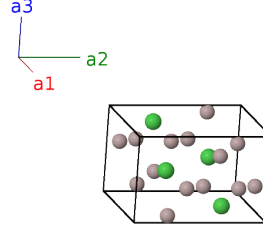

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

Basis vectors

	Lattice coordinates	=	Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_1 \mathbf{a}_3$	=	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4c)	Al I
\mathbf{B}_2	$= -(x_1 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	=	$-a(x_1 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Al I
\mathbf{B}_3	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_1 \mathbf{a}_3$	=	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	(4c)	Al I
\mathbf{B}_4	$= (x_1 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	=	$a(x_1 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Al I
\mathbf{B}_5	$= x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$ax_2 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4c)	Ni I
\mathbf{B}_6	$= -(x_2 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Ni I
\mathbf{B}_7	$= -x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$-ax_2 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4c)	Ni I
\mathbf{B}_8	$= (x_2 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	=	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Ni I
\mathbf{B}_9	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$ax_3 \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(8d)	Al II
\mathbf{B}_{10}	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 - y_3 \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Al II
\mathbf{B}_{11}	$= -x_3 \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-ax_3 \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(8d)	Al II
\mathbf{B}_{12}	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	=	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Al II
\mathbf{B}_{13}	$= -x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-ax_3 \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(8d)	Al II
\mathbf{B}_{14}	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 + y_3 \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	=	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Al II
\mathbf{B}_{15}	$= x_3 \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$ax_3 \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(8d)	Al II
\mathbf{B}_{16}	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Al II

References

- [1] A. J. Bradley and A. Taylor, *The crystal structures of Ni_2Al_3 and $NiAl_3$* , *Philos. Mag.* **23**, 1049–1067 (1937), doi:10.1080/14786443708561875.

Found in

- [1] W. B. Pearson, *A Handbook of Lattice Spacings and Structures of Metals and Alloys, International Series of Monographs on Metal Physics and Physical Metallurgy*, vol. 4 (Pergamon Press, Oxford, London, Edinburgh, New York, Paris, Frankfurt, 1958), 1964 reprint with corrections edn.