


Eulytine ($\text{Bi}_4(\text{SiO}_4)_3$, $S1_5$) Structure: A4B12C3_cI76_220_c_e_a-001

This structure originally had the label A4B12C3_cI76_220_c_e.a. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/p/VQL6>

https://aflow.org/p/A4B12C3_cI76_220_c_e_a-001

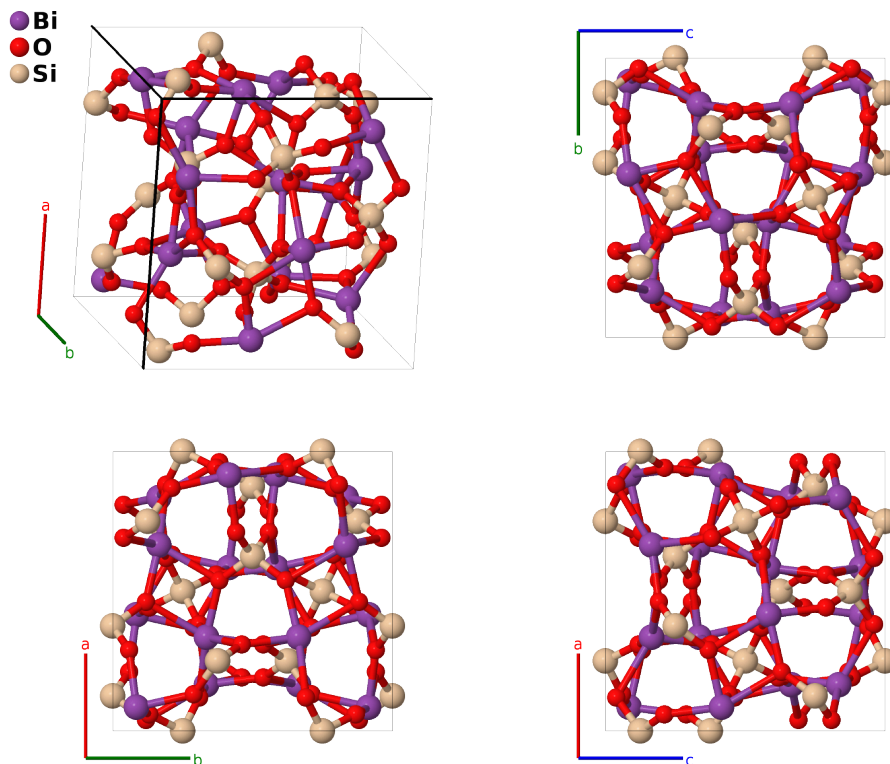

Prototype	$\text{Bi}_4\text{O}_{12}\text{Si}_3$
AFLOW prototype label	A4B12C3_cI76_220_c_e_a-001
<i>Strukturbericht</i> designation	$S1_5$
Mineral name	eulytine
ICSD	402349
Pearson symbol	cI76
Space group number	220
Space group symbol	$I\bar{4}3d$
AFLOW prototype command	<code>aflow --proto=A4B12C3_cI76_220_c_e_a-001 --params=a, x2, x3, y3, z3</code>

Other compounds with this structure


$\text{Ba}_3\text{Bi}(\text{PO}_4)_3$, $\text{Ba}_3\text{Gd}(\text{PO}_4)_3$, $\text{Ba}_3\text{In}(\text{PO}_4)_3$, $\text{Ba}_3\text{La}(\text{PO}_4)_3$, $\text{Ba}_3\text{Lu}(\text{PO}_4)_3$, $\text{Ba}_3\text{Nd}(\text{PO}_4)_3$, $\text{Ba}_3\text{Y}(\text{PO}_4)_3$, $\text{Sr}_3\text{Bi}(\text{PO}_4)_3$, $\text{Sr}_3\text{Gd}(\text{PO}_4)_3$, $\text{Sr}_3\text{In}(\text{PO}_4)_3$, $\text{Sr}_3\text{La}(\text{PO}_4)_3$, $\text{Sr}_3\text{Lu}(\text{PO}_4)_3$, $\text{Sr}_3\text{Nd}(\text{PO}_4)_3$, $\text{Sr}_3\text{Y}(\text{PO}_4)_3$, $\text{Bi}_4(\text{GeO}_4)_3$, $\text{Ca}_3\text{Bi}(\text{PO}_4)_3$

Body-centered Cubic primitive vectors

$$\mathbf{a}_1 = -\frac{1}{2}a\hat{x} + \frac{1}{2}a\hat{y} + \frac{1}{2}a\hat{z}$$

$$\mathbf{a}_2 = \frac{1}{2}a\hat{x} - \frac{1}{2}a\hat{y} + \frac{1}{2}a\hat{z}$$

$$\mathbf{a}_3 = \frac{1}{2}a\hat{x} + \frac{1}{2}a\hat{y} - \frac{1}{2}a\hat{z}$$

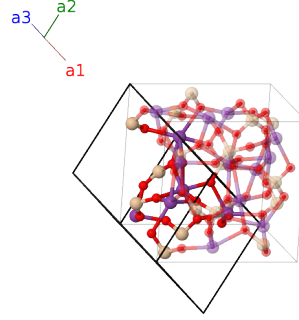

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= \frac{1}{4}\mathbf{a}_1 + \frac{5}{8}\mathbf{a}_2 + \frac{3}{8}\mathbf{a}_3$	$=$	$\frac{3}{8}a\hat{x} + \frac{1}{4}a\hat{z}$	(12a)	Si I
\mathbf{B}_2	$= \frac{3}{4}\mathbf{a}_1 + \frac{7}{8}\mathbf{a}_2 + \frac{1}{8}\mathbf{a}_3$	$=$	$\frac{1}{8}a\hat{x} + \frac{3}{4}a\hat{z}$	(12a)	Si I
\mathbf{B}_3	$= \frac{3}{8}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + \frac{5}{8}\mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{x} + \frac{3}{8}a\hat{y}$	(12a)	Si I
\mathbf{B}_4	$= \frac{1}{8}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 + \frac{7}{8}\mathbf{a}_3$	$=$	$\frac{3}{4}a\hat{x} + \frac{1}{8}a\hat{y}$	(12a)	Si I
\mathbf{B}_5	$= \frac{5}{8}\mathbf{a}_1 + \frac{3}{8}\mathbf{a}_2 + \frac{1}{4}\mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{y} + \frac{3}{8}a\hat{z}$	(12a)	Si I
\mathbf{B}_6	$= \frac{7}{8}\mathbf{a}_1 + \frac{1}{8}\mathbf{a}_2 + \frac{3}{4}\mathbf{a}_3$	$=$	$\frac{3}{4}a\hat{y} + \frac{1}{8}a\hat{z}$	(12a)	Si I
\mathbf{B}_7	$= 2x_2\mathbf{a}_1 + 2x_2\mathbf{a}_2 + 2x_2\mathbf{a}_3$	$=$	$ax_2\hat{x} + ax_2\hat{y} + ax_2\hat{z}$	(16c)	Bi I
\mathbf{B}_8	$= \frac{1}{2}\mathbf{a}_1 - (2x_2 - \frac{1}{2})\mathbf{a}_3$	$=$	$-ax_2\hat{x} - a(x_2 - \frac{1}{2})\hat{y} + ax_2\hat{z}$	(16c)	Bi I
\mathbf{B}_9	$= -(2x_2 - \frac{1}{2})\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{2})\hat{x} + ax_2\hat{y} - ax_2\hat{z}$	(16c)	Bi I
\mathbf{B}_{10}	$= -(2x_2 - \frac{1}{2})\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2$	$=$	$ax_2\hat{x} - ax_2\hat{y} - a(x_2 - \frac{1}{2})\hat{z}$	(16c)	Bi I
\mathbf{B}_{11}	$= (2x_2 + \frac{1}{2})\mathbf{a}_1 + (2x_2 + \frac{1}{2})\mathbf{a}_2 + (2x_2 + \frac{1}{2})\mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{4})\hat{x} + a(x_2 + \frac{1}{4})\hat{y} + a(x_2 + \frac{1}{4})\hat{z}$	(16c)	Bi I
\mathbf{B}_{12}	$= \frac{1}{2}\mathbf{a}_1 - 2x_2\mathbf{a}_3$	$=$	$-a(x_2 + \frac{1}{4})\hat{x} - a(x_2 - \frac{1}{4})\hat{y} + a(x_2 + \frac{1}{4})\hat{z}$	(16c)	Bi I
\mathbf{B}_{13}	$= -2x_2\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2$	$=$	$a(x_2 + \frac{1}{4})\hat{x} - a(x_2 + \frac{1}{4})\hat{y} - a(x_2 - \frac{1}{4})\hat{z}$	(16c)	Bi I
\mathbf{B}_{14}	$= -2x_2\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{4})\hat{x} + a(x_2 + \frac{1}{4})\hat{y} - a(x_2 + \frac{1}{4})\hat{z}$	(16c)	Bi I
\mathbf{B}_{15}	$= (y_3 + z_3)\mathbf{a}_1 + (x_3 + z_3)\mathbf{a}_2 + (x_3 + y_3)\mathbf{a}_3$	$=$	$ax_3\hat{x} + ay_3\hat{y} + az_3\hat{z}$	(48e)	O I
\mathbf{B}_{16}	$= (-y_3 + z_3 + \frac{1}{2})\mathbf{a}_1 - (x_3 - z_3)\mathbf{a}_2 - (x_3 + y_3 - \frac{1}{2})\mathbf{a}_3$	$=$	$-ax_3\hat{x} - a(y_3 - \frac{1}{2})\hat{y} + az_3\hat{z}$	(48e)	O I
\mathbf{B}_{17}	$= (y_3 - z_3)\mathbf{a}_1 - (x_3 + z_3 - \frac{1}{2})\mathbf{a}_2 + (-x_3 + y_3 + \frac{1}{2})\mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2})\hat{x} + ay_3\hat{y} - az_3\hat{z}$	(48e)	O I
\mathbf{B}_{18}	$= -(y_3 + z_3 - \frac{1}{2})\mathbf{a}_1 + (x_3 - z_3 + \frac{1}{2})\mathbf{a}_2 + (x_3 - y_3)\mathbf{a}_3$	$=$	$ax_3\hat{x} - ay_3\hat{y} - a(z_3 - \frac{1}{2})\hat{z}$	(48e)	O I
\mathbf{B}_{19}	$= (x_3 + y_3)\mathbf{a}_1 + (y_3 + z_3)\mathbf{a}_2 + (x_3 + z_3)\mathbf{a}_3$	$=$	$az_3\hat{x} + ax_3\hat{y} + ay_3\hat{z}$	(48e)	O I

$$\begin{aligned}
\mathbf{B}_{20} &= \begin{matrix} -\left(x_3 + y_3 - \frac{1}{2}\right) \mathbf{a}_1 + \\ \left(-y_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_2 - (x_3 - z_3) \mathbf{a}_3 \end{matrix} &= & az_3 \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} - a\left(y_3 - \frac{1}{2}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{21} &= \begin{matrix} \left(-x_3 + y_3 + \frac{1}{2}\right) \mathbf{a}_1 + \\ (y_3 - z_3) \mathbf{a}_2 - \left(x_3 + z_3 - \frac{1}{2}\right) \mathbf{a}_3 \end{matrix} &= & -az_3 \hat{\mathbf{x}} - a\left(x_3 - \frac{1}{2}\right) \hat{\mathbf{y}} + ay_3 \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{22} &= \begin{matrix} (x_3 - y_3) \mathbf{a}_1 - \left(y_3 + z_3 - \frac{1}{2}\right) \mathbf{a}_2 + \\ \left(x_3 - z_3 + \frac{1}{2}\right) \mathbf{a}_3 \end{matrix} &= & -a\left(z_3 - \frac{1}{2}\right) \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} - ay_3 \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{23} &= \begin{matrix} (x_3 + z_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + \\ (y_3 + z_3) \mathbf{a}_3 \end{matrix} &= & ay_3 \hat{\mathbf{x}} + az_3 \hat{\mathbf{y}} + ax_3 \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{24} &= \begin{matrix} -\left(x_3 - z_3\right) \mathbf{a}_1 - \\ \left(x_3 + y_3 - \frac{1}{2}\right) \mathbf{a}_2 + \\ \left(-y_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_3 \end{matrix} &= & -a\left(y_3 - \frac{1}{2}\right) \hat{\mathbf{x}} + az_3 \hat{\mathbf{y}} - ax_3 \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{25} &= \begin{matrix} -\left(x_3 + z_3 - \frac{1}{2}\right) \mathbf{a}_1 + \\ \left(-x_3 + y_3 + \frac{1}{2}\right) \mathbf{a}_2 + (y_3 - z_3) \mathbf{a}_3 \end{matrix} &= & ay_3 \hat{\mathbf{x}} - az_3 \hat{\mathbf{y}} - a\left(x_3 - \frac{1}{2}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{26} &= \begin{matrix} \left(x_3 - z_3 + \frac{1}{2}\right) \mathbf{a}_1 + \\ (x_3 - y_3) \mathbf{a}_2 - \left(y_3 + z_3 - \frac{1}{2}\right) \mathbf{a}_3 \end{matrix} &= & -ay_3 \hat{\mathbf{x}} - a\left(z_3 - \frac{1}{2}\right) \hat{\mathbf{y}} + ax_3 \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{27} &= \begin{matrix} \left(x_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_1 + \\ \left(y_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_2 + \\ \left(x_3 + y_3 + \frac{1}{2}\right) \mathbf{a}_3 \end{matrix} &= & a\left(y_3 + \frac{1}{4}\right) \hat{\mathbf{x}} + a\left(x_3 + \frac{1}{4}\right) \hat{\mathbf{y}} + a\left(z_3 + \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{28} &= \begin{matrix} \left(-x_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_1 - \\ (y_3 - z_3) \mathbf{a}_2 - (x_3 + y_3) \mathbf{a}_3 \end{matrix} &= & -a\left(y_3 + \frac{1}{4}\right) \hat{\mathbf{x}} - a\left(x_3 - \frac{1}{4}\right) \hat{\mathbf{y}} + a\left(z_3 + \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{29} &= \begin{matrix} -\left(x_3 + z_3\right) \mathbf{a}_1 + \\ \left(y_3 - z_3 + \frac{1}{2}\right) \mathbf{a}_2 - (x_3 - y_3) \mathbf{a}_3 \end{matrix} &= & a\left(y_3 + \frac{1}{4}\right) \hat{\mathbf{x}} - a\left(x_3 + \frac{1}{4}\right) \hat{\mathbf{y}} - a\left(z_3 - \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{30} &= \begin{matrix} (x_3 - z_3) \mathbf{a}_1 - (y_3 + z_3) \mathbf{a}_2 + \\ \left(x_3 - y_3 + \frac{1}{2}\right) \mathbf{a}_3 \end{matrix} &= & -a\left(y_3 - \frac{1}{4}\right) \hat{\mathbf{x}} + a\left(x_3 + \frac{1}{4}\right) \hat{\mathbf{y}} - a\left(z_3 + \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{31} &= \begin{matrix} \left(y_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_1 + \\ \left(x_3 + y_3 + \frac{1}{2}\right) \mathbf{a}_2 + \\ \left(x_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_3 \end{matrix} &= & a\left(x_3 + \frac{1}{4}\right) \hat{\mathbf{x}} + a\left(z_3 + \frac{1}{4}\right) \hat{\mathbf{y}} + a\left(y_3 + \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{32} &= \begin{matrix} -(y_3 - z_3) \mathbf{a}_1 - (x_3 + y_3) \mathbf{a}_2 + \\ \left(-x_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_3 \end{matrix} &= & -a\left(x_3 - \frac{1}{4}\right) \hat{\mathbf{x}} + a\left(z_3 + \frac{1}{4}\right) \hat{\mathbf{y}} - a\left(y_3 + \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{33} &= \begin{matrix} \left(y_3 - z_3 + \frac{1}{2}\right) \mathbf{a}_1 - \\ (x_3 - y_3) \mathbf{a}_2 - (x_3 + z_3) \mathbf{a}_3 \end{matrix} &= & -a\left(x_3 + \frac{1}{4}\right) \hat{\mathbf{x}} - a\left(z_3 - \frac{1}{4}\right) \hat{\mathbf{y}} + a\left(y_3 + \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{34} &= \begin{matrix} -(y_3 + z_3) \mathbf{a}_1 + \\ \left(x_3 - y_3 + \frac{1}{2}\right) \mathbf{a}_2 + (x_3 - z_3) \mathbf{a}_3 \end{matrix} &= & a\left(x_3 + \frac{1}{4}\right) \hat{\mathbf{x}} - a\left(z_3 + \frac{1}{4}\right) \hat{\mathbf{y}} - a\left(y_3 - \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{35} &= \begin{matrix} \left(x_3 + y_3 + \frac{1}{2}\right) \mathbf{a}_1 + \\ \left(x_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_2 + \\ \left(y_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_3 \end{matrix} &= & a\left(z_3 + \frac{1}{4}\right) \hat{\mathbf{x}} + a\left(y_3 + \frac{1}{4}\right) \hat{\mathbf{y}} + a\left(x_3 + \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{36} &= \begin{matrix} -(x_3 + y_3) \mathbf{a}_1 + \\ \left(-x_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_2 - (y_3 - z_3) \mathbf{a}_3 \end{matrix} &= & a\left(z_3 + \frac{1}{4}\right) \hat{\mathbf{x}} - a\left(y_3 + \frac{1}{4}\right) \hat{\mathbf{y}} - a\left(x_3 - \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{37} &= \begin{matrix} -(x_3 - y_3) \mathbf{a}_1 - (x_3 + z_3) \mathbf{a}_2 + \\ \left(y_3 - z_3 + \frac{1}{2}\right) \mathbf{a}_3 \end{matrix} &= & -a\left(z_3 - \frac{1}{4}\right) \hat{\mathbf{x}} + a\left(y_3 + \frac{1}{4}\right) \hat{\mathbf{y}} - a\left(x_3 + \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I} \\
\mathbf{B}_{38} &= \begin{matrix} \left(x_3 - y_3 + \frac{1}{2}\right) \mathbf{a}_1 + \\ (x_3 - z_3) \mathbf{a}_2 - (y_3 + z_3) \mathbf{a}_3 \end{matrix} &= & -a\left(z_3 + \frac{1}{4}\right) \hat{\mathbf{x}} - a\left(y_3 - \frac{1}{4}\right) \hat{\mathbf{y}} + a\left(x_3 + \frac{1}{4}\right) \hat{\mathbf{z}} & (48e) & \text{O I}
\end{aligned}$$

References

- [1] H. Liu and C. Kuo, *Crystal structure of bismuth(III) silicate, Bi_4SiO_4* , Z. Kristallogr. **212**, 48 (1997), doi:10.1524/zkri.1997.212.1.48.

Found in

- [1] R. T. Downs and M. Hall-Wallace, *The American Mineralogist Crystal Structure Database*, Am. Mineral. **88**, 247–250 (2003).