


SiF₄ (*D*₁₂) Structure: A4B_cI10_217_c_a-001

This structure originally had the label A4B_cI10_217_c_a. Calls to that address will be redirected here.

Cite this page as: M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017

<https://aflow.org/p/WBME>

https://aflow.org/p/A4B_cI10_217_c_a-001

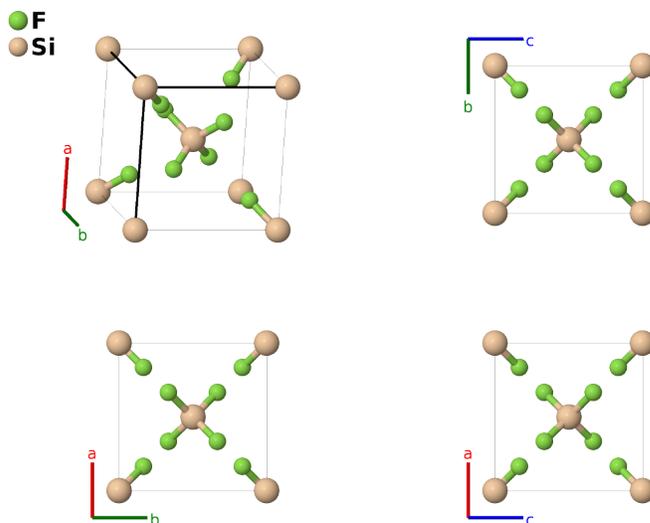


Prototype	F ₄ Si
AFLOW prototype label	A4B_cI10_217_c_a-001
<i>Strukturbericht</i> designation	<i>D</i> ₁₂
ICSD	14122
Pearson symbol	cI10
Space group number	217
Space group symbol	<i>I</i> $\bar{4}3m$
AFLOW prototype command	<code>aflow --proto=A4B_cI10_217_c_a-001 --params=a, x₂</code>

- We determined the lattice constant for this structure from the internal coordinates and the Si-F bond length given in (Atoji, 1954).

Body-centered Cubic primitive vectors

a3
a2
a1

$$\begin{aligned} \mathbf{a}_1 &= -\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}a \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}a \hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} - \frac{1}{2}a \hat{\mathbf{z}} \end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	=	0	=	0	(2a) Si I
\mathbf{B}_2	=	$2x_2 \mathbf{a}_1 + 2x_2 \mathbf{a}_2 + 2x_2 \mathbf{a}_3$	=	$ax_2 \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}} + ax_2 \hat{\mathbf{z}}$	(8c) F I
\mathbf{B}_3	=	$-2x_2 \mathbf{a}_3$	=	$-ax_2 \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}} + ax_2 \hat{\mathbf{z}}$	(8c) F I
\mathbf{B}_4	=	$-2x_2 \mathbf{a}_2$	=	$-ax_2 \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}} - ax_2 \hat{\mathbf{z}}$	(8c) F I
\mathbf{B}_5	=	$-2x_2 \mathbf{a}_1$	=	$ax_2 \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}} - ax_2 \hat{\mathbf{z}}$	(8c) F I

References

- [1] M. Atoji and W. N. Lipscomb, *The structure of SiF₄*, Acta Cryst. **7**, 597 (1954), doi:10.1107/S0365110X5400196X.