


Stoiberite [Cu₅O₂(VO₄)₂] Structure: A5B10C2_mP68_14_5e_10e_2e-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/S3GM>

https://aflow.org/prototype-encyclopedia/A5B10C2_mP68_14_5e_10e_2e-001

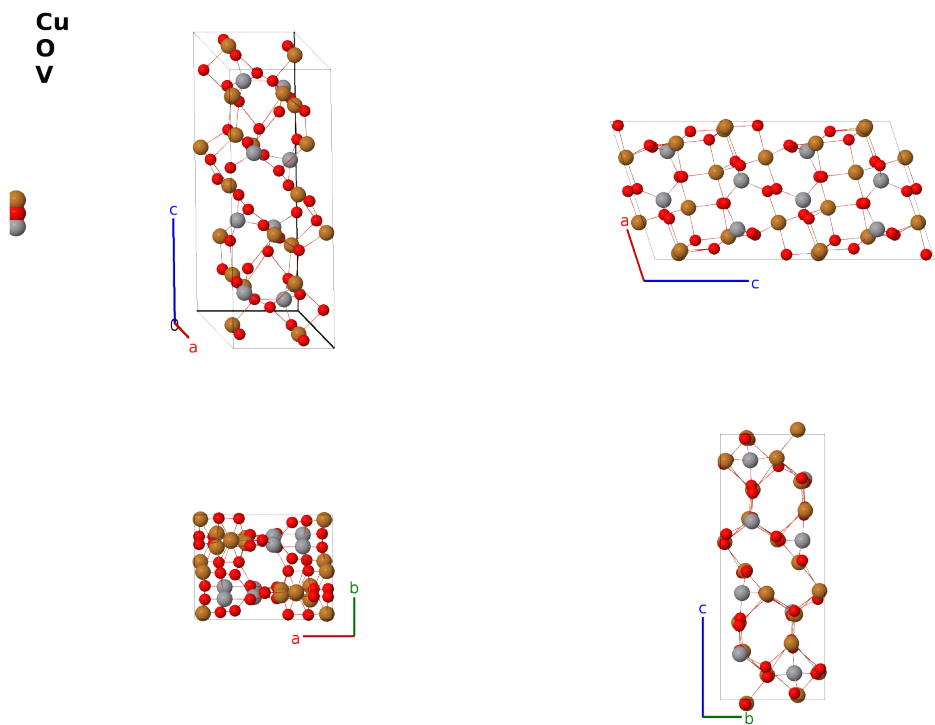


Prototype	Cu ₅ O ₁₀ V ₂
AFLOW prototype label	A5B10C2_mP68_14_5e_10e_2e-001
Mineral name	stoiberite
ICSD	2557
CCDC	1592433
Pearson symbol	mP68
Space group number	14
Space group symbol	$P2_1/c$
AFLOW prototype command	<pre>aflow --proto=A5B10C2_mP68_14_5e_10e_2e-001 --params=a,b/a,c/a,β,x₁,y₁,z₁,x₂,y₂,z₂,x₃,y₃,z₃,x₄,y₄,z₄,x₅,y₅,z₅,x₆,y₆,z₆,x₇, y₇,z₇,x₈,y₈,z₈,x₉,y₉,z₉,x₁₀,y₁₀,z₁₀,x₁₁,y₁₁,z₁₁,x₁₂,y₁₂,z₁₂,x₁₃,y₁₃,z₁₃,x₁₄,y₁₄,z₁₄,x₁₅, y₁₅,z₁₅,x₁₆,y₁₆,z₁₆,x₁₇,y₁₇,z₁₇</pre>

- Stoiberite is related to averievite, and similar structures (Botana 2018; Korniyakov, 2021) are often referred to as averievite. All consist of arrays of VO_4 tetraheda connected by copper and oxygen, and many structures include additional elements. We have collected an number of these structures, towit:

- Stoiberite, $\text{Cu}_5(\text{VO}_4)_2$ (this structure),
- $(\text{ClCu})_2\text{Cu}_5\text{O}_2(\text{VO}_4)_2$,
- $\text{Cu}_5\text{O}_2(\text{VO}_4)_2 \cdot \text{CuCl}_2$,
- $(\text{CsCl})\text{Cu}_5\text{O}_2(\text{PO}_4)_2$,
- Monoclinic $(\text{CsCl})\text{Cu}_5\text{O}_2(\text{VO}_4)_2$,
- Trigonal $(\text{CsCl})\text{Cu}_5\text{O}_2(\text{VO}_4)_2$, and
- $(\text{KBr})\text{Cu}_5\text{O}_2(\text{VO}_4)_2$.

Simple Monoclinic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}} \end{aligned}$$

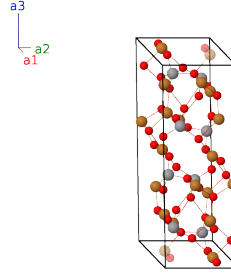

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$x_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	=	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu I
$\mathbf{B}_2$	$-x_1 \mathbf{a}_1 + (y_1 + \frac{1}{2}) \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_1 + c(z_1 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_1 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu I
$\mathbf{B}_3$	$-x_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	=	$-(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} - cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu I
$\mathbf{B}_4$	$x_1 \mathbf{a}_1 - (y_1 - \frac{1}{2}) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_1 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu I
$\mathbf{B}_5$	$x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu II
$\mathbf{B}_6$	$-x_2 \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_2 + c(z_2 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu II
$\mathbf{B}_7$	$-x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu II
$\mathbf{B}_8$	$x_2 \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu II
$\mathbf{B}_9$	$x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu III
$\mathbf{B}_{10}$	$-x_3 \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu III
$\mathbf{B}_{11}$	$-x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu III
$\mathbf{B}_{12}$	$x_3 \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu III
$\mathbf{B}_{13}$	$x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu IV

$\mathbf{B}_{14} =$	$-x_4 \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_4 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu IV
$\mathbf{B}_{15} =$	$-x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu IV
$\mathbf{B}_{16} =$	$x_4 \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_4 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu IV
$\mathbf{B}_{17} =$	$x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu V
$\mathbf{B}_{18} =$	$-x_5 \mathbf{a}_1 + (y_5 + \frac{1}{2}) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_5 + c(z_5 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_5 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu V
$\mathbf{B}_{19} =$	$-x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu V
$\mathbf{B}_{20} =$	$x_5 \mathbf{a}_1 - (y_5 - \frac{1}{2}) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_5 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu V
$\mathbf{B}_{21} =$	$x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(4e)	O I
$\mathbf{B}_{22} =$	$-x_6 \mathbf{a}_1 + (y_6 + \frac{1}{2}) \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_6 + c(z_6 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_6 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O I
$\mathbf{B}_{23} =$	$-x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \sin \beta \hat{\mathbf{z}}$	(4e)	O I
$\mathbf{B}_{24} =$	$x_6 \mathbf{a}_1 - (y_6 - \frac{1}{2}) \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_6 + c(z_6 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_6 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O I
$\mathbf{B}_{25} =$	$x_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$	$=$	$(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \sin \beta \hat{\mathbf{z}}$	(4e)	O II
$\mathbf{B}_{26} =$	$-x_7 \mathbf{a}_1 + (y_7 + \frac{1}{2}) \mathbf{a}_2 - (z_7 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_7 + c(z_7 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_7 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O II
$\mathbf{B}_{27} =$	$-x_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$	$=$	$-(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} - cz_7 \sin \beta \hat{\mathbf{z}}$	(4e)	O II
$\mathbf{B}_{28} =$	$x_7 \mathbf{a}_1 - (y_7 - \frac{1}{2}) \mathbf{a}_2 + (z_7 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_7 + c(z_7 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_7 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O II
$\mathbf{B}_{29} =$	$x_8 \mathbf{a}_1 + y_8 \mathbf{a}_2 + z_8 \mathbf{a}_3$	$=$	$(ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} + cz_8 \sin \beta \hat{\mathbf{z}}$	(4e)	O III
$\mathbf{B}_{30} =$	$-x_8 \mathbf{a}_1 + (y_8 + \frac{1}{2}) \mathbf{a}_2 - (z_8 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_8 + c(z_8 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_8 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_8 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O III
$\mathbf{B}_{31} =$	$-x_8 \mathbf{a}_1 - y_8 \mathbf{a}_2 - z_8 \mathbf{a}_3$	$=$	$-(ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} - cz_8 \sin \beta \hat{\mathbf{z}}$	(4e)	O III
$\mathbf{B}_{32} =$	$x_8 \mathbf{a}_1 - (y_8 - \frac{1}{2}) \mathbf{a}_2 + (z_8 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_8 + c(z_8 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_8 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_8 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O III
$\mathbf{B}_{33} =$	$x_9 \mathbf{a}_1 + y_9 \mathbf{a}_2 + z_9 \mathbf{a}_3$	$=$	$(ax_9 + cz_9 \cos \beta) \hat{\mathbf{x}} + by_9 \hat{\mathbf{y}} + cz_9 \sin \beta \hat{\mathbf{z}}$	(4e)	O IV
$\mathbf{B}_{34} =$	$-x_9 \mathbf{a}_1 + (y_9 + \frac{1}{2}) \mathbf{a}_2 - (z_9 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_9 + c(z_9 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_9 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_9 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O IV
$\mathbf{B}_{35} =$	$-x_9 \mathbf{a}_1 - y_9 \mathbf{a}_2 - z_9 \mathbf{a}_3$	$=$	$-(ax_9 + cz_9 \cos \beta) \hat{\mathbf{x}} - by_9 \hat{\mathbf{y}} - cz_9 \sin \beta \hat{\mathbf{z}}$	(4e)	O IV
$\mathbf{B}_{36} =$	$x_9 \mathbf{a}_1 - (y_9 - \frac{1}{2}) \mathbf{a}_2 + (z_9 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_9 + c(z_9 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_9 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_9 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O IV
$\mathbf{B}_{37} =$	$x_{10} \mathbf{a}_1 + y_{10} \mathbf{a}_2 + z_{10} \mathbf{a}_3$	$=$	$(ax_{10} + cz_{10} \cos \beta) \hat{\mathbf{x}} + by_{10} \hat{\mathbf{y}} + cz_{10} \sin \beta \hat{\mathbf{z}}$	(4e)	O V
$\mathbf{B}_{38} =$	$-x_{10} \mathbf{a}_1 + (y_{10} + \frac{1}{2}) \mathbf{a}_2 - (z_{10} - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_{10} + c(z_{10} - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_{10} + \frac{1}{2}) \hat{\mathbf{y}} - c(z_{10} - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O V
$\mathbf{B}_{39} =$	$-x_{10} \mathbf{a}_1 - y_{10} \mathbf{a}_2 - z_{10} \mathbf{a}_3$	$=$	$-(ax_{10} + cz_{10} \cos \beta) \hat{\mathbf{x}} - by_{10} \hat{\mathbf{y}} - cz_{10} \sin \beta \hat{\mathbf{z}}$	(4e)	O V
$\mathbf{B}_{40} =$	$x_{10} \mathbf{a}_1 - (y_{10} - \frac{1}{2}) \mathbf{a}_2 + (z_{10} + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_{10} + c(z_{10} + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_{10} - \frac{1}{2}) \hat{\mathbf{y}} + c(z_{10} + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O V
$\mathbf{B}_{41} =$	$x_{11} \mathbf{a}_1 + y_{11} \mathbf{a}_2 + z_{11} \mathbf{a}_3$	$=$	$(ax_{11} + cz_{11} \cos \beta) \hat{\mathbf{x}} + by_{11} \hat{\mathbf{y}} + cz_{11} \sin \beta \hat{\mathbf{z}}$	(4e)	O VI
$\mathbf{B}_{42} =$	$-x_{11} \mathbf{a}_1 + (y_{11} + \frac{1}{2}) \mathbf{a}_2 - (z_{11} - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_{11} + c(z_{11} - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_{11} + \frac{1}{2}) \hat{\mathbf{y}} - c(z_{11} - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O VI

References

- [1] R. D. Shannon and C. Calvo, *Crystal structure of $Cu_5V_2O_{10}$* , Acta Crystallogr. Sect. B **29**, 1338–1345 (1973), doi:10.1107/S0567740873004474.
- [2] A. S. Botana, H. Zheng, S. H. Lapidus, J. F. Mitchell, and M. R. Norman, *Averievite: A copper oxide kagome antiferromagnet*, Phys. Rev. B **98**, August (2018), doi:10.1103/PhysRevB.98.054421.
- [3] I. V. Korniyakov, V. A. Vladimirova, O. I. Siidra, and S. V. Krivovichev, *Expanding the Averievite Family, $(MX)Cu_5O_2(T^{5+}O_4)_2$ ($T^{5+} = P, V$; $M = K, Rb, Cs, Cu$; $X = Cl, Br$): Synthesis and Single-Crystal X-ray Diffraction Study*, Molecules **26**, 1833 (2021), doi:10.3390/molecules26071833.

First cited in

N. Anderson, M. J. Mehl, H. Eckert, S. Divilov, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 5*. Submitted to Computational Materials Science (2026).