

Ce₅Co₁₉ Structure:

A5B19_hR24_166_a2c_b3c2h-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/3D07>

https://aflow.org/prototype-encyclopedia/A5B19_hR24_166_a2c_b3c2h-001

Prototype	Ce ₅ Co ₁₉
AFLOW prototype label	A5B19_hR24_166_a2c_b3c2h-001
ICSD	620646
CCDC	1748866
Pearson symbol	hR24
Space group number	166
Space group symbol	$R\bar{3}m$
AFLOW prototype command	<code>aflow --proto=A5B19_hR24_166_a2c_b3c2h-001</code> <code>--params=a, c/a, x₃, x₄, x₅, x₆, x₇, x₈, z₈, x₉, z₉</code>


Other compounds with this structure

Ce₅Co₁₉, La₅Co₁₉, Nd₅Co₁₉, Nd₅Ni₁₉, Pr₅Co₁₉, Pr₅Ni₁₉, Sm₅Co₁₉, Y₅Co₁₉

- This is the binary version of the Ce₅Ga₇Rh₁₂ structure.






Rhombohedral primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + \frac{1}{3}c\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{\sqrt{3}}a\hat{\mathbf{y}} + \frac{1}{3}c\hat{\mathbf{z}} \\ \mathbf{a}_3 &= -\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + \frac{1}{3}c\hat{\mathbf{z}}\end{aligned}$$



Basis vectors

Ce
Co

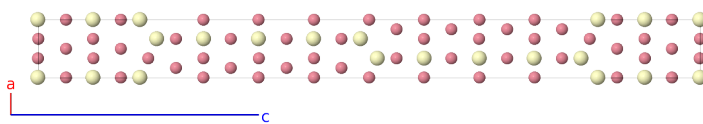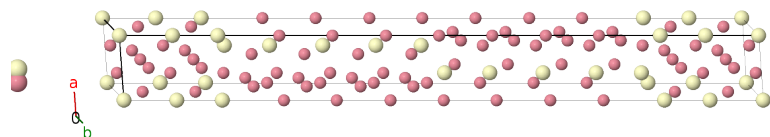

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	(1a) Ce I
$\mathbf{B}_2$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} c \hat{\mathbf{z}}$	(1b) Co I
$\mathbf{B}_3$	$=$	$x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$cx_3 \hat{\mathbf{z}}$	(2c) Ce II
$\mathbf{B}_4$	$=$	$-x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - x_3 \mathbf{a}_3$	$=$	$-cx_3 \hat{\mathbf{z}}$	(2c) Ce II
$\mathbf{B}_5$	$=$	$x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$	$=$	$cx_4 \hat{\mathbf{z}}$	(2c) Ce III
$\mathbf{B}_6$	$=$	$-x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$	$=$	$-cx_4 \hat{\mathbf{z}}$	(2c) Ce III
$\mathbf{B}_7$	$=$	$x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + x_5 \mathbf{a}_3$	$=$	$cx_5 \hat{\mathbf{z}}$	(2c) Co II
$\mathbf{B}_8$	$=$	$-x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - x_5 \mathbf{a}_3$	$=$	$-cx_5 \hat{\mathbf{z}}$	(2c) Co II
$\mathbf{B}_9$	$=$	$x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 + x_6 \mathbf{a}_3$	$=$	$cx_6 \hat{\mathbf{z}}$	(2c) Co III
$\mathbf{B}_{10}$	$=$	$-x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 - x_6 \mathbf{a}_3$	$=$	$-cx_6 \hat{\mathbf{z}}$	(2c) Co III
$\mathbf{B}_{11}$	$=$	$x_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 + x_7 \mathbf{a}_3$	$=$	$cx_7 \hat{\mathbf{z}}$	(2c) Co IV
$\mathbf{B}_{12}$	$=$	$-x_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - x_7 \mathbf{a}_3$	$=$	$-cx_7 \hat{\mathbf{z}}$	(2c) Co IV
$\mathbf{B}_{13}$	$=$	$x_8 \mathbf{a}_1 + x_8 \mathbf{a}_2 + z_8 \mathbf{a}_3$	$=$	$\frac{1}{2} a (x_8 - z_8) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a (x_8 - z_8) \hat{\mathbf{y}} + \frac{1}{3} c (2x_8 + z_8) \hat{\mathbf{z}}$	(6h) Co V
$\mathbf{B}_{14}$	$=$	$z_8 \mathbf{a}_1 + x_8 \mathbf{a}_2 + x_8 \mathbf{a}_3$	$=$	$-\frac{1}{2} a (x_8 - z_8) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a (x_8 - z_8) \hat{\mathbf{y}} + \frac{1}{3} c (2x_8 + z_8) \hat{\mathbf{z}}$	(6h) Co V
$\mathbf{B}_{15}$	$=$	$x_8 \mathbf{a}_1 + z_8 \mathbf{a}_2 + x_8 \mathbf{a}_3$	$=$	$-\frac{1}{\sqrt{3}} a (x_8 - z_8) \hat{\mathbf{y}} + \frac{1}{3} c (2x_8 + z_8) \hat{\mathbf{z}}$	(6h) Co V
$\mathbf{B}_{16}$	$=$	$-z_8 \mathbf{a}_1 - x_8 \mathbf{a}_2 - x_8 \mathbf{a}_3$	$=$	$\frac{1}{2} a (x_8 - z_8) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a (x_8 - z_8) \hat{\mathbf{y}} - \frac{1}{3} c (2x_8 + z_8) \hat{\mathbf{z}}$	(6h) Co V
$\mathbf{B}_{17}$	$=$	$-x_8 \mathbf{a}_1 - x_8 \mathbf{a}_2 - z_8 \mathbf{a}_3$	$=$	$-\frac{1}{2} a (x_8 - z_8) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a (x_8 - z_8) \hat{\mathbf{y}} - \frac{1}{3} c (2x_8 + z_8) \hat{\mathbf{z}}$	(6h) Co V
$\mathbf{B}_{18}$	$=$	$-x_8 \mathbf{a}_1 - z_8 \mathbf{a}_2 - x_8 \mathbf{a}_3$	$=$	$\frac{1}{\sqrt{3}} a (x_8 - z_8) \hat{\mathbf{y}} - \frac{1}{3} c (2x_8 + z_8) \hat{\mathbf{z}}$	(6h) Co V
$\mathbf{B}_{19}$	$=$	$x_9 \mathbf{a}_1 + x_9 \mathbf{a}_2 + z_9 \mathbf{a}_3$	$=$	$\frac{1}{2} a (x_9 - z_9) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a (x_9 - z_9) \hat{\mathbf{y}} + \frac{1}{3} c (2x_9 + z_9) \hat{\mathbf{z}}$	(6h) Co VI
$\mathbf{B}_{20}$	$=$	$z_9 \mathbf{a}_1 + x_9 \mathbf{a}_2 + x_9 \mathbf{a}_3$	$=$	$-\frac{1}{2} a (x_9 - z_9) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a (x_9 - z_9) \hat{\mathbf{y}} + \frac{1}{3} c (2x_9 + z_9) \hat{\mathbf{z}}$	(6h) Co VI
$\mathbf{B}_{21}$	$=$	$x_9 \mathbf{a}_1 + z_9 \mathbf{a}_2 + x_9 \mathbf{a}_3$	$=$	$-\frac{1}{\sqrt{3}} a (x_9 - z_9) \hat{\mathbf{y}} + \frac{1}{3} c (2x_9 + z_9) \hat{\mathbf{z}}$	(6h) Co VI
$\mathbf{B}_{22}$	$=$	$-z_9 \mathbf{a}_1 - x_9 \mathbf{a}_2 - x_9 \mathbf{a}_3$	$=$	$\frac{1}{2} a (x_9 - z_9) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a (x_9 - z_9) \hat{\mathbf{y}} - \frac{1}{3} c (2x_9 + z_9) \hat{\mathbf{z}}$	(6h) Co VI
$\mathbf{B}_{23}$	$=$	$-x_9 \mathbf{a}_1 - x_9 \mathbf{a}_2 - z_9 \mathbf{a}_3$	$=$	$-\frac{1}{2} a (x_9 - z_9) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a (x_9 - z_9) \hat{\mathbf{y}} - \frac{1}{3} c (2x_9 + z_9) \hat{\mathbf{z}}$	(6h) Co VI
$\mathbf{B}_{24}$	$=$	$-x_9 \mathbf{a}_1 - z_9 \mathbf{a}_2 - x_9 \mathbf{a}_3$	$=$	$\frac{1}{\sqrt{3}} a (x_9 - z_9) \hat{\mathbf{y}} - \frac{1}{3} c (2x_9 + z_9) \hat{\mathbf{z}}$	(6h) Co VI

References

- [1] A. E. Ray, A. T. Biermann, R. S. Harmer, and J. E. Davison, *Ueberpruefung der Zustandsschaubilder der binaeren Systeme Cer-Kobalt, Praseodym-Kobalt und Neodym-Kobalt*, Kobalt **4**, 90–93 (1973).

Found in

- [1] Y. Khan, *The crystal structure of $R_5\text{Co}_{19}$* , Acta Crystallogr. Sect. B **30**, 1533–1537 (1974), doi:10.1107/S0567740874005206.

First cited in

N. Anderson, M. J. Mehl, H. Eckert, S. Divilov, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 5*. Submitted to Computational Materials Science (2026).