


Ordoñezite (ZnSb_2O_6) Structure: A6B2C_tP18_136_fj_e_a-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/8DHD>

https://aflow.org/p/A6B2C_tP18_136_fj_e_a-001

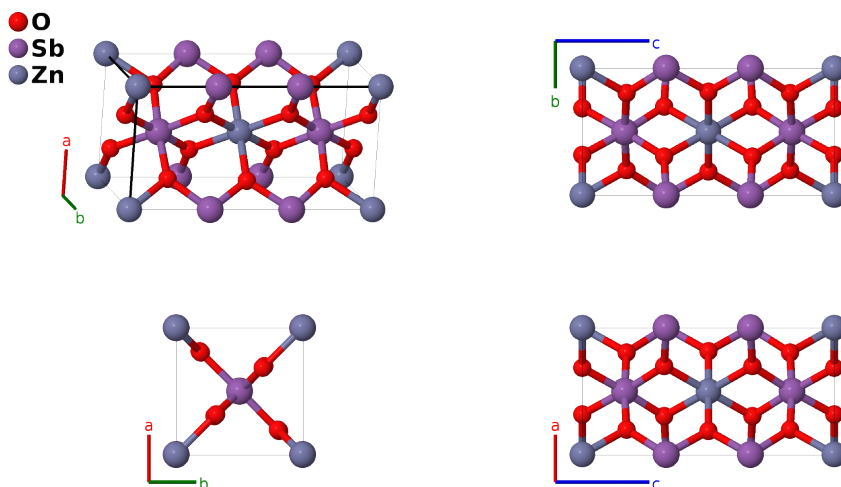

Prototype	$\text{O}_6\text{Sb}_2\text{Zn}$
AFLOW prototype label	A6B2C_tP18_136_fj_e_a-001
Mineral name	ordonezite
ICSD	96612
Pearson symbol	tP18
Space group number	136
Space group symbol	$P4_2/mnm$
AFLOW prototype command	<code>aflow --proto=A6B2C_tP18_136_fj_e_a-001 --params=a, c/a, z2, x3, x4, z4</code>

Other compounds with this structure

FeTa_2O_6 , RhLi_2F_6 , TiLi_2F_6


- The actual composition of the experimentally measured sample is $(\text{Zn}_{0.98}\text{Fe}_{0.02})\text{Sb}_2\text{O}_6$.

Simple Tetragonal primitive vectors

$$\mathbf{a}_1 = a \hat{x}$$

$$\mathbf{a}_2 = a \hat{y}$$

$$\mathbf{a}_3 = c \hat{z}$$

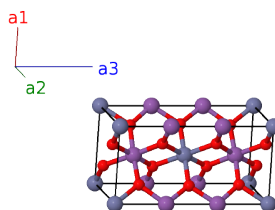

Basis vectors

	Lattice coordinates	=	Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	= 0	=	0	(2a)	Zn I
\mathbf{B}_2	= $\frac{1}{2}\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}}$	(2a)	Zn I
\mathbf{B}_3	= $z_2\mathbf{a}_3$	=	$cz_2\hat{\mathbf{z}}$	(4e)	Sb I
\mathbf{B}_4	= $\frac{1}{2}\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2 + (z_2 + \frac{1}{2})\mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} + c(z_2 + \frac{1}{2})\hat{\mathbf{z}}$	(4e)	Sb I
\mathbf{B}_5	= $\frac{1}{2}\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2 - (z_2 - \frac{1}{2})\mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} - c(z_2 - \frac{1}{2})\hat{\mathbf{z}}$	(4e)	Sb I
\mathbf{B}_6	= $-z_2\mathbf{a}_3$	=	$-cz_2\hat{\mathbf{z}}$	(4e)	Sb I
\mathbf{B}_7	= $x_3\mathbf{a}_1 + x_3\mathbf{a}_2$	=	$ax_3\hat{\mathbf{x}} + ax_3\hat{\mathbf{y}}$	(4f)	O I
\mathbf{B}_8	= $-x_3\mathbf{a}_1 - x_3\mathbf{a}_2$	=	$-ax_3\hat{\mathbf{x}} - ax_3\hat{\mathbf{y}}$	(4f)	O I
\mathbf{B}_9	= $-(x_3 - \frac{1}{2})\mathbf{a}_1 + (x_3 + \frac{1}{2})\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	=	$-a(x_3 - \frac{1}{2})\hat{\mathbf{x}} + a(x_3 + \frac{1}{2})\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}}$	(4f)	O I
\mathbf{B}_{10}	= $(x_3 + \frac{1}{2})\mathbf{a}_1 - (x_3 - \frac{1}{2})\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	=	$a(x_3 + \frac{1}{2})\hat{\mathbf{x}} - a(x_3 - \frac{1}{2})\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}}$	(4f)	O I
\mathbf{B}_{11}	= $x_4\mathbf{a}_1 + x_4\mathbf{a}_2 + z_4\mathbf{a}_3$	=	$ax_4\hat{\mathbf{x}} + ax_4\hat{\mathbf{y}} + cz_4\hat{\mathbf{z}}$	(8j)	O II
\mathbf{B}_{12}	= $-x_4\mathbf{a}_1 - x_4\mathbf{a}_2 + z_4\mathbf{a}_3$	=	$-ax_4\hat{\mathbf{x}} - ax_4\hat{\mathbf{y}} + cz_4\hat{\mathbf{z}}$	(8j)	O II
\mathbf{B}_{13}	= $-(x_4 - \frac{1}{2})\mathbf{a}_1 + (x_4 + \frac{1}{2})\mathbf{a}_2 + (z_4 + \frac{1}{2})\mathbf{a}_3$	=	$-a(x_4 - \frac{1}{2})\hat{\mathbf{x}} + a(x_4 + \frac{1}{2})\hat{\mathbf{y}} + c(z_4 + \frac{1}{2})\hat{\mathbf{z}}$	(8j)	O II
\mathbf{B}_{14}	= $(x_4 + \frac{1}{2})\mathbf{a}_1 - (x_4 - \frac{1}{2})\mathbf{a}_2 + (z_4 + \frac{1}{2})\mathbf{a}_3$	=	$a(x_4 + \frac{1}{2})\hat{\mathbf{x}} - a(x_4 - \frac{1}{2})\hat{\mathbf{y}} + c(z_4 + \frac{1}{2})\hat{\mathbf{z}}$	(8j)	O II
\mathbf{B}_{15}	= $-(x_4 - \frac{1}{2})\mathbf{a}_1 + (x_4 + \frac{1}{2})\mathbf{a}_2 - (z_4 - \frac{1}{2})\mathbf{a}_3$	=	$-a(x_4 - \frac{1}{2})\hat{\mathbf{x}} + a(x_4 + \frac{1}{2})\hat{\mathbf{y}} - c(z_4 - \frac{1}{2})\hat{\mathbf{z}}$	(8j)	O II
\mathbf{B}_{16}	= $(x_4 + \frac{1}{2})\mathbf{a}_1 - (x_4 - \frac{1}{2})\mathbf{a}_2 - (z_4 - \frac{1}{2})\mathbf{a}_3$	=	$a(x_4 + \frac{1}{2})\hat{\mathbf{x}} - a(x_4 - \frac{1}{2})\hat{\mathbf{y}} - c(z_4 - \frac{1}{2})\hat{\mathbf{z}}$	(8j)	O II
\mathbf{B}_{17}	= $x_4\mathbf{a}_1 + x_4\mathbf{a}_2 - z_4\mathbf{a}_3$	=	$ax_4\hat{\mathbf{x}} + ax_4\hat{\mathbf{y}} - cz_4\hat{\mathbf{z}}$	(8j)	O II
\mathbf{B}_{18}	= $-x_4\mathbf{a}_1 - x_4\mathbf{a}_2 - z_4\mathbf{a}_3$	=	$-ax_4\hat{\mathbf{x}} - ax_4\hat{\mathbf{y}} - cz_4\hat{\mathbf{z}}$	(8j)	O II

References

- [1] T. S. Ercit, E. E. Foord, and J. J. Fitzpatrick, *Ordoñezite from the Theodoso Soto Mine, Sapioris, Durango, Mexico: New Data and Structure Refinement*, Can. Mineral. **40**, 1207–1210 (2002), doi:10.2113/gscanmin.40.4.1207.

Found in

- [1] R. T. Downs and M. Hall-Wallace, *The American Mineralogist Crystal Structure Database*, Am. Mineral. **88**, 247–250 (2003).