


Cd₈As₇Cl Structure: A7B12C_cP20_195_ag_3e_b-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/J7FX>

https://aflow.org/p/A7B12C_cP20_195_ag_3e_b-001

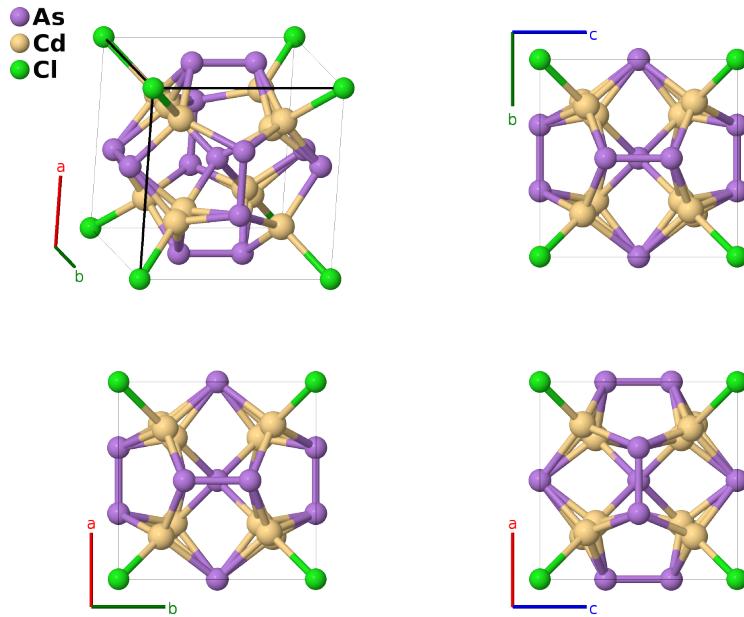


| | |
|--------------------------------|--|
| Prototype | As ₇ Cd ₈ Cl |
| AFLOW prototype label | A7B12C_cP20_195_ag_3e_b-001 |
| ICSD | 84983 |
| Pearson symbol | cP20 |
| Space group number | 195 |
| Space group symbol | <i>P</i> 23 |
| AFLOW prototype command | <code>aflow --proto=A7B12C_cP20_195_ag_3e_b-001 --params=<i>a</i>,<i>x</i>₃,<i>x</i>₄,<i>x</i>₅,<i>x</i>₆</code> |

- The paired Cd-II and Cd-III sites are never simultaneously occupied. The Cd-II site is filled 53.5% of the time, and Cd-III 46.5%. For approximate first-principles calculations one could average the two positions.

Simple Cubic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= a \hat{\mathbf{z}}\end{aligned}$$

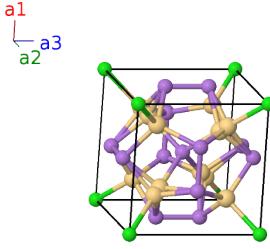

Basis vectors

| | Lattice coordinates | = | Cartesian coordinates | Wyckoff position | Atom type |
|-------------------|--|---|---|------------------|-----------|
| \mathbf{B}_1 | 0 | = | 0 | (1a) | As I |
| \mathbf{B}_2 | $\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$ | = | $\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}a \hat{\mathbf{z}}$ | (1b) | Cl I |
| \mathbf{B}_3 | $x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$ | = | $ax_3 \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} + ax_3 \hat{\mathbf{z}}$ | (4e) | Cd I |
| \mathbf{B}_4 | $-x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$ | = | $-ax_3 \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} + ax_3 \hat{\mathbf{z}}$ | (4e) | Cd I |
| \mathbf{B}_5 | $-x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 - x_3 \mathbf{a}_3$ | = | $-ax_3 \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} - ax_3 \hat{\mathbf{z}}$ | (4e) | Cd I |
| \mathbf{B}_6 | $x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - x_3 \mathbf{a}_3$ | = | $ax_3 \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} - ax_3 \hat{\mathbf{z}}$ | (4e) | Cd I |
| \mathbf{B}_7 | $x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$ | = | $ax_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} + ax_4 \hat{\mathbf{z}}$ | (4e) | Cd II |
| \mathbf{B}_8 | $-x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$ | = | $-ax_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} + ax_4 \hat{\mathbf{z}}$ | (4e) | Cd II |
| \mathbf{B}_9 | $-x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$ | = | $-ax_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} - ax_4 \hat{\mathbf{z}}$ | (4e) | Cd II |
| \mathbf{B}_{10} | $x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$ | = | $ax_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} - ax_4 \hat{\mathbf{z}}$ | (4e) | Cd II |
| \mathbf{B}_{11} | $x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + x_5 \mathbf{a}_3$ | = | $ax_5 \hat{\mathbf{x}} + ax_5 \hat{\mathbf{y}} + ax_5 \hat{\mathbf{z}}$ | (4e) | Cd III |
| \mathbf{B}_{12} | $-x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 + x_5 \mathbf{a}_3$ | = | $-ax_5 \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}} + ax_5 \hat{\mathbf{z}}$ | (4e) | Cd III |
| \mathbf{B}_{13} | $-x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 - x_5 \mathbf{a}_3$ | = | $-ax_5 \hat{\mathbf{x}} + ax_5 \hat{\mathbf{y}} - ax_5 \hat{\mathbf{z}}$ | (4e) | Cd III |
| \mathbf{B}_{14} | $x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - x_5 \mathbf{a}_3$ | = | $ax_5 \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}} - ax_5 \hat{\mathbf{z}}$ | (4e) | Cd III |
| \mathbf{B}_{15} | $x_6 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$ | = | $ax_6 \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{z}}$ | (6g) | As II |
| \mathbf{B}_{16} | $-x_6 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$ | = | $-ax_6 \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{z}}$ | (6g) | As II |
| \mathbf{B}_{17} | $\frac{1}{2} \mathbf{a}_1 + x_6 \mathbf{a}_2$ | = | $\frac{1}{2}a \hat{\mathbf{x}} + ax_6 \hat{\mathbf{y}}$ | (6g) | As II |
| \mathbf{B}_{18} | $\frac{1}{2} \mathbf{a}_1 - x_6 \mathbf{a}_2$ | = | $\frac{1}{2}a \hat{\mathbf{x}} - ax_6 \hat{\mathbf{y}}$ | (6g) | As II |
| \mathbf{B}_{19} | $\frac{1}{2} \mathbf{a}_2 + x_6 \mathbf{a}_3$ | = | $\frac{1}{2}a \hat{\mathbf{y}} + ax_6 \hat{\mathbf{z}}$ | (6g) | As II |
| \mathbf{B}_{20} | $\frac{1}{2} \mathbf{a}_2 - x_6 \mathbf{a}_3$ | = | $\frac{1}{2}a \hat{\mathbf{y}} - ax_6 \hat{\mathbf{z}}$ | (6g) | As II |

References

- [1] A. V. Shevelkov, L. N. Reshetova, and B. A. Popovkin, *Cd₈As₇Cl: A Novel Pnictidohalide with a New Structure Type*, J. Solid State Chem. **134**, 282–285 (1997), doi:10.1006/jssc.1997.7555.