


EuIn₂P₂ Structure: AB2C2_hP10_194_a_f_f-001

This structure originally had the label `AB2C2_hP10_194_a_f_f`. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://afLOW.org/p/PL9Q>

https://afLOW.org/p/AB2C2_hP10_194_a_f_f-001

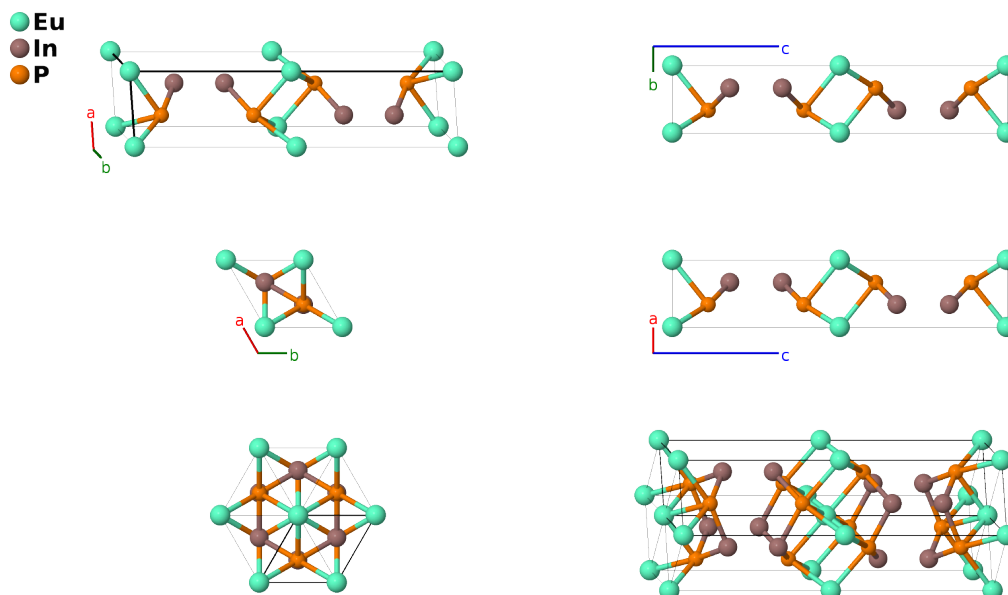

Prototype	EuIn ₂ P ₂
AFLOW prototype label	AB2C2_hP10_194_a_f_f-001
ICSD	none
Pearson symbol	hP10
Space group number	194
Space group symbol	<i>P6₃/mmc</i>
AFLOW prototype command	<code>afLOW --proto=AB2C2_hP10_194_a_f_f-001 --params=a, c/a, z₂, z₃</code>

Other compounds with this structure


EuIn₂As₂

Hexagonal primitive vectors

$$\mathbf{a}_1 = \frac{1}{2}a\hat{x} - \frac{\sqrt{3}}{2}a\hat{y}$$

$$\mathbf{a}_2 = \frac{1}{2}a\hat{x} + \frac{\sqrt{3}}{2}a\hat{y}$$

$$\mathbf{a}_3 = c\hat{z}$$

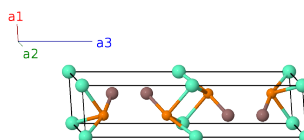

Basis vectors

	Lattice coordinates	=	Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	=	0	=	0	(2a) Eu I
\mathbf{B}_2	=	$\frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2} c \hat{\mathbf{z}}$	(2a) Eu I
\mathbf{B}_3	=	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4f) In I
\mathbf{B}_4	=	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2} a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4f) In I
\mathbf{B}_5	=	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$\frac{1}{2} a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4f) In I
\mathbf{B}_6	=	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4f) In I
\mathbf{B}_7	=	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(4f) P I
\mathbf{B}_8	=	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2} a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(4f) P I
\mathbf{B}_9	=	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$\frac{1}{2} a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(4f) P I
\mathbf{B}_{10}	=	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(4f) P I

References

- [1] J. Jiang and S. M. Kauzlarich, *Colossal Magnetoresistance in a Rare Earth Zintl Compound with a New Structure Type: EuIn_2P_2* , Chem. Mater. **18**, 435–441 (2006), doi:10.1021/cm0520362.