


Mn₂Co₂C Structure: AB2C2_tP5_123_b_e_ac-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/8ZWP>

https://aflow.org/p/AB2C2_tP5_123_b_e_ac-001

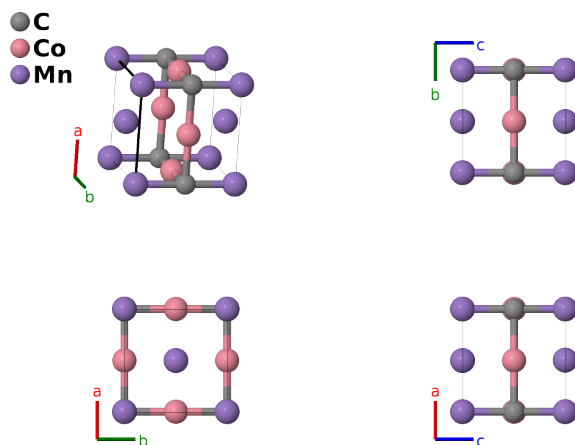


| | |
|--------------------------------|---|
| Prototype | CCo ₂ Mn ₂ |
| AFLOW prototype label | AB2C2_tP5_123_b_e_ac-001 |
| ICSD | 44353 |
| Pearson symbol | tP5 |
| Space group number | 123 |
| Space group symbol | <i>P4/mmm</i> |
| AFLOW prototype command | <code>aflow --proto=AB2C2_tP5_123_b_e_ac-001 --params=a, c/a</code> |

- We have inferred the value of a and the positions of the atoms from Figure 2(a) of (Holtzman, 1959) and Figure 3 of (Murthy, 1969), shifting the origin to be on the Mn_{II} atom. The value of c was inferred from the C-Mn_{II} distance given in the paper. This is a pseudo-cubic lattice, with $c/a \approx 1$.

Simple Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{x} \\ \mathbf{a}_2 &= a \hat{y} \\ \mathbf{a}_3 &= c \hat{z}\end{aligned}$$



Basis vectors

| | Lattice coordinates | | Cartesian coordinates | Wyckoff position | Atom type |
|----------------|------------------------|---|--------------------------|---|--------------|
| \mathbf{B}_1 | = | 0 | = | 0 | (1a) Mn I |
| \mathbf{B}_2 | = | $\frac{1}{2}\mathbf{a}_3$ | = | $\frac{1}{2}c\hat{\mathbf{z}}$ | (1b) C I |
| \mathbf{B}_3 | = | $\frac{1}{2}\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2$ | = | $\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}}$ | (1c) Mn II |
| \mathbf{B}_4 | = | $\frac{1}{2}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$ | = | $\frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}}$ | (2e) Co I |
| \mathbf{B}_5 | = | $\frac{1}{2}\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_3$ | = | $\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}c\hat{\mathbf{z}}$ | (2e) Co I |

References

- [1] A. H. Holtzman and I. G. P. Conrad, *Structural and Magnetic Properties of Mn-Co-C Alloys*, J. Appl. Phys. **30**, 103S–104S (1959), doi:10.1063/1.2185842.
- [2] N. S. S. Murthy, R. J. Begum, C. S. Somanathan, B. S. Srinivasan, and M. R. L. N. Murthy, *Ferrimagnetic structure of Mn_2Co_2C* , J. Phys.: Conf. Ser. **30**, 939–945 (1969), doi:10.1016/0022-3697(69)90291-1.