


Zabuyelite (Li₂CO₃) Structure: AB2C3_mC24_15_e_f_ef-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/JF5W>


https://aflow.org/p/AB2C3_mC24_15_e_f_ef-001

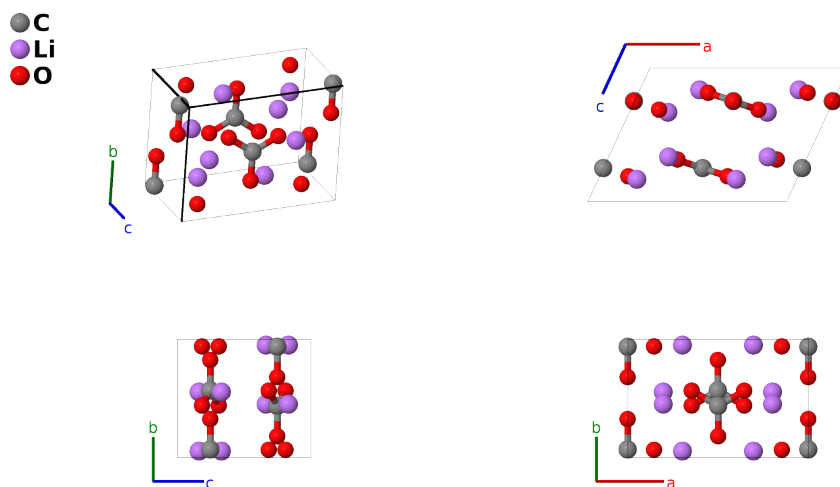

Prototype	CLi ₂ O ₃
AFLOW prototype label	AB2C3_mC24_15_e_f_ef-001
Mineral name	zabuyelite
ICSD	100324
Pearson symbol	mC24
Space group number	15
Space group symbol	C2/c
AFLOW prototype command	aflow --proto=AB2C3_mC24_15_e_f_ef-001 --params=a, b/a, c/a, β, y ₁ , y ₂ , x ₃ , y ₃ , z ₃ , x ₄ , y ₄ , z ₄

Base-centered Monoclinic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}} \end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= -y_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	C I
\mathbf{B}_2	$= y_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	C I
\mathbf{B}_3	$= -y_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	O I
\mathbf{B}_4	$= y_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	O I
\mathbf{B}_5	$= (x_3 - y_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Li I
\mathbf{B}_6	$= -(x_3 + y_3) \mathbf{a}_1 - (x_3 - y_3) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Li I
\mathbf{B}_7	$= -(x_3 - y_3) \mathbf{a}_1 - (x_3 + y_3) \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Li I
\mathbf{B}_8	$= (x_3 + y_3) \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Li I
\mathbf{B}_9	$= (x_4 - y_4) \mathbf{a}_1 + (x_4 + y_4) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	O II
\mathbf{B}_{10}	$= -(x_4 + y_4) \mathbf{a}_1 - (x_4 - y_4) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	O II
\mathbf{B}_{11}	$= -(x_4 - y_4) \mathbf{a}_1 - (x_4 + y_4) \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	O II
\mathbf{B}_{12}	$= (x_4 + y_4) \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	O II

References

- [1] H. Effenberger and J. Zemmann, *Verfeinerung der Kristallstruktur des Lithiumkarbonates, Li_2CO_3* , Z. Kristallogr. **150**, 133–138 (1979).

Found in

- [1] R. T. Downs and M. Hall-Wallace, *The American Mineralogist Crystal Structure Database*, Am. Mineral. **88**, 247–250 (2003).