


β -Na₂CuP₂O₇ Structure: AB2C7D2_mC48_15_a_f_e3f_f-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/9DDX>

https://aflow.org/p/AB2C7D2_mC48_15_a_f_e3f_f-001

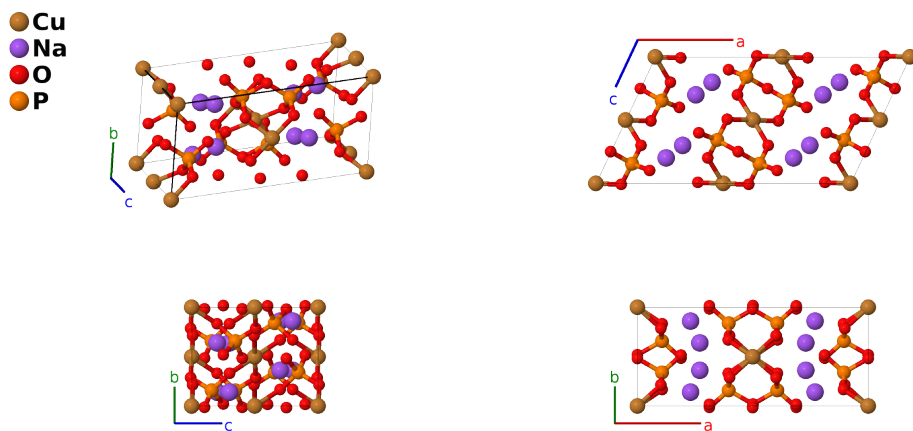

Prototype	CuNa ₂ O ₇ P ₂
AFLOW prototype label	AB2C7D2_mC48_15_a_f_e3f_f-001
ICSD	80418
Pearson symbol	mC48
Space group number	15
Space group symbol	<i>C</i> 2/ <i>c</i>
AFLOW prototype command	<code>aflow --proto=AB2C7D2_mC48_15_a_f_e3f_f-001</code> <code>--params=a, b/a, c/a, β, y_2, x_3, y_3, z_3, x_4, y_4, z_4, x_5, y_5, z_5, x_6, y_6, z_6, x_7, y_7, z_7</code>


Other compounds with this structure

Li₂CuP₂O₇

- Na₂CuP₂O₇ exists in two forms (Erragh, 1995):
 - Light blue α -Na₂CuP₂O₇ is stable up to 843K.
 - Above 843K it transforms into dark blue β -Na₂CuP₂O₇, which is metastable at room temperature.
- We use the data taken at 295K.

Base-centered Monoclinic primitive vectors

$$\begin{aligned}
\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\
\mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\
\mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}
\end{aligned}$$

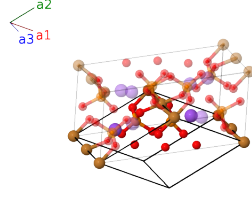

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	0	$=$	0	(4a)	Cu I
\mathbf{B}_2	$\frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}c \cos \beta \hat{\mathbf{x}} + \frac{1}{2}c \sin \beta \hat{\mathbf{z}}$	(4a)	Cu I
\mathbf{B}_3	$-y_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	O I
\mathbf{B}_4	$y_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	O I
\mathbf{B}_5	$(x_3 - y_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Na I
\mathbf{B}_6	$-(x_3 + y_3) \mathbf{a}_1 - (x_3 - y_3) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Na I
\mathbf{B}_7	$-(x_3 - y_3) \mathbf{a}_1 - (x_3 + y_3) \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Na I
\mathbf{B}_8	$(x_3 + y_3) \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Na I
\mathbf{B}_9	$(x_4 - y_4) \mathbf{a}_1 + (x_4 + y_4) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	O II
\mathbf{B}_{10}	$-(x_4 + y_4) \mathbf{a}_1 - (x_4 - y_4) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	O II
\mathbf{B}_{11}	$-(x_4 - y_4) \mathbf{a}_1 - (x_4 + y_4) \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	O II
\mathbf{B}_{12}	$(x_4 + y_4) \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	O II
\mathbf{B}_{13}	$(x_5 - y_5) \mathbf{a}_1 + (x_5 + y_5) \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(8f)	O III
\mathbf{B}_{14}	$-(x_5 + y_5) \mathbf{a}_1 - (x_5 - y_5) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_5 + c(z_5 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	O III
\mathbf{B}_{15}	$-(x_5 - y_5) \mathbf{a}_1 - (x_5 + y_5) \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(8f)	O III
\mathbf{B}_{16}	$(x_5 + y_5) \mathbf{a}_1 + (x_5 - y_5) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	O III
\mathbf{B}_{17}	$(x_6 - y_6) \mathbf{a}_1 + (x_6 + y_6) \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(8f)	O IV
\mathbf{B}_{18}	$-(x_6 + y_6) \mathbf{a}_1 - (x_6 - y_6) \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_6 + c(z_6 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	O IV
\mathbf{B}_{19}	$-(x_6 - y_6) \mathbf{a}_1 - (x_6 + y_6) \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \sin \beta \hat{\mathbf{z}}$	(8f)	O IV
\mathbf{B}_{20}	$(x_6 + y_6) \mathbf{a}_1 + (x_6 - y_6) \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_6 + c(z_6 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	O IV

$$\mathbf{B}_{21} = \begin{matrix} (x_7 - y_7) \mathbf{a}_1 + (x_7 + y_7) \mathbf{a}_2 + \\ z_7 \mathbf{a}_3 \end{matrix} = (ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \sin \beta \hat{\mathbf{z}} \quad (8f) \quad \text{P I}$$

$$\mathbf{B}_{22} = \begin{matrix} -(x_7 + y_7) \mathbf{a}_1 - (x_7 - y_7) \mathbf{a}_2 - \\ (z_7 - \frac{1}{2}) \mathbf{a}_3 \end{matrix} = - \begin{matrix} (ax_7 + c(z_7 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} - \\ c(z_7 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{matrix} \quad (8f) \quad \text{P I}$$

$$\mathbf{B}_{23} = \begin{matrix} -(x_7 - y_7) \mathbf{a}_1 - (x_7 + y_7) \mathbf{a}_2 - \\ z_7 \mathbf{a}_3 \end{matrix} = - \begin{matrix} (ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} - cz_7 \sin \beta \hat{\mathbf{z}} \end{matrix} \quad (8f) \quad \text{P I}$$

$$\mathbf{B}_{24} = \begin{matrix} (x_7 + y_7) \mathbf{a}_1 + (x_7 - y_7) \mathbf{a}_2 + \\ (z_7 + \frac{1}{2}) \mathbf{a}_3 \end{matrix} = \begin{matrix} (ax_7 + c(z_7 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} + \\ c(z_7 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{matrix} \quad (8f) \quad \text{P I}$$

References

- [1] F. Erragh, A. Boukhari, F. Abraham, and B. Elouadi, *The Crystal Structure of α - and β - $\text{Na}_2\text{CuP}_2\text{O}_7$* , *J. Solid State Chem.* **120**, 23–31 (1995), doi:10.1006/jssc.1995.1370.