


α -Na₂CuP₂O₇ Structure: AB2C7D2_mP48_14_e_2e_7e_2e-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/8Z5C>

https://aflow.org/p/AB2C7D2_mP48_14_e_2e_7e_2e-001

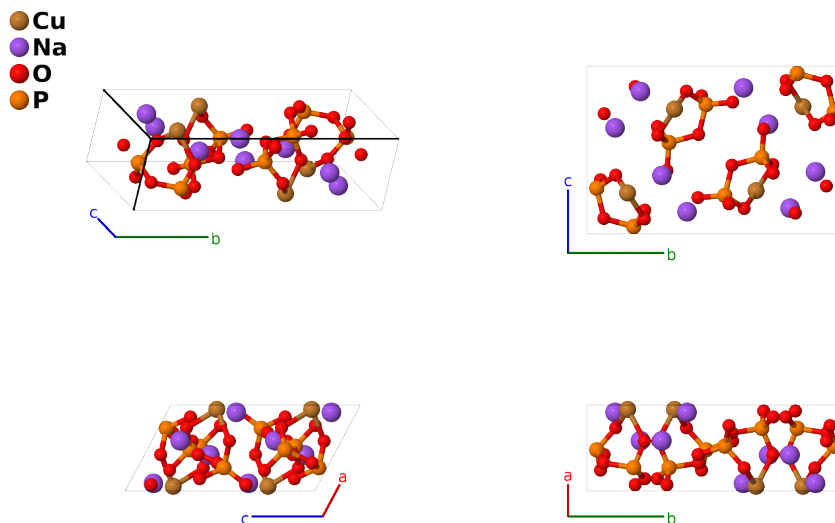

Prototype	CuNa ₂ O ₇ P ₂
AFLOW prototype label	AB2C7D2_mP48_14_e_2e_7e_2e-001
ICSD	80417
Pearson symbol	mP48
Space group number	14
Space group symbol	$P2_1/c$
AFLOW prototype command	<pre>aflow --proto=AB2C7D2_mP48_14_e_2e_7e_2e-001 --params=a,b/a,c/a,beta,x1,y1,z1,x2,y2,z2,x3,y3,z3,x4,y4,z4,x5,y5,z5,x6,y6,z6,x7,y7,z7,x8,y8,z8,x9,y9,z9,x10,y10,z10,x11,y11,z11,x12,y12,z12</pre>



Other compounds with this structure

KNaCuP₂O₇

- Na₂CuP₂O₇ exists in two forms (Erragh, 1995):
 - Light blue α -Na₂CuP₂O₇ is stable up to 843K.
 - Above 843K it transforms into dark blue β -Na₂CuP₂O₇, which is metastable at room temperature.
- We use the data taken at 295K.
- (Erragh, 1995) give the structural data for α -Na₂CuP₂O₇ in the $P2_1/n$ setting of space group #14. We use FINDSYM to transform this to the standard $P2_1/c$ setting.

Simple Monoclinic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}} \end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$x_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	=	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu I
\mathbf{B}_2	$-x_1 \mathbf{a}_1 + (y_1 + \frac{1}{2}) \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_1 + c(z_1 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_1 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu I
\mathbf{B}_3	$-x_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	=	$-(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} - cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	Cu I
\mathbf{B}_4	$x_1 \mathbf{a}_1 - (y_1 - \frac{1}{2}) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_1 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Cu I
\mathbf{B}_5	$x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	Na I
\mathbf{B}_6	$-x_2 \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_2 + c(z_2 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Na I
\mathbf{B}_7	$-x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	Na I
\mathbf{B}_8	$x_2 \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Na I
\mathbf{B}_9	$x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	Na II
\mathbf{B}_{10}	$-x_3 \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Na II
\mathbf{B}_{11}	$-x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	Na II
\mathbf{B}_{12}	$x_3 \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Na II
\mathbf{B}_{13}	$x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	O I
\mathbf{B}_{14}	$-x_4 \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_4 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O I
\mathbf{B}_{15}	$-x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	=	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	O I
\mathbf{B}_{16}	$x_4 \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_4 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O I
\mathbf{B}_{17}	$x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	=	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4e)	O II
\mathbf{B}_{18}	$-x_5 \mathbf{a}_1 + (y_5 + \frac{1}{2}) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_5 + c(z_5 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_5 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O II
\mathbf{B}_{19}	$-x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	=	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(4e)	O II
\mathbf{B}_{20}	$x_5 \mathbf{a}_1 - (y_5 - \frac{1}{2}) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_5 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O II
\mathbf{B}_{21}	$x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	=	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(4e)	O III

References

- [1] F. Erragh, A. Boukhari, F. Abraham, and B. Elouadi, *The Crystal Structure of α - and β - $\text{Na}_2\text{CuP}_2\text{O}_7$* , *J. Solid State Chem.* **120**, 23–31 (1995), doi:10.1006/jssc.1995.1370.