


AgF₂ Structure: AB2_oP12_61_a_c-002

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/F3J5>

https://aflow.org/p/AB2_oP12_61_a_c-002

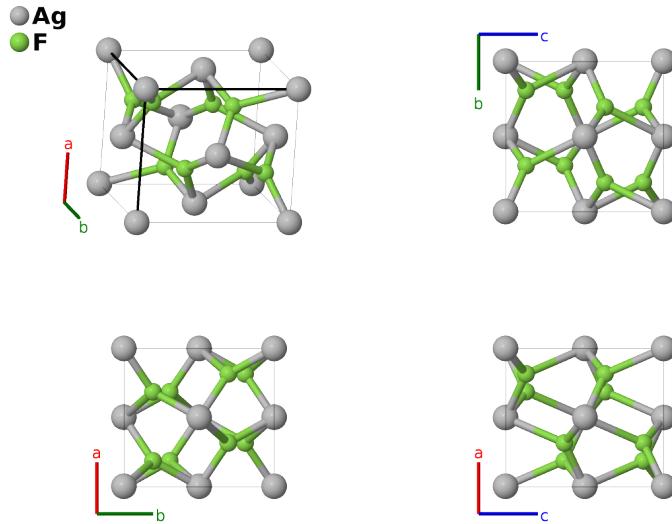


Prototype	AgF ₂
AFLOW prototype label	AB2_oP12_61_a_c-002
ICSD	9922
Pearson symbol	oP12
Space group number	61
Space group symbol	<i>Pbca</i>
AFLOW prototype command	<code>aflow --proto=AB2_oP12_61_a_c-002 --params=a, b/a, c/a, x2, y2, z2</code>

- This is a distortion of the fluorite (*C1*) structure. We can recover that structure when $a = b = c$ and $x_2 = y_2 = z_2 = 1/2$.
- β -HgO₂, AgF₂, and PdSe₂ have the same AFLOW prototype label, AB2_oP12_61_a_c. The structures are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Simple Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

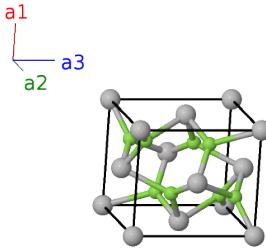

Basis vectors

	Lattice coordinates	=	Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	0	=	0	(4a)	Ag I
\mathbf{B}_2	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4a)	Ag I
\mathbf{B}_3	$\frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}b \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4a)	Ag I
\mathbf{B}_4	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	=	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}}$	(4a)	Ag I
\mathbf{B}_5	$x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$ax_2 \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(8c)	F I
\mathbf{B}_6	$-(x_2 - \frac{1}{2}) \mathbf{a}_1 - y_2 \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(8c)	F I
\mathbf{B}_7	$-x_2 \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	=	$-ax_2 \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(8c)	F I
\mathbf{B}_8	$(x_2 + \frac{1}{2}) \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(8c)	F I
\mathbf{B}_9	$-x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$-ax_2 \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(8c)	F I
\mathbf{B}_{10}	$(x_2 + \frac{1}{2}) \mathbf{a}_1 + y_2 \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	=	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(8c)	F I
\mathbf{B}_{11}	$x_2 \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$ax_2 \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(8c)	F I
\mathbf{B}_{12}	$-(x_2 - \frac{1}{2}) \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(8c)	F I

References

- [1] P. Fischer, D. Schwarzenbach, and H. M. Rietveld, *Crystal and magnetic structure of silver difluoride: I. Determination of the AgF₂ structure*, J. Phys. Chem. Solids **32**, 543–550 (1971), doi:10.1016/0022-3697(71)90003-5.

Found in

- [1] P. Fischer, G. Roult, and D. Schwarzenbach, *Crystal and magnetic structure of silver difluoride-II. Weak 4d-ferromagnetism of AgF₂*, J. Phys. Chem. Solids **32**, 1641–1647 (1971), doi:10.1016/S0022-3697(71)80057-4.