


α -SrIrO₃ Perovskite Structure: AB3C_mC60_15_af_e4f_ef-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/ZJ0D>

https://aflow.org/prototype-encyclopedia/AB3C_mC60_15_af_e4f_ef-001

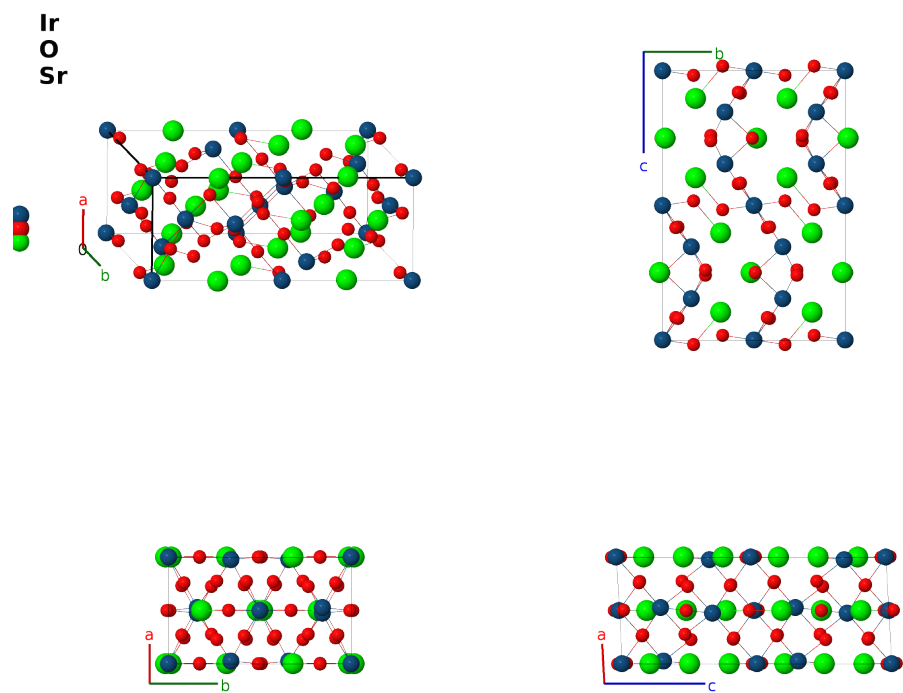

Prototype	IrSrO ₃
AFLOW prototype label	AB3C_mC60_15_af_e4f_ef-001
ICSD	16295
CCDC	1596894
Pearson symbol	mC60
Space group number	15
Space group symbol	$C2/c$
AFLOW prototype command	<code>aflow --proto=AB3C_mC60_15_af_e4f_ef-001</code> <code>--params=a,b/a,c/a,β,y₂,y₃,x₄,y₄,z₄,x₅,y₅,z₅,x₆,y₆,z₆,x₇,y₇,z₇,x₈,y₈,z₈,x₉,y₉,z₉</code>


Other compounds with this structure

BaIrO₃, MnPbO₃, RhSrO₃

- The structural transitions in SrIrO₃ are less certain than for other perovskites.
 - The ground state is usually believed to be monoclinic with space group $C2/c$ #15 (this structure), however
 - (Schmalle, 1990) found a somewhat disordered room temperature cubic phase.
 - (Longo, 1971) found that to the right of a line from (700°C, 5GPa) to (1650°, 2GPa) there is a transformation to the orthorhombic CaTiO₃ structure, but
 - (Wang, 2024) found a tetragonal double perovskite structure formed at 1400°C and 6GPa, well into the range where (Longo, 1971) found the orthorhombic structure. This structure is very close to cubic perovskite ($E2_1$), which may well be the structure found at higher pressures and temperatures.
- The Greek letters used to designate the phase are arbitrarily assigned in the order of the first publication describing the phases.
- We give the similar compounds in the order ABC₃, where the “A” atoms are on the (4a)/(8f) sites, the “B” atoms on the (4e)/(8f) sites, and the “C” atoms on the (4e)/(8f)⁴ sites.
- We list quaternary compounds having this structure under the Ba₃CoIr₂O₉ prototype.

Base-centered Monoclinic primitive vectors

$$\begin{aligned}
 \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\
 \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\
 \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}
 \end{aligned}$$

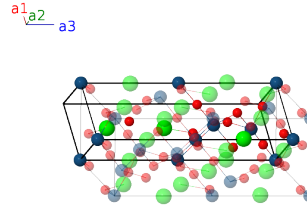

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= 0$	$=$	0	(4a)	Ir I
$\mathbf{B}_2$	$= \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}c \cos \beta \hat{\mathbf{x}} + \frac{1}{2}c \sin \beta \hat{\mathbf{z}}$	(4a)	Ir I
$\mathbf{B}_3$	$= -y_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	O I
$\mathbf{B}_4$	$= y_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	O I
$\mathbf{B}_5$	$= -y_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Sr I
$\mathbf{B}_6$	$= y_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Sr I
$\mathbf{B}_7$	$= (x_4 - y_4) \mathbf{a}_1 + (x_4 + y_4) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	Ir II
$\mathbf{B}_8$	$= -(x_4 + y_4) \mathbf{a}_1 - (x_4 - y_4) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Ir II
$\mathbf{B}_9$	$= -(x_4 - y_4) \mathbf{a}_1 - (x_4 + y_4) \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	Ir II

$$\begin{aligned}
\mathbf{B}_{10} &= (x_4 + y_4) \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3 = (ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} & (8f) & \text{Ir II} \\
\mathbf{B}_{11} &= (x_5 - y_5) \mathbf{a}_1 + (x_5 + y_5) \mathbf{a}_2 + z_5 \mathbf{a}_3 = (ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}} & (8f) & \text{O II} \\
\mathbf{B}_{12} &= -(x_5 + y_5) \mathbf{a}_1 - (x_5 - y_5) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3 = -(ax_5 + c(z_5 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} & (8f) & \text{O II} \\
\mathbf{B}_{13} &= -(x_5 - y_5) \mathbf{a}_1 - (x_5 + y_5) \mathbf{a}_2 - z_5 \mathbf{a}_3 = -(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \sin \beta \hat{\mathbf{z}} & (8f) & \text{O II} \\
\mathbf{B}_{14} &= (x_5 + y_5) \mathbf{a}_1 + (x_5 - y_5) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3 = (ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} & (8f) & \text{O II} \\
\mathbf{B}_{15} &= (x_6 - y_6) \mathbf{a}_1 + (x_6 + y_6) \mathbf{a}_2 + z_6 \mathbf{a}_3 = (ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}} & (8f) & \text{O III} \\
\mathbf{B}_{16} &= -(x_6 + y_6) \mathbf{a}_1 - (x_6 - y_6) \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3 = -(ax_6 + c(z_6 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} & (8f) & \text{O III} \\
\mathbf{B}_{17} &= -(x_6 - y_6) \mathbf{a}_1 - (x_6 + y_6) \mathbf{a}_2 - z_6 \mathbf{a}_3 = -(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \sin \beta \hat{\mathbf{z}} & (8f) & \text{O III} \\
\mathbf{B}_{18} &= (x_6 + y_6) \mathbf{a}_1 + (x_6 - y_6) \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3 = (ax_6 + c(z_6 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} & (8f) & \text{O III} \\
\mathbf{B}_{19} &= (x_7 - y_7) \mathbf{a}_1 + (x_7 + y_7) \mathbf{a}_2 + z_7 \mathbf{a}_3 = (ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \sin \beta \hat{\mathbf{z}} & (8f) & \text{O IV} \\
\mathbf{B}_{20} &= -(x_7 + y_7) \mathbf{a}_1 - (x_7 - y_7) \mathbf{a}_2 - (z_7 - \frac{1}{2}) \mathbf{a}_3 = -(ax_7 + c(z_7 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} & (8f) & \text{O IV} \\
\mathbf{B}_{21} &= -(x_7 - y_7) \mathbf{a}_1 - (x_7 + y_7) \mathbf{a}_2 - z_7 \mathbf{a}_3 = -(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} - cz_7 \sin \beta \hat{\mathbf{z}} & (8f) & \text{O IV} \\
\mathbf{B}_{22} &= (x_7 + y_7) \mathbf{a}_1 + (x_7 - y_7) \mathbf{a}_2 + (z_7 + \frac{1}{2}) \mathbf{a}_3 = (ax_7 + c(z_7 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} & (8f) & \text{O IV} \\
\mathbf{B}_{23} &= (x_8 - y_8) \mathbf{a}_1 + (x_8 + y_8) \mathbf{a}_2 + z_8 \mathbf{a}_3 = (ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} + cz_8 \sin \beta \hat{\mathbf{z}} & (8f) & \text{O V} \\
\mathbf{B}_{24} &= -(x_8 + y_8) \mathbf{a}_1 - (x_8 - y_8) \mathbf{a}_2 - (z_8 - \frac{1}{2}) \mathbf{a}_3 = -(ax_8 + c(z_8 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} - c(z_8 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} & (8f) & \text{O V} \\
\mathbf{B}_{25} &= -(x_8 - y_8) \mathbf{a}_1 - (x_8 + y_8) \mathbf{a}_2 - z_8 \mathbf{a}_3 = -(ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} - cz_8 \sin \beta \hat{\mathbf{z}} & (8f) & \text{O V} \\
\mathbf{B}_{26} &= (x_8 + y_8) \mathbf{a}_1 + (x_8 - y_8) \mathbf{a}_2 + (z_8 + \frac{1}{2}) \mathbf{a}_3 = (ax_8 + c(z_8 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} + c(z_8 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} & (8f) & \text{O V} \\
\mathbf{B}_{27} &= (x_9 - y_9) \mathbf{a}_1 + (x_9 + y_9) \mathbf{a}_2 + z_9 \mathbf{a}_3 = (ax_9 + cz_9 \cos \beta) \hat{\mathbf{x}} + by_9 \hat{\mathbf{y}} + cz_9 \sin \beta \hat{\mathbf{z}} & (8f) & \text{Sr II} \\
\mathbf{B}_{28} &= -(x_9 + y_9) \mathbf{a}_1 - (x_9 - y_9) \mathbf{a}_2 - (z_9 - \frac{1}{2}) \mathbf{a}_3 = -(ax_9 + c(z_9 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_9 \hat{\mathbf{y}} - c(z_9 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} & (8f) & \text{Sr II} \\
\mathbf{B}_{29} &= -(x_9 - y_9) \mathbf{a}_1 - (x_9 + y_9) \mathbf{a}_2 - z_9 \mathbf{a}_3 = -(ax_9 + cz_9 \cos \beta) \hat{\mathbf{x}} - by_9 \hat{\mathbf{y}} - cz_9 \sin \beta \hat{\mathbf{z}} & (8f) & \text{Sr II} \\
\mathbf{B}_{30} &= (x_9 + y_9) \mathbf{a}_1 + (x_9 - y_9) \mathbf{a}_2 + (z_9 + \frac{1}{2}) \mathbf{a}_3 = (ax_9 + c(z_9 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_9 \hat{\mathbf{y}} + c(z_9 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} & (8f) & \text{Sr II}
\end{aligned}$$

References

- [1] J. M. Longo, J. A. Kafalas, and R. Arnott, *Structure and properties of the high and low pressure forms of SrIrO₃*, J. Solid State Chem. **3**, 174–179 (1971), doi:10.1016/0022-4596(71)90022-3.

- [2] H. Schmalle, C. Gurtner, H. R. Oswald, and A. Reller, *The crystal structure of SrIrO_3* , Z. Kristallogr. **191**, 239–247 (1990), doi:10.1524/zkri.1990.191.14.239.
- [3] H. Wang, A. de la Torre, J. T. Race, Q. Wang, J. P. C. Ruff, P. M. Woodward, K. W. Plumb, D. Walker, and W. Xie, *Pseudosymmetry in Tetragonal Perovskite SrIrO_3 Synthesized under High Pressure*, ACS App. Electron. Mater. **6**, 6820–6825 (2024), doi:10.1021/acsaelm.4c01214.

First cited in

N. Anderson, M. J. Mehl, H. Eckert, S. Divilov, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 5*. Submitted to Computational Materials Science (2026).