







Rhombohedral CuTi_2S_4 Structure: AB4C2_hR28_166_2c_2c2h_abh-001

This structure originally had the label AB4C2_hR28_166_2c_2c2h_abh. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/p/8BYU>

https://aflow.org/p/AB4C2_hR28_166_2c_2c2h_abh-001

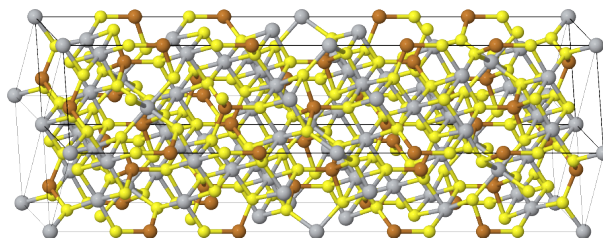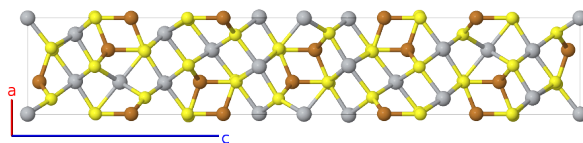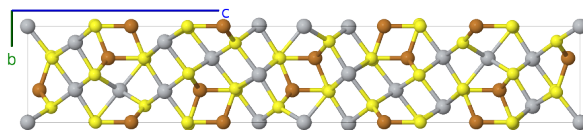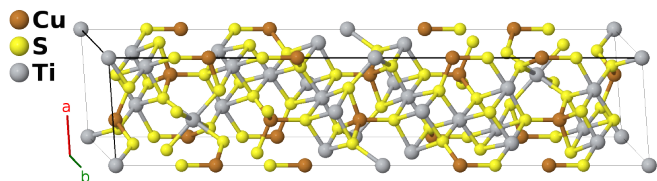


Prototype	CuS_4Ti_2
AFLOW prototype label	AB4C2_hR28_166_2c_2c2h_abh-001
ICSD	170228
Pearson symbol	hR28
Space group number	166
Space group symbol	$R\bar{3}m$
AFLOW prototype command	<pre>aflow --proto=AB4C2_hR28_166_2c_2c2h_abh-001 --params=a, c/a, x3, x4, x5, x6, x7, z7, x8, z8, x9, z9</pre>

- CuTi_2S_4 can also be found in a spinel phase.

Rhombohedral primitive vectors

$$\begin{aligned}
\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}} \\
\mathbf{a}_2 &= \frac{1}{\sqrt{3}}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}} \\
\mathbf{a}_3 &= -\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}}
\end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	0	$=$	0	(1a)	Ti I
\mathbf{B}_2	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}c \hat{\mathbf{z}}$	(1b)	Ti II
\mathbf{B}_3	$x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$cx_3 \hat{\mathbf{z}}$	(2c)	Cu I
\mathbf{B}_4	$-x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - x_3 \mathbf{a}_3$	$=$	$-cx_3 \hat{\mathbf{z}}$	(2c)	Cu I
\mathbf{B}_5	$x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$	$=$	$cx_4 \hat{\mathbf{z}}$	(2c)	Cu II
\mathbf{B}_6	$-x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$	$=$	$-cx_4 \hat{\mathbf{z}}$	(2c)	Cu II
\mathbf{B}_7	$x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + x_5 \mathbf{a}_3$	$=$	$cx_5 \hat{\mathbf{z}}$	(2c)	S I
\mathbf{B}_8	$-x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - x_5 \mathbf{a}_3$	$=$	$-cx_5 \hat{\mathbf{z}}$	(2c)	S I
\mathbf{B}_9	$x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 + x_6 \mathbf{a}_3$	$=$	$cx_6 \hat{\mathbf{z}}$	(2c)	S II
\mathbf{B}_{10}	$-x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 - x_6 \mathbf{a}_3$	$=$	$-cx_6 \hat{\mathbf{z}}$	(2c)	S II
\mathbf{B}_{11}	$x_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_7 - z_7) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_7 - z_7) \hat{\mathbf{y}} + \frac{1}{3}c(2x_7 + z_7) \hat{\mathbf{z}}$	(6h)	S III
\mathbf{B}_{12}	$z_7 \mathbf{a}_1 + z_7 \mathbf{a}_2 + x_7 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_7 - z_7) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_7 - z_7) \hat{\mathbf{y}} + \frac{1}{3}c(2x_7 + z_7) \hat{\mathbf{z}}$	(6h)	S III
\mathbf{B}_{13}	$x_7 \mathbf{a}_1 + z_7 \mathbf{a}_2 + x_7 \mathbf{a}_3$	$=$	$-\frac{1}{\sqrt{3}}a(x_7 - z_7) \hat{\mathbf{y}} + \frac{1}{3}c(2x_7 + z_7) \hat{\mathbf{z}}$	(6h)	S III
\mathbf{B}_{14}	$-z_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - x_7 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_7 - z_7) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_7 - z_7) \hat{\mathbf{y}} - \frac{1}{3}c(2x_7 + z_7) \hat{\mathbf{z}}$	(6h)	S III
\mathbf{B}_{15}	$-x_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_7 - z_7) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_7 - z_7) \hat{\mathbf{y}} - \frac{1}{3}c(2x_7 + z_7) \hat{\mathbf{z}}$	(6h)	S III
\mathbf{B}_{16}	$-x_7 \mathbf{a}_1 - z_7 \mathbf{a}_2 - x_7 \mathbf{a}_3$	$=$	$\frac{1}{\sqrt{3}}a(x_7 - z_7) \hat{\mathbf{y}} - \frac{1}{3}c(2x_7 + z_7) \hat{\mathbf{z}}$	(6h)	S III
\mathbf{B}_{17}	$x_8 \mathbf{a}_1 + x_8 \mathbf{a}_2 + z_8 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_8 - z_8) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_8 - z_8) \hat{\mathbf{y}} + \frac{1}{3}c(2x_8 + z_8) \hat{\mathbf{z}}$	(6h)	S IV
\mathbf{B}_{18}	$z_8 \mathbf{a}_1 + x_8 \mathbf{a}_2 + x_8 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_8 - z_8) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_8 - z_8) \hat{\mathbf{y}} + \frac{1}{3}c(2x_8 + z_8) \hat{\mathbf{z}}$	(6h)	S IV
\mathbf{B}_{19}	$x_8 \mathbf{a}_1 + z_8 \mathbf{a}_2 + x_8 \mathbf{a}_3$	$=$	$-\frac{1}{\sqrt{3}}a(x_8 - z_8) \hat{\mathbf{y}} + \frac{1}{3}c(2x_8 + z_8) \hat{\mathbf{z}}$	(6h)	S IV
\mathbf{B}_{20}	$-z_8 \mathbf{a}_1 - x_8 \mathbf{a}_2 - x_8 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_8 - z_8) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_8 - z_8) \hat{\mathbf{y}} - \frac{1}{3}c(2x_8 + z_8) \hat{\mathbf{z}}$	(6h)	S IV
\mathbf{B}_{21}	$-x_8 \mathbf{a}_1 - x_8 \mathbf{a}_2 - z_8 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_8 - z_8) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_8 - z_8) \hat{\mathbf{y}} - \frac{1}{3}c(2x_8 + z_8) \hat{\mathbf{z}}$	(6h)	S IV
\mathbf{B}_{22}	$-x_8 \mathbf{a}_1 - z_8 \mathbf{a}_2 - x_8 \mathbf{a}_3$	$=$	$\frac{1}{\sqrt{3}}a(x_8 - z_8) \hat{\mathbf{y}} - \frac{1}{3}c(2x_8 + z_8) \hat{\mathbf{z}}$	(6h)	S IV
\mathbf{B}_{23}	$x_9 \mathbf{a}_1 + x_9 \mathbf{a}_2 + z_9 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_9 - z_9) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_9 - z_9) \hat{\mathbf{y}} + \frac{1}{3}c(2x_9 + z_9) \hat{\mathbf{z}}$	(6h)	Ti III
\mathbf{B}_{24}	$z_9 \mathbf{a}_1 + x_9 \mathbf{a}_2 + x_9 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_9 - z_9) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_9 - z_9) \hat{\mathbf{y}} + \frac{1}{3}c(2x_9 + z_9) \hat{\mathbf{z}}$	(6h)	Ti III
\mathbf{B}_{25}	$x_9 \mathbf{a}_1 + z_9 \mathbf{a}_2 + x_9 \mathbf{a}_3$	$=$	$-\frac{1}{\sqrt{3}}a(x_9 - z_9) \hat{\mathbf{y}} + \frac{1}{3}c(2x_9 + z_9) \hat{\mathbf{z}}$	(6h)	Ti III
\mathbf{B}_{26}	$-z_9 \mathbf{a}_1 - x_9 \mathbf{a}_2 - x_9 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_9 - z_9) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_9 - z_9) \hat{\mathbf{y}} - \frac{1}{3}c(2x_9 + z_9) \hat{\mathbf{z}}$	(6h)	Ti III

$$\mathbf{B}_{27} = -x_9 \mathbf{a}_1 - x_9 \mathbf{a}_2 - z_9 \mathbf{a}_3 = -\frac{1}{2}a(x_9 - z_9) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a(x_9 - z_9) \hat{\mathbf{y}} - \frac{1}{3}c(2x_9 + z_9) \hat{\mathbf{z}} \quad (6h) \quad \text{Ti III}$$

$$\mathbf{B}_{28} = -x_9 \mathbf{a}_1 - z_9 \mathbf{a}_2 - x_9 \mathbf{a}_3 = \frac{1}{\sqrt{3}}a(x_9 - z_9) \hat{\mathbf{y}} - \frac{1}{3}c(2x_9 + z_9) \hat{\mathbf{z}} \quad (6h) \quad \text{Ti III}$$

References

- [1] N. Soheilnia, K. M. Kleinke, E. Dashjav, H. L. Cuthbert, J. E. Greedan, and H. Kleinke, *Crystal Structure and Physical Properties of a New CuTi_2S_4 Modification in Comparison to the Thiospinel*, *Inorg. Chem.* **43**, 6473–6478 (2004), doi:10.1021/ic0495113.