


BPO₄ (*H0*₇) Structure: AB4C_tI12_82_c_g_a-001

This structure originally had the label AB4C_tI12_82_c_g_a. Calls to that address will be redirected here.

Cite this page as: M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017

<https://aflow.org/p/C601>

https://aflow.org/p/AB4C_tI12_82_c_g_a-001

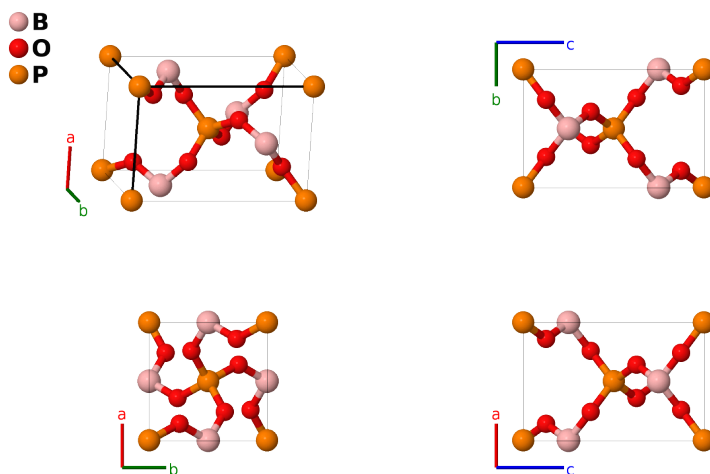


Prototype	BO ₄ P
AFLOW prototype label	AB4C_tI12_82_c_g_a-001
<i>Strukturbericht</i> designation	<i>H0</i> ₇
ICSD	55082
Pearson symbol	tI12
Space group number	82
Space group symbol	$I\bar{4}$
AFLOW prototype command	aflow --proto=AB4C_tI12_82_c_g_a-001 --params=a, c/a, x ₃ , y ₃ , z ₃

Other compounds with this structure
AlAsO₄

Body-centered Tetragonal primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= -\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} - \frac{1}{2}c \hat{\mathbf{z}} \end{aligned}$$

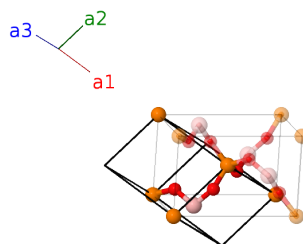

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	=	0	=	0	(2a) P I
\mathbf{B}_2	=	$\frac{3}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{4}c\hat{\mathbf{z}}$	(2c) B I
\mathbf{B}_3	=	$(y_3 + z_3)\mathbf{a}_1 + (x_3 + z_3)\mathbf{a}_2 +$ $(x_3 + y_3)\mathbf{a}_3$	=	$ax_3\hat{\mathbf{x}} + ay_3\hat{\mathbf{y}} + cz_3\hat{\mathbf{z}}$	(8g) O I
\mathbf{B}_4	=	$-(y_3 - z_3)\mathbf{a}_1 - (x_3 - z_3)\mathbf{a}_2 -$ $(x_3 + y_3)\mathbf{a}_3$	=	$-ax_3\hat{\mathbf{x}} - ay_3\hat{\mathbf{y}} + cz_3\hat{\mathbf{z}}$	(8g) O I
\mathbf{B}_5	=	$-(x_3 + z_3)\mathbf{a}_1 + (y_3 - z_3)\mathbf{a}_2 -$ $(x_3 - y_3)\mathbf{a}_3$	=	$ay_3\hat{\mathbf{x}} - ax_3\hat{\mathbf{y}} - cz_3\hat{\mathbf{z}}$	(8g) O I
\mathbf{B}_6	=	$(x_3 - z_3)\mathbf{a}_1 - (y_3 + z_3)\mathbf{a}_2 +$ $(x_3 - y_3)\mathbf{a}_3$	=	$-ay_3\hat{\mathbf{x}} + ax_3\hat{\mathbf{y}} - cz_3\hat{\mathbf{z}}$	(8g) O I

References

- [1] M. Schmidt, B. Ewald, Y. Prots, R. Cardoso-Gil, M. Armbrüster, I. Loa, L. Zhang, Y.-X. Huang, U. Schwarz, and R. Kniep, *Growth and Characterization of BPO₄ Single Crystals*, *Z. Anorganische und Allgemeine Chemie* **630**, 655–662 (2004), doi:10.1002/zaac.200400002.