

$\text{NaSb}(\text{OH})_6$ ($J1_{11}$) Structure:


AB6C_tP32_86_c_3g_d-001

This structure originally had the label AB6C_tP32_86_d_3g_c. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/p/NR43>

https://aflow.org/p/AB6C_tP32_86_c_3g_d-001

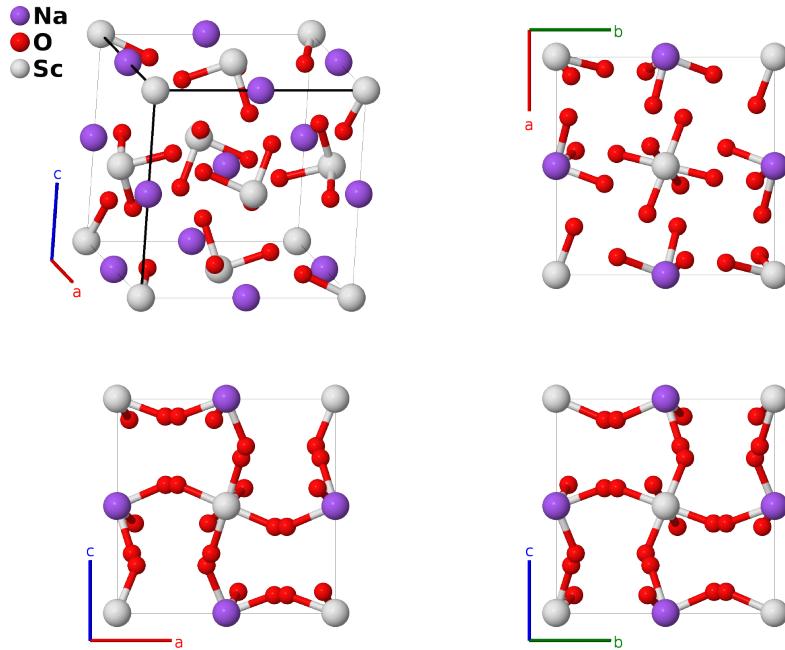

Prototype $\text{Na}(\text{OH})_6\text{Sb}$

AFLOW prototype label AB6C_tP32_86_c_3g_d-001

Strukturbericht designation $J1_{11}$

ICSD 4211

Pearson symbol tP32

Space group number 86

Space group symbol $P4_2/n$

AFLOW prototype command

```
aflow --proto=AB6C_tP32_86_c_3g_d-001
--params=a,c/a,x3,y3,z3,x4,y4,z4,x5,y5,z5
```

Other compounds with this structure


$\text{AgSb}(\text{OH})_6$

-
- The atomic positions were originally determined using setting 1 of space group $P4_2/n$ #86. We used FINDSYM to change the origin to setting 2.

- The sites labeled “O” are actually OH radicals.
- Although the replacement of fluorine by OH does not affect the shape of the Sb-(F,OH)₆ ions, it has a profound effect on the structure, as can be seen by looking at NaSbF₆ and NaSbF₄(OH)₂ ($J1_{12}$).

Simple Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

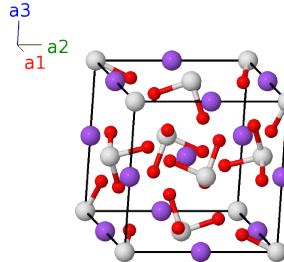

Basis vectors

	Lattice coordinates	=	Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	0	=	0	(4c)	Na I
\mathbf{B}_2	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	=	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}}$	(4c)	Na I
\mathbf{B}_3	$\frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4c)	Na I
\mathbf{B}_4	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4c)	Na I
\mathbf{B}_5	$\frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}c \hat{\mathbf{z}}$	(4d)	Sc I
\mathbf{B}_6	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4d)	Sc I
\mathbf{B}_7	$\frac{1}{2} \mathbf{a}_2$	=	$\frac{1}{2}a \hat{\mathbf{y}}$	(4d)	Sc I
\mathbf{B}_8	$\frac{1}{2} \mathbf{a}_1$	=	$\frac{1}{2}a \hat{\mathbf{x}}$	(4d)	Sc I
\mathbf{B}_9	$x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$ax_3 \hat{\mathbf{x}} + ay_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(8g)	O I
\mathbf{B}_{10}	$-\left(x_3 - \frac{1}{2}\right) \mathbf{a}_1 - \left(y_3 - \frac{1}{2}\right) \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$-a\left(x_3 - \frac{1}{2}\right) \hat{\mathbf{x}} - a\left(y_3 - \frac{1}{2}\right) \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(8g)	O I
\mathbf{B}_{11}	$-y_3 \mathbf{a}_1 + \left(x_3 + \frac{1}{2}\right) \mathbf{a}_2 + \left(z_3 + \frac{1}{2}\right) \mathbf{a}_3$	=	$-ay_3 \hat{\mathbf{x}} + a\left(x_3 + \frac{1}{2}\right) \hat{\mathbf{y}} + c\left(z_3 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8g)	O I
\mathbf{B}_{12}	$\left(y_3 + \frac{1}{2}\right) \mathbf{a}_1 - x_3 \mathbf{a}_2 + \left(z_3 + \frac{1}{2}\right) \mathbf{a}_3$	=	$a\left(y_3 + \frac{1}{2}\right) \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} + c\left(z_3 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8g)	O I
\mathbf{B}_{13}	$-x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-ax_3 \hat{\mathbf{x}} - ay_3 \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(8g)	O I
\mathbf{B}_{14}	$\left(x_3 + \frac{1}{2}\right) \mathbf{a}_1 + \left(y_3 + \frac{1}{2}\right) \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$a\left(x_3 + \frac{1}{2}\right) \hat{\mathbf{x}} + a\left(y_3 + \frac{1}{2}\right) \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(8g)	O I
\mathbf{B}_{15}	$y_3 \mathbf{a}_1 - \left(x_3 - \frac{1}{2}\right) \mathbf{a}_2 - \left(z_3 - \frac{1}{2}\right) \mathbf{a}_3$	=	$ay_3 \hat{\mathbf{x}} - a\left(x_3 - \frac{1}{2}\right) \hat{\mathbf{y}} - c\left(z_3 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(8g)	O I
\mathbf{B}_{16}	$-\left(y_3 - \frac{1}{2}\right) \mathbf{a}_1 + x_3 \mathbf{a}_2 - \left(z_3 - \frac{1}{2}\right) \mathbf{a}_3$	=	$-a\left(y_3 - \frac{1}{2}\right) \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} - c\left(z_3 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(8g)	O I
\mathbf{B}_{17}	$x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$ax_4 \hat{\mathbf{x}} + ay_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8g)	O II
\mathbf{B}_{18}	$-\left(x_4 - \frac{1}{2}\right) \mathbf{a}_1 - \left(y_4 - \frac{1}{2}\right) \mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$-a\left(x_4 - \frac{1}{2}\right) \hat{\mathbf{x}} - a\left(y_4 - \frac{1}{2}\right) \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8g)	O II
\mathbf{B}_{19}	$-y_4 \mathbf{a}_1 + \left(x_4 + \frac{1}{2}\right) \mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_3$	=	$-ay_4 \hat{\mathbf{x}} + a\left(x_4 + \frac{1}{2}\right) \hat{\mathbf{y}} + c\left(z_4 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8g)	O II
\mathbf{B}_{20}	$\left(y_4 + \frac{1}{2}\right) \mathbf{a}_1 - x_4 \mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_3$	=	$a\left(y_4 + \frac{1}{2}\right) \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} + c\left(z_4 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8g)	O II
\mathbf{B}_{21}	$-x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	=	$-ax_4 \hat{\mathbf{x}} - ay_4 \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(8g)	O II
\mathbf{B}_{22}	$\left(x_4 + \frac{1}{2}\right) \mathbf{a}_1 + \left(y_4 + \frac{1}{2}\right) \mathbf{a}_2 - z_4 \mathbf{a}_3$	=	$a\left(x_4 + \frac{1}{2}\right) \hat{\mathbf{x}} + a\left(y_4 + \frac{1}{2}\right) \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(8g)	O II

\mathbf{B}_{23}	$=$	$y_4 \mathbf{a}_1 - (x_4 - \frac{1}{2}) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a y_4 \hat{\mathbf{x}} - a (x_4 - \frac{1}{2}) \hat{\mathbf{y}} - c (z_4 - \frac{1}{2}) \hat{\mathbf{z}}$	(8g)	O II
\mathbf{B}_{24}	$=$	$- (y_4 - \frac{1}{2}) \mathbf{a}_1 + x_4 \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-a (y_4 - \frac{1}{2}) \hat{\mathbf{x}} + a x_4 \hat{\mathbf{y}} - c (z_4 - \frac{1}{2}) \hat{\mathbf{z}}$	(8g)	O II
\mathbf{B}_{25}	$=$	$x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$a x_5 \hat{\mathbf{x}} + a y_5 \hat{\mathbf{y}} + c z_5 \hat{\mathbf{z}}$	(8g)	O III
\mathbf{B}_{26}	$=$	$- (x_5 - \frac{1}{2}) \mathbf{a}_1 - (y_5 - \frac{1}{2}) \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$-a (x_5 - \frac{1}{2}) \hat{\mathbf{x}} - a (y_5 - \frac{1}{2}) \hat{\mathbf{y}} + c z_5 \hat{\mathbf{z}}$	(8g)	O III
\mathbf{B}_{27}	$=$	$-y_5 \mathbf{a}_1 + (x_5 + \frac{1}{2}) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a y_5 \hat{\mathbf{x}} + a (x_5 + \frac{1}{2}) \hat{\mathbf{y}} + c (z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(8g)	O III
\mathbf{B}_{28}	$=$	$(y_5 + \frac{1}{2}) \mathbf{a}_1 - x_5 \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$a (y_5 + \frac{1}{2}) \hat{\mathbf{x}} - a x_5 \hat{\mathbf{y}} + c (z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(8g)	O III
\mathbf{B}_{29}	$=$	$-x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-a x_5 \hat{\mathbf{x}} - a y_5 \hat{\mathbf{y}} - c z_5 \hat{\mathbf{z}}$	(8g)	O III
\mathbf{B}_{30}	$=$	$(x_5 + \frac{1}{2}) \mathbf{a}_1 + (y_5 + \frac{1}{2}) \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$a (x_5 + \frac{1}{2}) \hat{\mathbf{x}} + a (y_5 + \frac{1}{2}) \hat{\mathbf{y}} - c z_5 \hat{\mathbf{z}}$	(8g)	O III
\mathbf{B}_{31}	$=$	$y_5 \mathbf{a}_1 - (x_5 - \frac{1}{2}) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a y_5 \hat{\mathbf{x}} - a (x_5 - \frac{1}{2}) \hat{\mathbf{y}} - c (z_5 - \frac{1}{2}) \hat{\mathbf{z}}$	(8g)	O III
\mathbf{B}_{32}	$=$	$- (y_5 - \frac{1}{2}) \mathbf{a}_1 + x_5 \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-a (y_5 - \frac{1}{2}) \hat{\mathbf{x}} + a x_5 \hat{\mathbf{y}} - c (z_5 - \frac{1}{2}) \hat{\mathbf{z}}$	(8g)	O III

References

- [1] T. Asai, *Refinement of the Crystal Structure of Sodium Hexahydroxoantimonate(V), NaSb(OH)₆*, Bull. Chem. Soc. Japan **48**, 2677–2679 (1975), doi:10.1246/bcsj.48.2677.

Found in

- [1] F. Hoffmann, M. Sartor, and M. Fröba, *The Fascination of Crystals and Symmetry* (2014). NASB(OH)6.