


Sodium Chlorate (NaClO_3 , $G0_3$) Structure: ABC3_cP20_198_a_a_b-001

This structure originally had the label ABC3_cP20_198_a_a_b. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043

<https://aflow.org/p/QEXW>

https://aflow.org/p/ABC3_cP20_198_a_a_b-001

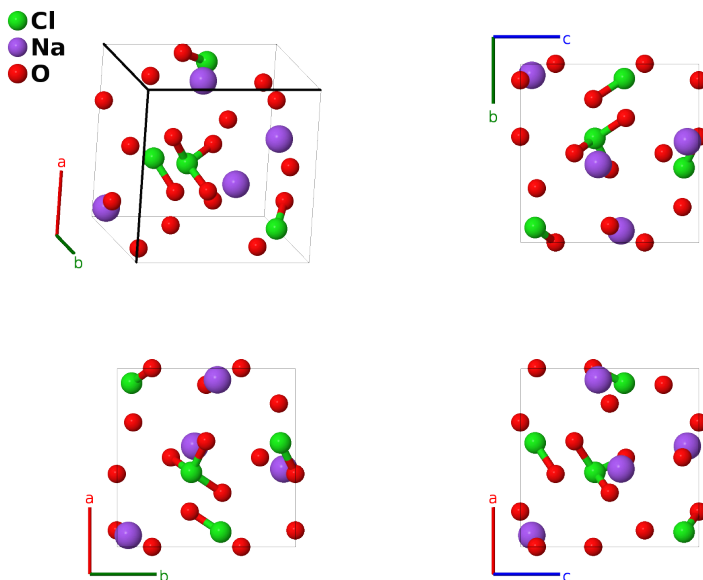


Prototype	NaClO_3
AFLOW prototype label	ABC3_cP20_198_a_a_b-001
Strukturbericht designation	$G0_3$
Mineral name	sodium chlorate
ICSD	16714
Pearson symbol	cP20
Space group number	198
Space group symbol	$P2_13$
AFLOW prototype command	<code>aflow --proto=ABC3_cP20_198_a_a_b-001 --params=$a, x_1, x_2, x_3, y_3, z_3$</code>

Other compounds with this structure

NaBrO_3

Simple Cubic primitive vectors

a1
a2
a3



$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= a \hat{\mathbf{z}}\end{aligned}$$

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2 + x_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + ax_1 \hat{\mathbf{y}} + ax_1 \hat{\mathbf{z}}$	(4a)	Cl I
\mathbf{B}_2	$= -(x_1 - \frac{1}{2}) \mathbf{a}_1 - x_1 \mathbf{a}_2 + (x_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_1 - \frac{1}{2}) \hat{\mathbf{x}} - ax_1 \hat{\mathbf{y}} + a(x_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	Cl I
\mathbf{B}_3	$= -x_1 \mathbf{a}_1 + (x_1 + \frac{1}{2}) \mathbf{a}_2 - (x_1 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + a(x_1 + \frac{1}{2}) \hat{\mathbf{y}} - a(x_1 - \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	Cl I
\mathbf{B}_4	$= (x_1 + \frac{1}{2}) \mathbf{a}_1 - (x_1 - \frac{1}{2}) \mathbf{a}_2 - x_1 \mathbf{a}_3$	$=$	$a(x_1 + \frac{1}{2}) \hat{\mathbf{x}} - a(x_1 - \frac{1}{2}) \hat{\mathbf{y}} - ax_1 \hat{\mathbf{z}}$	(4a)	Cl I
\mathbf{B}_5	$= x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}} + ax_2 \hat{\mathbf{z}}$	(4a)	Na I
\mathbf{B}_6	$= -(x_2 - \frac{1}{2}) \mathbf{a}_1 - x_2 \mathbf{a}_2 + (x_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}} + a(x_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	Na I
\mathbf{B}_7	$= -x_2 \mathbf{a}_1 + (x_2 + \frac{1}{2}) \mathbf{a}_2 - (x_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + a(x_2 + \frac{1}{2}) \hat{\mathbf{y}} - a(x_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	Na I
\mathbf{B}_8	$= (x_2 + \frac{1}{2}) \mathbf{a}_1 - (x_2 - \frac{1}{2}) \mathbf{a}_2 - x_2 \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} - a(x_2 - \frac{1}{2}) \hat{\mathbf{y}} - ax_2 \hat{\mathbf{z}}$	(4a)	Na I
\mathbf{B}_9	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + ay_3 \hat{\mathbf{y}} + az_3 \hat{\mathbf{z}}$	(12b)	O I
\mathbf{B}_{10}	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 - y_3 \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} - ay_3 \hat{\mathbf{y}} + a(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(12b)	O I
\mathbf{B}_{11}	$= -x_3 \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + a(y_3 + \frac{1}{2}) \hat{\mathbf{y}} - a(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(12b)	O I
\mathbf{B}_{12}	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} - a(y_3 - \frac{1}{2}) \hat{\mathbf{y}} - az_3 \hat{\mathbf{z}}$	(12b)	O I
\mathbf{B}_{13}	$= z_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + y_3 \mathbf{a}_3$	$=$	$az_3 \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} + ay_3 \hat{\mathbf{z}}$	(12b)	O I
\mathbf{B}_{14}	$= (z_3 + \frac{1}{2}) \mathbf{a}_1 - (x_3 - \frac{1}{2}) \mathbf{a}_2 - y_3 \mathbf{a}_3$	$=$	$a(z_3 + \frac{1}{2}) \hat{\mathbf{x}} - a(x_3 - \frac{1}{2}) \hat{\mathbf{y}} - ay_3 \hat{\mathbf{z}}$	(12b)	O I
\mathbf{B}_{15}	$= -(z_3 - \frac{1}{2}) \mathbf{a}_1 - x_3 \mathbf{a}_2 + (y_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(z_3 - \frac{1}{2}) \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} + a(y_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(12b)	O I
\mathbf{B}_{16}	$= -z_3 \mathbf{a}_1 + (x_3 + \frac{1}{2}) \mathbf{a}_2 - (y_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-az_3 \hat{\mathbf{x}} + a(x_3 + \frac{1}{2}) \hat{\mathbf{y}} - a(y_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(12b)	O I
\mathbf{B}_{17}	$= y_3 \mathbf{a}_1 + z_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$ay_3 \hat{\mathbf{x}} + az_3 \hat{\mathbf{y}} + ax_3 \hat{\mathbf{z}}$	(12b)	O I
\mathbf{B}_{18}	$= -y_3 \mathbf{a}_1 + (z_3 + \frac{1}{2}) \mathbf{a}_2 - (x_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-ay_3 \hat{\mathbf{x}} + a(z_3 + \frac{1}{2}) \hat{\mathbf{y}} - a(x_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(12b)	O I
\mathbf{B}_{19}	$= (y_3 + \frac{1}{2}) \mathbf{a}_1 - (z_3 - \frac{1}{2}) \mathbf{a}_2 - x_3 \mathbf{a}_3$	$=$	$a(y_3 + \frac{1}{2}) \hat{\mathbf{x}} - a(z_3 - \frac{1}{2}) \hat{\mathbf{y}} - ax_3 \hat{\mathbf{z}}$	(12b)	O I
\mathbf{B}_{20}	$= -(y_3 - \frac{1}{2}) \mathbf{a}_1 - z_3 \mathbf{a}_2 + (x_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(y_3 - \frac{1}{2}) \hat{\mathbf{x}} - az_3 \hat{\mathbf{y}} + a(x_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(12b)	O I

References

- [1] G. N. Ramachandran and K. S. Chandrasekaran, *The absolute configuration of sodium chlorate* **10**, 671–675 (1957), doi:10.1107/S0365110X57002327.

Found in

- [1] A. A. Kaminskii, S. N. Bagayev, J. Hulliger, H. Eichler, J. Findeisen, and R. Macdonald, *Acentric cubic NaClO_3 —a new crystal for Raman lasers*, Applied Physics B **67**, 157–162 (1998), doi:10.1007/s003400050487.