


Aragonite ($G0_2$, CaCO_3) Structure: ABC3_oP20_62_c_c_cd-003

This structure originally had the label ABC3_oP20_62_c_c_cd. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/p/7S19>

https://aflow.org/p/ABC3_oP20_62_c_c_cd-003

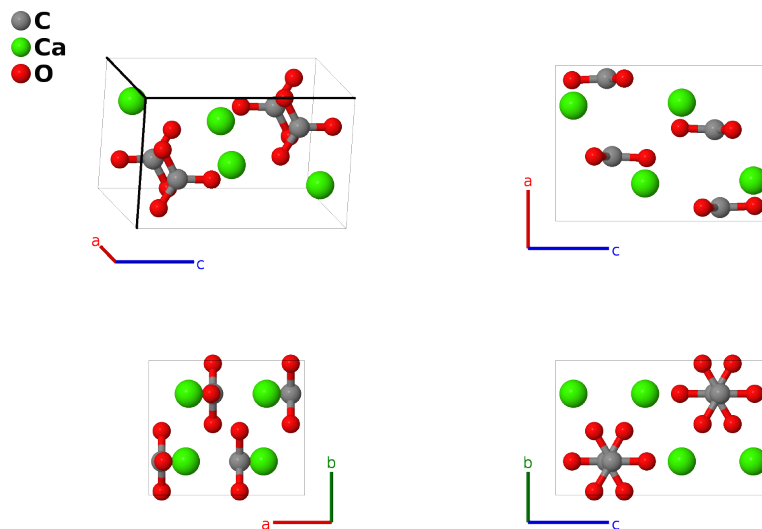

Prototype	CaCO_3
AFLOW prototype label	ABC3_oP20_62_c_c_cd-003
<i>Strukturbericht</i> designation	$G0_2$
Mineral name	aragonite
ICSD	15194
Pearson symbol	oP20
Space group number	62
Space group symbol	$Pnma$
AFLOW prototype command	<pre>aflow --proto=ABC3_oP20_62_c_c_cd-003 --params=a, b/a, c/a, x1, z1, x2, z2, x3, z3, x4, y4, z4</pre>

Other compounds with this structure

BaCO_3 (Witherite), $(\text{Ba}, \text{Ca})\text{CO}_3$ (Bromlite), $(\text{Cu}, \text{Mg}, \text{Mn})\text{CO}_3$ (Manganocalcite), MnCO_3 (Rhodochrosite), PbCO_3 (Cerussite), SrCO_3 (Strontianite)


- (Ewald, 1931) originally listed this as *Strukturbericht G2*, but it was designated $G0_2$ in (Gottfried, 1937).

- Argonite (CaCO_3 , $G0_2$, $\alpha\text{-KNO}_3$, and $(\text{NH}_4)\text{NO}_3$ III ($G0_{10}$) all share the same AFLOW label, ABC3_oP20_62_c.c.cd. The structures are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Simple Orthorhombic primitive vectors



$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4c)	C I
\mathbf{B}_2	$= -(x_1 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_1 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	C I
\mathbf{B}_3	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	(4c)	C I
\mathbf{B}_4	$= (x_1 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_1 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	C I
\mathbf{B}_5	$= x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4c)	Ca I
\mathbf{B}_6	$= -(x_2 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Ca I
\mathbf{B}_7	$= -x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4c)	Ca I
\mathbf{B}_8	$= (x_2 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Ca I
\mathbf{B}_9	$= x_3 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(4c)	O I
\mathbf{B}_{10}	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	O I
\mathbf{B}_{11}	$= -x_3 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(4c)	O I
\mathbf{B}_{12}	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	O I
\mathbf{B}_{13}	$= x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8d)	O II
\mathbf{B}_{14}	$= -(x_4 - \frac{1}{2}) \mathbf{a}_1 - y_4 \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_4 - \frac{1}{2}) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O II
\mathbf{B}_{15}	$= -x_4 \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + b(y_4 + \frac{1}{2}) \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(8d)	O II
\mathbf{B}_{16}	$= (x_4 + \frac{1}{2}) \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_4 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_4 - \frac{1}{2}) \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O II
\mathbf{B}_{17}	$= -x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(8d)	O II
\mathbf{B}_{18}	$= (x_4 + \frac{1}{2}) \mathbf{a}_1 + y_4 \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_4 + \frac{1}{2}) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O II
\mathbf{B}_{19}	$= x_4 \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} - b(y_4 - \frac{1}{2}) \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8d)	O II
\mathbf{B}_{20}	$= -(x_4 - \frac{1}{2}) \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_4 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_4 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O II

References

- [1] J. P. R. de Villiers, *Crystal Structures of Aragonite, Strontianite, and Witherite*, Am. Mineral. **56**, 758–767 (1971).
- [2] P. P. Ewald and C. Hermann, eds., *Strukturbericht 1913-1928* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1931).
- [3] C. Gottfried and F. Schosberger, eds., *Strukturbericht Band III 1933-1935* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1937).

Found in

- [1] mindat.org, *Aragonite*. Mineral Database.