Garavellite ($FeSbBiS_4$) Structure: ABC4D_oP28_62_c_c_4c_c-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

---

https://aflow.org/prototype-encyclopedia/76MJ

https://aflow.org/prototype-encyclopedia/ABC4D_oP28_62_c_c_4c_c-001

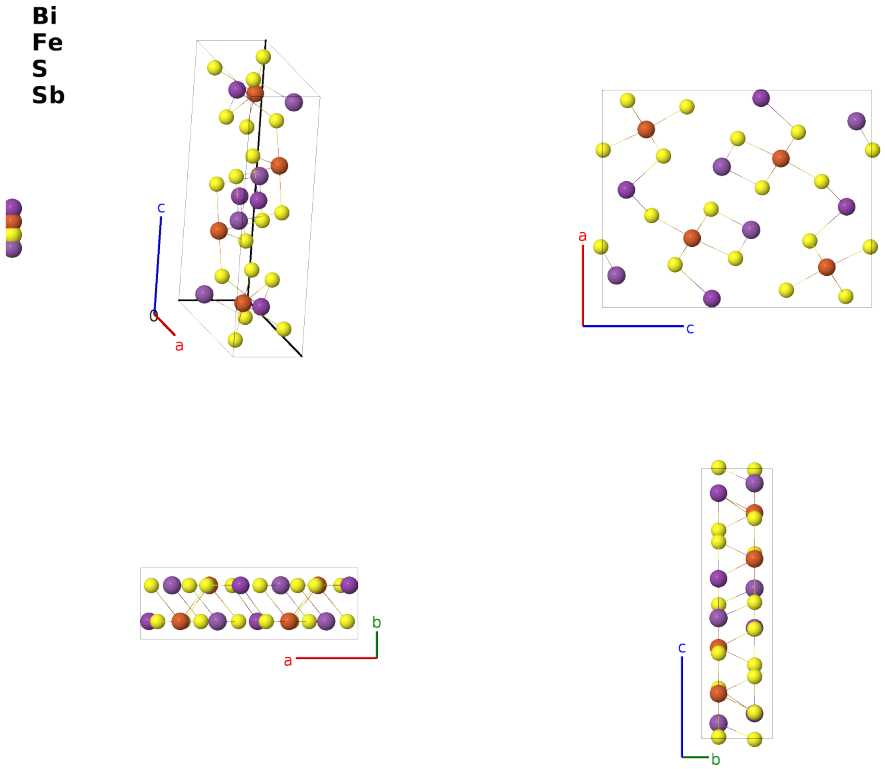

Prototype	$BiFeS_4Sb$
AFLOW prototype label	ABC4D_oP28_62_c_c_4c_c-001
Mineral name	garavellite
ICSD	155236
CCDC	1671849
Pearson symbol	oP28
Space group number	62
Space group symbol	*Pnma*
AFLOW prototype command	`aflow --proto=ABC4D_oP28_62_c_c_4c_c-001 --params=`$a, b/a, c/a, x_1, z_1, x_2, z_2, x_3, z_3, x_4, z_4, x_5, z_5, x_6, z_6, x_7, z_7$

Other compounds with this structure
$EuGdBiS_4$

- This is the quaternary form of the binary Eu_3O_4 and the ternary Bi_2PbS_4. We chose it for the prototype as it is the earliest such entry in the ICSD.

Simple Orthorhombic primitive vectors

$$\mathbf{a_1} = a\,\hat{\mathbf{x}}$$
$$\mathbf{a_2} = b\,\hat{\mathbf{y}}$$
$$\mathbf{a_3} = c\,\hat{\mathbf{z}}$$

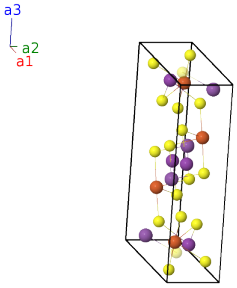

Basis vectors

		Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B_1}$	=	$x_1\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_1\,\mathbf{a}_3$	=	$ax_1\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_1\,\hat{\mathbf{z}}$	(4c)	Bi I
$\mathbf{B_2}$	=	$-\left(x_1 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_1 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_1 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_1 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	Bi I
$\mathbf{B_3}$	=	$-x_1\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_1\,\mathbf{a}_3$	=	$-ax_1\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_1\,\hat{\mathbf{z}}$	(4c)	Bi I
$\mathbf{B_4}$	=	$\left(x_1 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_1 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_1 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_1 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	Bi I
$\mathbf{B_5}$	=	$x_2\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_2\,\mathbf{a}_3$	=	$ax_2\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_2\,\hat{\mathbf{z}}$	(4c)	Fe I
$\mathbf{B_6}$	=	$-\left(x_2 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_2 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_2 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_2 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	Fe I
$\mathbf{B_7}$	=	$-x_2\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_2\,\mathbf{a}_3$	=	$-ax_2\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_2\,\hat{\mathbf{z}}$	(4c)	Fe I
$\mathbf{B_8}$	=	$\left(x_2 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_2 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_2 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_2 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	Fe I
$\mathbf{B_9}$	=	$x_3\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_3\,\mathbf{a}_3$	=	$ax_3\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_3\,\hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B_{10}}$	=	$-\left(x_3 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_3 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_3 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_3 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B_{11}}$	=	$-x_3\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_3\,\mathbf{a}_3$	=	$-ax_3\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_3\,\hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B_{12}}$	=	$\left(x_3 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_3 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_3 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_3 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B_{13}}$	=	$x_4\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_4\,\mathbf{a}_3$	=	$ax_4\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_4\,\hat{\mathbf{z}}$	(4c)	S II
$\mathbf{B_{14}}$	=	$-\left(x_4 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_4 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_4 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	S II
$\mathbf{B_{15}}$	=	$-x_4\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_4\,\mathbf{a}_3$	=	$-ax_4\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_4\,\hat{\mathbf{z}}$	(4c)	S II
$\mathbf{B_{16}}$	=	$\left(x_4 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_4 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_4 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_4 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	S II
$\mathbf{B_{17}}$	=	$x_5\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_5\,\mathbf{a}_3$	=	$ax_5\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_5\,\hat{\mathbf{z}}$	(4c)	S III
$\mathbf{B_{18}}$	=	$-\left(x_5 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_5 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_5 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_5 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	S III
$\mathbf{B_{19}}$	=	$-x_5\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_5\,\mathbf{a}_3$	=	$-ax_5\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_5\,\hat{\mathbf{z}}$	(4c)	S III

$\mathbf{B_{20}}$	=	$\left(x_5 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_5 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_5 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_5 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	S III
$\mathbf{B_{21}}$	=	$x_6\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_6\,\mathbf{a}_3$	=	$ax_6\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_6\,\hat{\mathbf{z}}$	(4c)	S IV
$\mathbf{B_{22}}$	=	$-\left(x_6 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_6 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_6 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_6 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	S IV
$\mathbf{B_{23}}$	=	$-x_6\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_6\,\mathbf{a}_3$	=	$-ax_6\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_6\,\hat{\mathbf{z}}$	(4c)	S IV
$\mathbf{B_{24}}$	=	$\left(x_6 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_6 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_6 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_6 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	S IV
$\mathbf{B_{25}}$	=	$x_7\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_7\,\mathbf{a}_3$	=	$ax_7\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_7\,\hat{\mathbf{z}}$	(4c)	Sb I
$\mathbf{B_{26}}$	=	$-\left(x_7 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_7 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_7 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_7 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	Sb I
$\mathbf{B_{27}}$	=	$-x_7\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_7\,\mathbf{a}_3$	=	$-ax_7\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_7\,\hat{\mathbf{z}}$	(4c)	Sb I
$\mathbf{B_{28}}$	=	$\left(x_7 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_7 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_7 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_7 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	Sb I

References

[1] L. Bindi and S. Menchetti, *Garavellite, $FeSbBiS_4$, from the Caspari mine, North Rhine-Westphalia, Germany: composition, physical properties and determination of the crystal structure*, Mineral. and Petrol. **85**, 131–139 (2005), doi:10.1007/s00710-005-0083-7.

Found in

[1] ICSD, *$FeSbBiS_4$, Inorganic Crystal Structure Database*. ID 155236.

First cited in

N. Anderson, M. J. Mehl, H. Eckert, S. Divilov, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 5*. Submitted to Computational Materials Science (2026).