


Arsenopyrite (FeAsS, $E0_7$) Structure: ABC_mP12_14_e_e_e-002

This structure originally had the label ABC_mP12_14_e_e_e. Calls to that address will be redirected here.

Cite this page as: D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/p/RH3X>

https://aflow.org/p/ABC_mP12_14_e_e_e-002

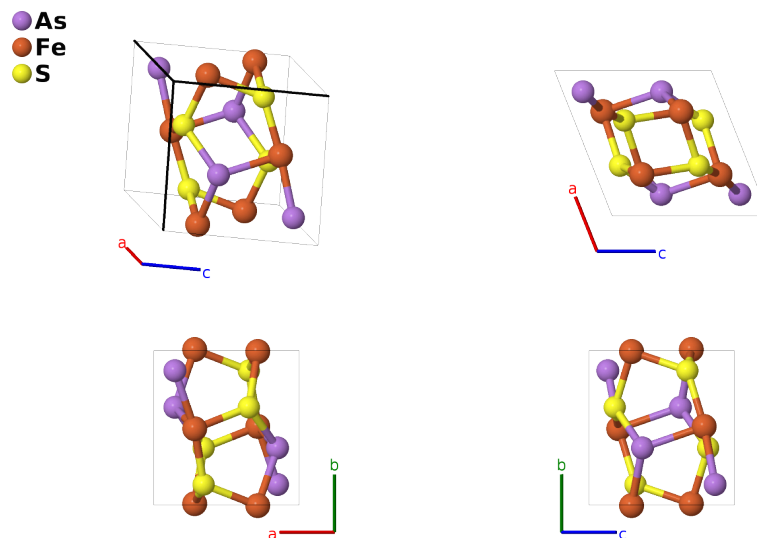

Prototype	AsFeS
AFLOW prototype label	ABC_mP12_14_e_e_e-002
<i>Strukturbericht</i> designation	$E0_7$
Mineral name	arsenopyrite
ICSD	185809
Pearson symbol	mP12
Space group number	14
Space group symbol	$P2_1/c$
AFLOW prototype command	<code>aflow --proto=ABC_mP12_14_e_e_e-002 --params=a, b/a, c/a, β, x_1, y_1, z_1, x_2, y_2, z_2, x_3, y_3, z_3</code>

Other compounds with this structure


AuTeI, FeSbS (gudmundite), OsAsS, OsAsSe, OsPS, OsPSe, OsSbS, RhAsSb, RuAsS, RuAsSe, RuAsTe, RuPS, RuPSe, RuSbS, RuSbSe, RuSbTe, CoAs₂ (clinosafflorite), CoSb₂, HfO₂, IrAs₂ (iridarsenite), IrN₂, MoO₂ (tugarinovite), ReO₂, TcO₂, VO₂, WO₂

- This is very similar to $C43$ Baddeleyite, ZrO₂.

Simple Monoclinic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}\end{aligned}$$

a_1 a_2
 a_3



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$x_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	=	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	As I
\mathbf{B}_2	$-x_1 \mathbf{a}_1 + (y_1 + \frac{1}{2}) \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_1 + c(z_1 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_1 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	As I
\mathbf{B}_3	$-x_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	=	$-(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} - cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	As I
\mathbf{B}_4	$x_1 \mathbf{a}_1 - (y_1 - \frac{1}{2}) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_1 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	As I
\mathbf{B}_5	$x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	Fe I
\mathbf{B}_6	$-x_2 \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_2 + c(z_2 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Fe I
\mathbf{B}_7	$-x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	Fe I
\mathbf{B}_8	$x_2 \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Fe I
\mathbf{B}_9	$x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	S I
\mathbf{B}_{10}	$-x_3 \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	S I
\mathbf{B}_{11}	$-x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	S I
\mathbf{B}_{12}	$x_3 \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	S I

References

- [1] L. Bindi, Y. Moëlo, P. Léone, and M. Suchaud, *Stoichiometric Arsenopyrite, FeAsS, from La Roche-Balue Quarry, Loire-Atlantique, France: Crystal Structure And Mössbauer Study*, *Can. Min.* **50**, 471–479 (2012), doi:10.3749/canmin.50.2.471.