





NaSi Structure: AB_mC32_15_2f_2f-001

Cite this page as: H. Eckert, S. Divilov, A. Zettel, M. J. Mehl, D. Hicks, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*. In preparation.

<https://aflow.org/p/58NH>

https://aflow.org/p/AB_mC32_15_2f_2f-001


● Na
● Si

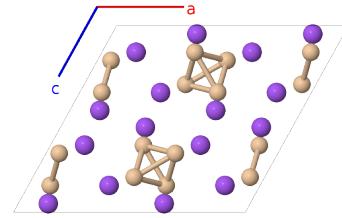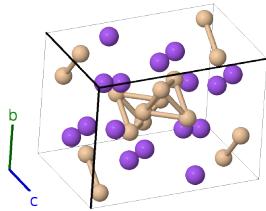

Prototype	NaSi
AFLOW prototype label	AB_mC32_15_2f_2f-001
ICSD	43276
Pearson symbol	mC32
Space group number	15
Space group symbol	$C2/c$
AFLOW prototype command	<pre>aflow --proto=AB_mC32_15_2f_2f-001 --params=a,b/a,c/a,\beta,x1,y1,z1,x2,y2,z2,x3,y3,z3,x4,y4,z4</pre>

Base-centered Monoclinic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{1}{2}b\hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}b\hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}\end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
B₁	$(x_1 - y_1) \mathbf{a}_1 + (x_1 + y_1) \mathbf{a}_2 + z_1 \mathbf{a}_3$	=	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(8f)	Na I
B₂	$-(x_1 + y_1) \mathbf{a}_1 - (x_1 - y_1) \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_1 + c(z_1 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Na I
B₃	$-(x_1 - y_1) \mathbf{a}_1 - (x_1 + y_1) \mathbf{a}_2 - z_1 \mathbf{a}_3$	=	$-(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} - cz_1 \sin \beta \hat{\mathbf{z}}$	(8f)	Na I
B₄	$(x_1 + y_1) \mathbf{a}_1 + (x_1 - y_1) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Na I
B₅	$(x_2 - y_2) \mathbf{a}_1 + (x_2 + y_2) \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(8f)	Na II
B₆	$-(x_2 + y_2) \mathbf{a}_1 - (x_2 - y_2) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_2 + c(z_2 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Na II
B₇	$-(x_2 - y_2) \mathbf{a}_1 - (x_2 + y_2) \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(8f)	Na II
B₈	$(x_2 + y_2) \mathbf{a}_1 + (x_2 - y_2) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Na II
B₉	$(x_3 - y_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Si I
B₁₀	$-(x_3 + y_3) \mathbf{a}_1 - (x_3 - y_3) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Si I
B₁₁	$-(x_3 - y_3) \mathbf{a}_1 - (x_3 + y_3) \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Si I
B₁₂	$(x_3 + y_3) \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Si I
B₁₃	$(x_4 - y_4) \mathbf{a}_1 + (x_4 + y_4) \mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	Si II
B₁₄	$-(x_4 + y_4) \mathbf{a}_1 - (x_4 - y_4) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Si II
B₁₅	$-(x_4 - y_4) \mathbf{a}_1 - (x_4 + y_4) \mathbf{a}_2 - z_4 \mathbf{a}_3$	=	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	Si II
B₁₆	$(x_4 + y_4) \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Si II

References

- [1] J. Witte, H. G. Schnering, and W. Klemm, *Das Verhalten der Alkalimetalle zu Halbmetallen. XI. Die Kristallstruktur von NaSi und NaGe*, Z. Anorganische und Allgemeine Chemie **327**, 260–273 (1964), doi:10.1002/zaac.19643270319.

Found in

- [1] D. Hao, M. Bu, Y. Wang, Y. Tang, Q. Gao, M. Wang, B. Hu, and Y. Du, *Thermodynamic Modeling of the Na-X (X = Si, Ag, Cu, Cr) Systems*, Journal of Mining and Metallurgy B **48**, 273–282 (2012).