


α -Ga (A11) Structure: A_oC8_64_f-001

This structure originally had the label A_oC8_64_f.alpha-Ga. Calls to that address will be redirected here.

Cite this page as: M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017

<https://aflow.org/p/JS9R>

https://aflow.org/p/A_oC8_64_f-001

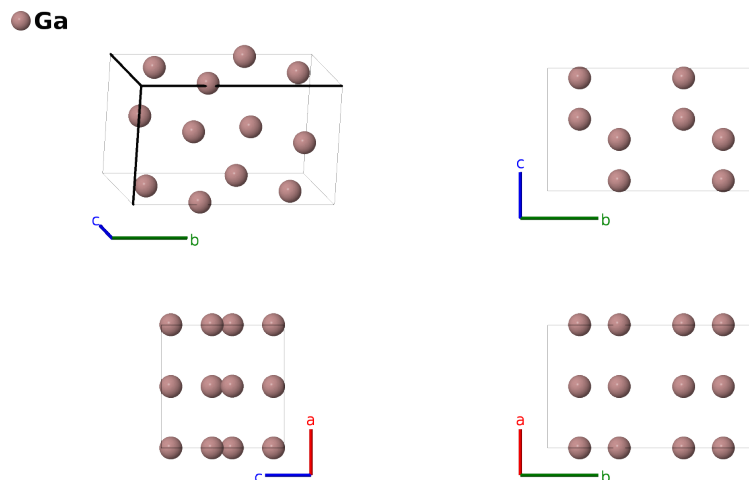

Prototype	Ga
AFLOW prototype label	A_oC8_64_f-001
Strukturbericht designation	A11
ICSD	43388
Pearson symbol	oC8
Space group number	64
Space group symbol	<i>Cmce</i>
AFLOW prototype command	<code>aflow --proto=A_oC8_64_f-001 --params=a, b/a, c/a, y1, z1</code>

- α -gallium (A11), molecular iodine (A14), and black phosphorous (A17) all share the same AFLOW label, A_oC8_64_f. The structures are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.


Base-centered Orthorhombic primitive vectors

a_1 a_3 a_2

$$\mathbf{a}_1 = \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}}$$

$$\mathbf{a}_2 = \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}}$$

$$\mathbf{a}_3 = c \hat{\mathbf{z}}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
\mathbf{B}_1	$= -y_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$by_1 \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(8f)	Ga I
\mathbf{B}_2	$= (y_1 + \frac{1}{2}) \mathbf{a}_1 - (y_1 - \frac{1}{2}) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(8f)	Ga I
\mathbf{B}_3	$= -(y_1 - \frac{1}{2}) \mathbf{a}_1 + (y_1 + \frac{1}{2}) \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \hat{\mathbf{z}}$	(8f)	Ga I
\mathbf{B}_4	$= y_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-by_1 \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	(8f)	Ga I

References

- [1] B. D. Sharma and J. Donohue, *A refinement of the crystal structure of gallium*, Z. Kristallogr. **117**, 293–300 (1962), doi:10.1524/zkri.1962.117.4.293.

Found in

- [1] R. T. Downs and M. Hall-Wallace, *The American Mineralogist Crystal Structure Database*, Am. Mineral. **88**, 247–250 (2003).